

Review

Effects of Flue Gas Impurities on the Performance of Rare Earth Denitration Catalysts

Xue Bian ^{*}, Kaikai Lv, Ming Cai, Peng Cen and Wenyuan Wu

Key Laboratory of Ecological Metallurgy of Multi-Metal Intergrown Ores of Ministry of Education, School of Metallurgy, Northeastern University, Shenyang 110819, China; 2171640@stu.neu.edu.cn (K.L.); 1910573@stu.neu.edu.cn (M.C.); cenpeng@smm.neu.edu.cn (P.C.); wuwuy@smm.neu.edu.cn (W.W.)

* Correspondence: bianx@smm.neu.edu.cn

Abstract: Selective catalytic reduction (SCR) is still the most widely used process for controlling NO_x gas pollution. Specifically, commercial vanadium-based catalysts have problems such as narrow operating temperature range and environmental pollution. Researchers have developed a series of cerium-based catalysts with good oxygen storage performance and excellent redox performance of CeO₂. However, the anti-poisoning performance of the catalyst is the key to its application. There are many kinds of impurities in the flue gas, which has a huge impact on the catalyst. The deposition of substances, the reduction of active sites, the reduction of specific surface area, and the reduction of chemically adsorbed oxygen will affect the denitration activity of the catalyst to varying degrees, and the poisoning mechanism of different impurities on the catalyst is also different. Therefore, this review divides the impurities contained in flue gas into different types such as alkali metals, alkaline earth metals, heavy metals, and non-metals, and summarizes the effects and deactivation mechanisms of various types of impurities on the activity of rare earth catalysts. Finally, we hope that this work can provide a valuable reference for the development and application of NH₃-SCR catalysts for rare earth denitration in the field of NO_x control.

Keywords: rare earth catalyst; flue gas impurities; denitration activity; poisoning mechanism



Citation: Bian, X.; Lv, K.; Cai, M.; Cen, P.; Wu, W. Effects of Flue Gas Impurities on the Performance of Rare Earth Denitration Catalysts. *Catalysts* **2022**, *12*, 808. <https://doi.org/10.3390/catal12080808>

Academic Editor: Antonella Gervasini

Received: 13 June 2022

Accepted: 20 July 2022

Published: 23 July 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Nitrogen oxides (NO_x) cause a series of air pollution problems such as acid rain, photochemical smog, and ozone depletion [1]. Typically, NO_x emissions are produced by stationary or mobile sources, including coal-fired power plants and automobile engines. In order to reduce the emission of NO_x, various denitration technologies such as SNCR (non-selective catalytic reduction), SCR (selective catalytic reduction), and SNCR-SCR combined method have been developed. Among them, the SCR method is a mature and efficient denitration method [2]. Selective catalytic reduction (SCR) with NH₃ is the best technology for NO_x removal in terms of removal efficiency, stability and cost. At present, most commercial SCR denitration catalysts are vanadium-based catalysts, which are widely used due to their better thermal stability and denitration efficiency, but vanadium-based catalysts also have obvious shortcomings. For example, the working temperature range is relatively narrow (300~400 °C), and they exhibit poor resistance to alkali metals, heavy metals, sulfur dioxide, etc. However, because vanadium is highly toxic, usage of catalytic material with large amounts of vanadium can lead to further hazard waste environmental problem [3]. Therefore, the development of alternative low-temperature SCR catalysts has attracted much attention in recent years.

In order to solve the problems existing in vanadium-based catalysts, a series of “environmental friendly” catalysts were born; for example, Cu- and Fe-exchanged zeolite catalysts showed good SCR activities [4–7]. Other nontoxic transition metal oxide-based catalysts such as CeO₂-TiO₂-based catalysts [8,9], FeO_x-TiO₂-based catalysts [10–13], and

CeO₂-WO_x-based catalysts [14,15], etc. have also been investigated as potential alternatives. But rare earth-based catalysts stand out among these catalysts. Today, rare earth-based denitration catalysts have become a research focus. The rare earth elements represented by cerium oxide have excellent oxygen storage and redox properties and unique redox pairs Ce³⁺/Ce⁴⁺ [16–19], and was used as the active component of the catalyst, such as CeO₂-TiO₂ [20], CeO₂/WO₃ [21,22], CeO₂/WO₃-TiO₂ [23,24], CeO₂-MoO₃-TiO₂ [25,26], Ce/TiZrO_x [27], Ce₂/Cu₄Al₁O_x [28] and Ce-Cu/TiO₂ [29]. The results of numerous studies have shown that the rare earth-based catalysts have wider denitration temperature range, higher efficiency, and higher resistance to SO₂, especially the cerium-based polymetallic oxide catalysts, which further improve the redox performance, surface acidity, and resistance to H₂O/SO₂. For example, Mn-Ce/TiO₂ catalyst, MnO_x have many variable valence states. Its oxides can be interconverted and exhibit good catalytic activity at low temperature [30–33]. Meanwhile, ceria can reduce the loss of specific surface area and pore volume during calcination, thereby improving the oxygen storage capacity and redox performance of the catalyst. Therefore, it has great potential in the field of low-temperature SCR catalysts [16,17,34–40], promising to replace traditional vanadium-based catalysts.

Rare earth-based flue gas denitration catalysts have broad application prospects in sintering, coking, cement, glass and other industries. Although its denitration performance is excellent, the denitration process performs well, there are still some problems to be solved for rare earth-based catalysts. The sulfur dioxide, alkali metals, alkaline earth metals, heavy metals and other impurities contained in the flue gas will irreversibly affect the denitration efficiency and service life of the catalyst [41]. In addition, there are a large number of non-metallic impurities in the flowing gas of coal-fired boilers and municipal solid waste incinerators, such as phosphorus, hydrogen halide, etc., and the influence of these impurities on the catalyst cannot be ignored. Therefore, researchers have carried out a lot of research on the influence and mechanism of different impurities on the denitration performance of catalysts. In this paper, the impurities in flue gas are classified, and the influence rules of different types of impurities on the performance of rare earth denitration catalysts are summarized, in order to provide a reference for the development and application of rare earth denitration catalysts.

2. The Influence of Metal Impurities

It is well known that the influence of metal impurities on the catalyst is very large, including alkali metals, alkaline earth metals and heavy metals. Among these metal impurities are K, Na, Pb, and their compounds. These substances deposited on the surface of the catalyst, thus reducing the SCR activity of the catalyst [42]. Next, the specific effects of these metal impurities on the catalyst are discussed.

2.1. Influence of Alkali Metals

The alkali metal elements are the most harmful element to chemically poison a catalytic material, including alkali metal oxides, alkali metal sulfates and alkali metal chlorides [43]. These substances typically come from fluid gases from static sources, such as coal, biomass, power plants, etc. Studies had shown that in high mobility gases, the hydrolysis or ion exchange of alkali metals (K and Na) will neutralize the acid sites on the catalyst surface, and the presence of alkali metals will also reduce the amount of NH₃ adsorbed by the catalyst. It has a serious deactivation effect on traditional vanadium-based catalysts, and the deactivation is more serious with the increase of its content. In addition, the different forms of alkali metals have different effects on catalyst activity. Many researchers have studied the influence of alkali metals on vanadium-based catalysts, but the research on cerium-based catalysts is not in-depth. With the promotion of cerium-based catalysts, it is necessary to study the influence of alkali metals on cerium-based catalysts from the perspective of industrial application.

Peng et al. [22] studied the effect and mechanism of K and Na on the performance of CeO₂-WO₃ catalysts. Figure 1a showed the activity comparisons of V-W/Ti and CeW catalysts

and corresponding 1 wt% K-doped catalysts at temperature ranging from 100 to 300 °C under a GHSV of 60,000 h⁻¹. Without K doping, the activity of the CeW catalyst was slightly higher than the V-W/Ti catalyst below 280 °C, with a maximum of nearly 99% NO_x conversion at 220 °C, maintained up to 300 °C. During the NO_x conversion test, when 1% K was loaded, the activity of the V-W/Ti catalyst dropped to 20% at 200 °C, while the CeW catalyst remained above 70% at the same temperature. It can be concluded that the CeW catalyst is more resistant to alkali metals than the traditional vanadium-based catalyst V-W/Ti below 300 °C. For CeW catalyst, The Na&K catalyst was less active at low temperatures but yielded higher NO_x conversion above 200 °C compared with the 1 K and 0.58 Na catalysts. At a given molar concentration, K gave rise to more deactivation than Na below 200 °C, due to its more potent neutralizing properties (Figure 1b). At the same time, with the increase of the concentration of alkali metal loaded on the catalyst, the denitration efficiency of the catalyst decreases more obviously at the same temperature. NH₃-TPD, in-situ infrared (DRIFTS), H₂-TPR analysis, and DFT calculation showed that K and Na decreased the content of acid sites on the catalyst surface (Figure 2), thereby reducing the NH₃ gas adsorption amount and weakening the denitration performance. In addition, the DFT calculation in Figure 3 H₂O can bond to the surface with a hydrogen atom interacting with the moved oxygen (1.38 Å). The bond length of H–O in H₂O was 1.11 Å, which was longer than the standard H–O bond in H₂O (0.98 Å) and the other H–O bond is remained unchanged. This model indicated that the hydrolysis dissociation is H⁺ and OH⁻, and H⁺ combines with the O element on the catalyst surface to form the Brønsted acidic site. Therefore, in the experiment, the denitration efficiency of the poisoned catalyst can be restored to 90% of that of the fresh catalyst after hot water cleaning (Figure 1c). Du et al. [3] also used DFT calculation to find that the strong interaction of K ions with cerium oxide and titanium oxide reduced the oxygen vacancy and NH₃ gas adsorption of the catalyst, thereby reducing the reduction and denitration performance of the cerium-titanium oxide catalyst.

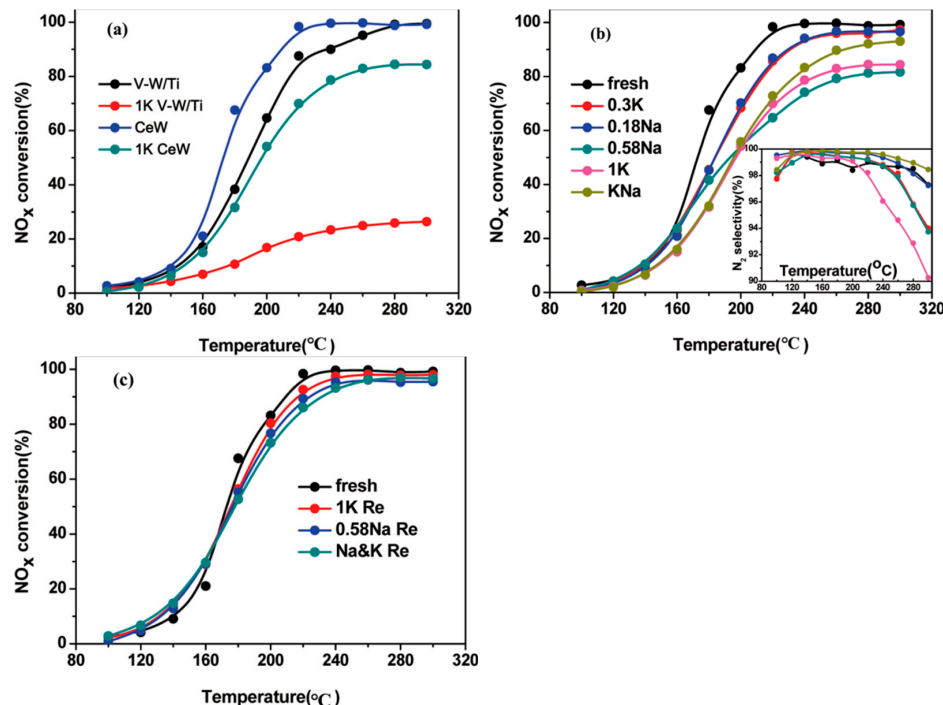


Figure 1. (a) Comparison of NH₃–SCR activity of V–W/Ti and CeW catalysts with corresponding 1 wt% K-doped catalysts; (b) The NH₃–SCR activity and N₂ selectivity of CeW and alkali-doped Ce W catalysts; (c) The NH₃–SCR activity of the regenerated poisoned catalysts. Reaction conditions: catalyst = 300 mg, [NO] = [NH₃] = 500 ppm, [O₂] = 3%, total flow rate = 300 mL/min, GHSV = 60,000 h⁻¹ [22].

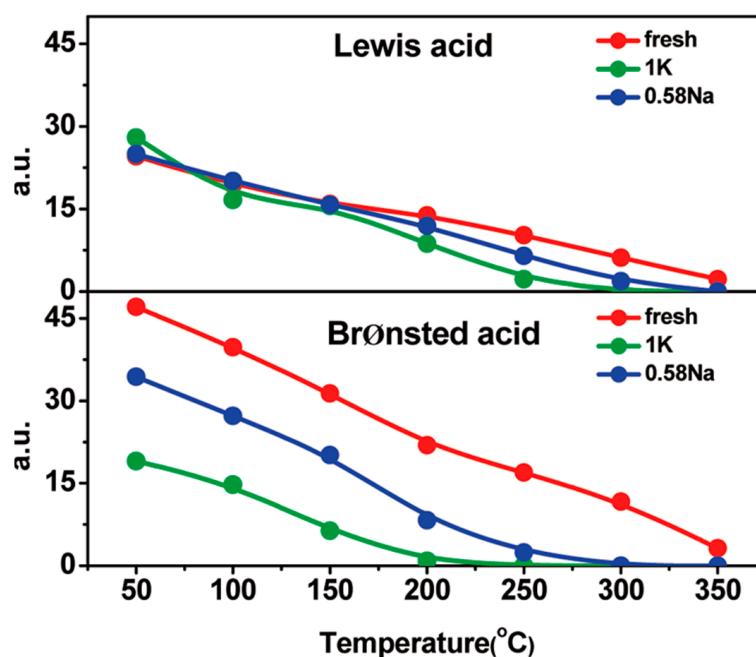


Figure 2. The strength and quantity of Lewis and Brønsted acid sites calculated from DRIFTS spectra, centered at 1160 cm^{-1} (Lewis acid) and 1430 cm^{-1} (Brønsted acid), respectively [22].

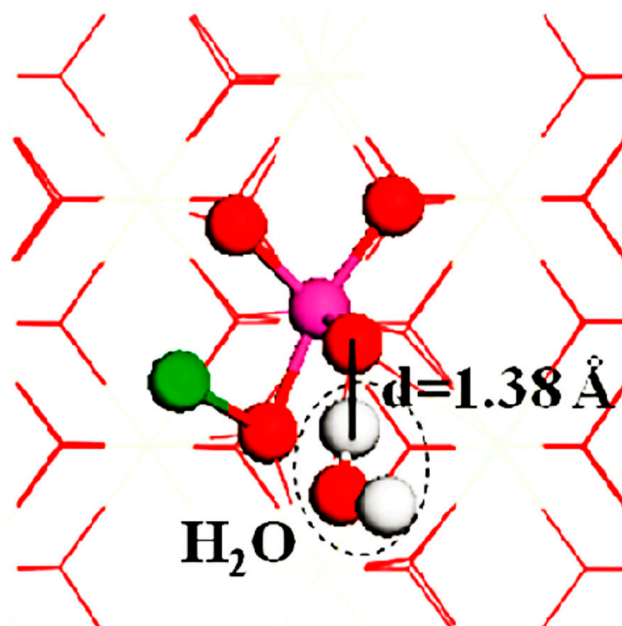


Figure 3. H₂O adsorbed on the K-poisoned (110) catalyst surface [22].

Wang et al. [44] studied the effect of alkali metal K and Na loaded on the denitration performance of Ce/TiO₂ catalyst by coprecipitation method. The results showed that the denitration efficiency of fresh catalyst reached 90% at 200 °C, while the denitration efficiency of Na and K loaded with 0.2 mol ratio of Ce to Na decreased to 25% and 10% respectively at this temperature. Zhou's study [45] showed that the influence of alkali metal salts on Ce-Ti catalyst was in the order of nitrate < chloride < carbonate. The catalyst was almost completely inactivated when potassium carbonate was loaded. When sodium carbonate was loaded, the denitration efficiency at 100 °C decreased from more than 90% to about 15%.

In addition, Jiang et al. [46] also studied the influence of alkali metal compounds sodium oxide and sodium chloride on the denitration performance of CeO₂-TiO₂ catalyst.

The results in Figure 4 showed that both sodium oxide and sodium chloride lead to catalyst deactivation, and the effect of sodium oxide is greater than that of sodium chloride. At 350 °C, when the molar ratio of Na: Ce = 0.5 Na₂O was added, the catalyst almost had no denitration effect. When NaCl with molar ratio of Na: Ce = 0.5 was added, the denitration performance of the catalyst decreased to 60%. The XRD patterns of the fresh and Na-poisoned CT samples indicated the interaction between Na species and TiO₂ (Figure 5a). From the results of XPS, NH₃-TPD (Figure 5b) and in situ DRIFT studies, it was found that the addition of Na could inhibit the transformation of Ce⁴⁺ to Ce³⁺, sodium oxide, and sodium chloride decreased the specific surface area, chemical adsorption of oxygen, surface acidity, and reduction capacity of the catalyst, inhibited the adsorption of NH₃, and reduced the denitration performance. The denitration reaction is still controlled by E-R and L-H mixed mechanism when the catalyst is loaded with sodium oxide and sodium chloride.

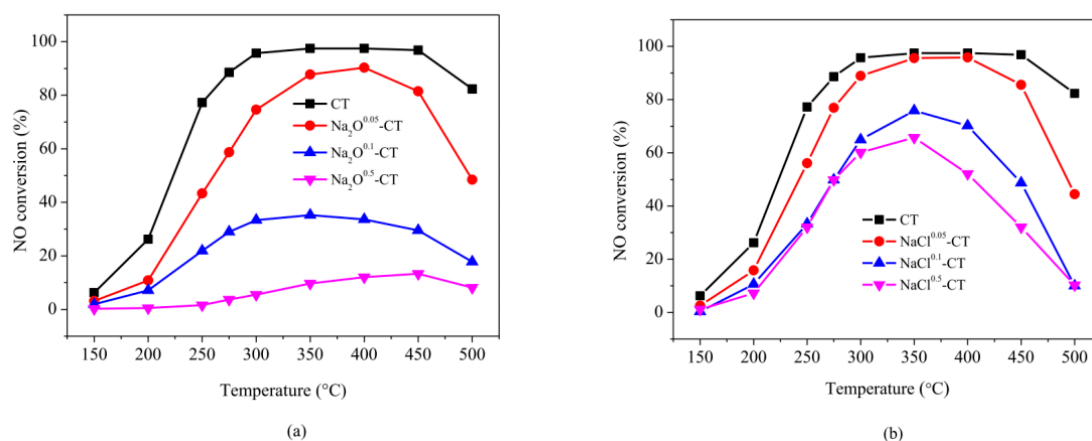


Figure 4. NO conversion of Na₂O^{0.5}-CT (a), NaCl^{0.5}-CT (b). Reaction condition: [NO] = [NH₃] = 1000 ppm, [O₂] = 3 vol%, N₂ balance, total flowrate = 500 mL/min, GHSV = 90,000 h⁻¹ [46].

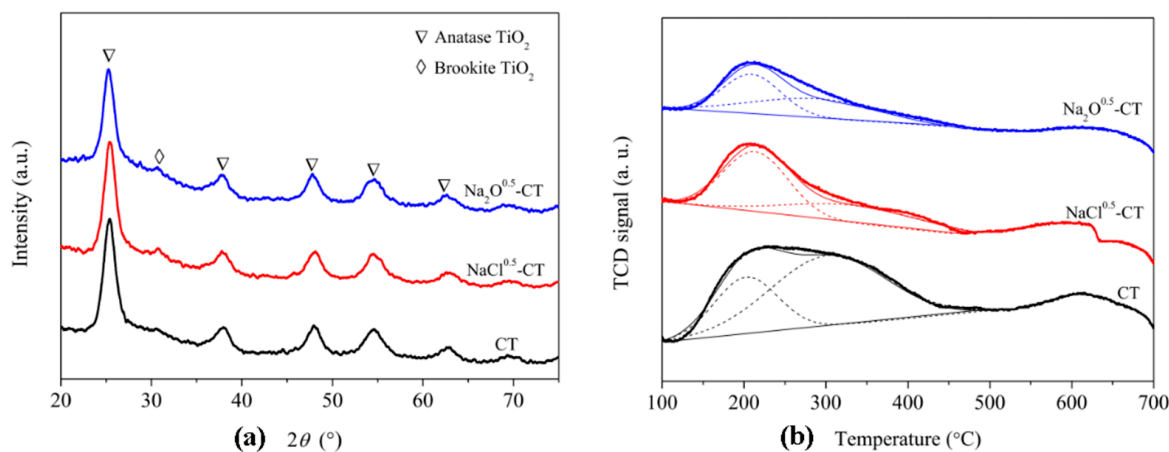


Figure 5. (a) XRD patterns of CT, Na₂O^{0.5}-CT, and NaCl^{0.5}-CT catalysts; (b) NH₃-TPD profiles of CT, Na₂O^{0.5}-CT, and NaCl^{0.5}-CT catalysts [46].

Similarly, for CeO₂-TiO₂ catalyst, the poisoning effect of K₂O is more serious than that of KCl, as shown in Figure 6. When K₂O with molar ratio K: Ce = 0.5 was added below 300 °C, the catalyst was almost completely deactivated. The characterization results showed that, compared to KCl, K₂O could significantly reduce the surface acidity, reduction, Ce³⁺/Ce⁴⁺ ratio, and the concentration of surface chemisorption oxygen of CeO₂-TiO₂ catalyst. In-situ DRIFT results showed that K₂O had a stronger inhibitory effect on NH₃ adsorption on the catalyst surface than KCl. The introduction of K₂O or KCl promoted the adsorption of NO on the catalyst surface, but not all NO_x species were reactive in NH₃-SCR

reaction. These results are further confirmed by DFT calculations [47]. The PDOS, oxygen vacancy, chemical oxygen adsorption, NH_3 and NO_x adsorption energies of $\text{CeO}_2\text{-TiO}_2$ catalysts doped with different K species were calculated by MS Dmol 3. It was found that the introduction of K species weakened the reaction activity on the catalyst surface, inhibited the formation of oxygen vacancies and chemical adsorbed oxygen, and reduced the adsorption of NH_3 on the catalyst surface, all of which led to the decrease of catalytic activity [48].

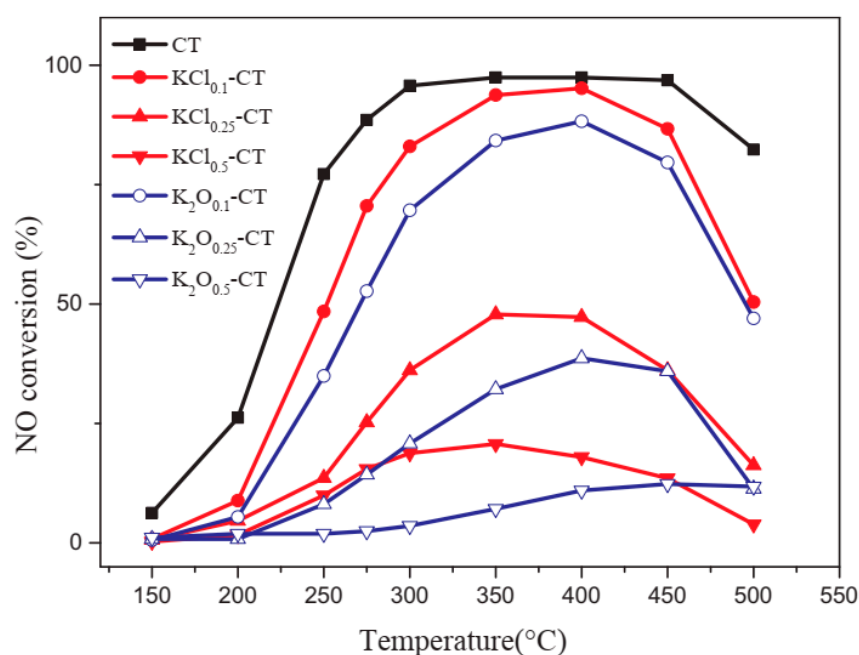


Figure 6. NO conversion of $\text{KCl}_x\text{-CT}$, $\text{K}_2\text{O}_x\text{-CT}$ and CT. Reaction condition: $[\text{NO}] = [\text{NH}_3] = 1000$ ppm, $[\text{O}_2] = 3\%$, N_2 balance, total flow rate = 500 mL/min, GHSV = 90,000 h^{-1} [48].

The above studies show that the existence forms and types of alkali metals have different effects on cerium-based catalysts.

2.2. Effect of Alkaline Earth Metal Ca

Although the low temperature SCR denitration reactor is mostly arranged after the dust removal system, there is still a small amount of residual dust in the flue gas. The catalyst is exposed to the flue gas with complex components for a long time, and it is easy to be inactivated by K, Na, Ca, Si, and As [49], especially when the low temperature SCR denitration technology is used in some industrial furnaces, such as glass furnaces, cement furnaces, etc. A large amount of alkaline earth metal Ca in flue gas will have a great influence on the activity of the catalyst [50,51]. The common way of catalyst poisoning caused by alkaline earth metal is that alkaline earth metal oxides (such as CaO) react with SO_3 in their pores to form calcium sulfate, which causes the pores to be blocked. The results of XRD on the catalyst surface by Benson et al. [52] showed that the alkaline earth metal compounds deposited on the catalyst surface are mainly CaSO_4 , and the rest are $\text{Ca}_3\text{Mg}(\text{SiO}_4)_2$ and CaCO_3 . Among them, CaSO_4 and CaCO_3 are obtained by the reaction of CaO with SO_3 and CO_2 , respectively. In addition, similar to alkali metals, alkali-earth metals can also interact with the Brønsted acid sites on the catalyst surface to cause the chemical poisoning of the catalyst, but due to the weak alkaline limit, the poisoning effect is relatively small [53].

The doping of Ca into the catalyst will have a certain effect on the structure, acid site and activity of the catalyst. Liu et al. [54] doped Ca element in $\text{MnO}_x/\text{TiO}_2$ catalyst found that Ca doping could have negative effect on the activities of the $\text{MnO}_x/\text{TiO}_2$ catalysts. However, at a high Ca doping level of 10 wt%, this effect would become dilute, the SCR

activity and NO oxidation were somewhat recovered., due to the formation of CaTiO_3 that weakened the deactivation.

Shen et al. [55] loaded $\text{Ca}(\text{NO}_3)_2$ with a molar ratio of $\text{Ca}/\text{Mn} = 0.5$ on a $\text{Mn-CeO}_x/\text{Ti-PILC}$ catalyst, and found that the denitration efficiency of the catalyst decreased from 90% before loading to 20% at 180 °C. Zhou et al. [56] used the impregnation method to deposit CaCl_2 , CaCO_3 and CaSO_4 on the $\text{Mn-Ce}/\text{TiO}_2$ catalyst, and the denitration efficiency decreased. At 100 °C, the denitration efficiency of the catalyst without calcium loading reached more than 90%, and the denitration efficiency decreased to 80%, 70% and 40% when CaCO_3 , CaSO_4 and CaCl_2 with a mass content of 1% were loaded, respectively. BET, XPS, TPD and other characterizations found that the main reasons for catalyst poisoning were the change of crystal form, the destruction of pore structure, and the reduction of surface active elements and acid sites. Wang et al. [57] studied the effects of CaCl_2 and $\text{Ca}(\text{OH})_2$ on the denitration efficiency of Mn-Ce-Ti catalysts. The results are shown in Figure 7. At 270 °C, the denitration efficiency of Mn-Ce-Ti catalysts exceeded 90%. After $\text{Ca}(\text{OH})_2$ was loaded on the Mn-Ce-Ti catalyst, the denitration efficiency decreased to 75% and 80.8%, respectively.

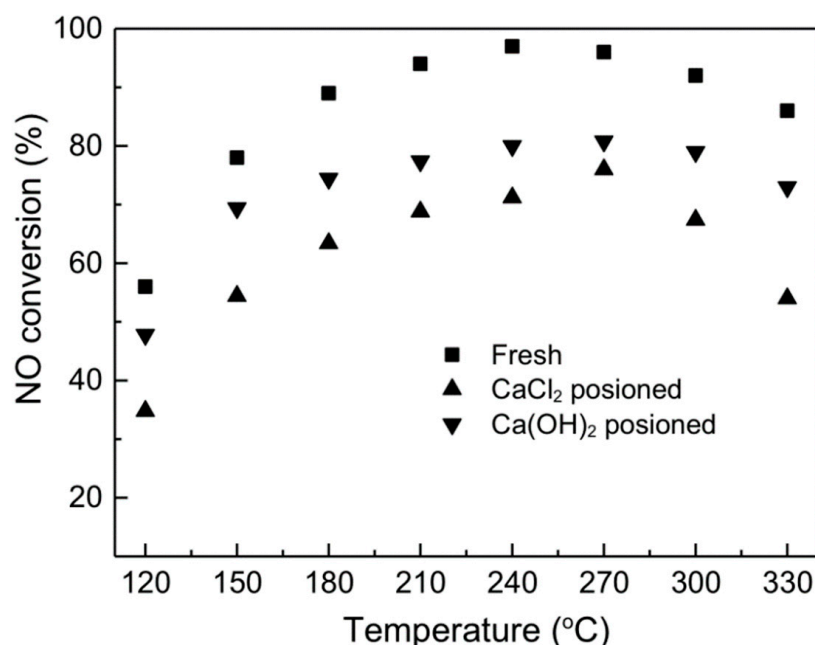


Figure 7. NO conversion over fresh and different Ca-poisoned catalysts [57].

In addition, Li et al. [58] also studied the effect of CaO on the $\text{V}_2\text{O}_5\text{-WO}_3/\text{TiO}_2$ and $\text{CeO}_2\text{-WO}_3$ catalyst. The results showed that CW catalyst had a better CaO resistance effect than VWTcatalyst for SCR (Figure 8). At 200 °C, the denitration efficiency of the catalyst after adding 5 wt% CaO was reduced from about 90% without CaO to 50%. XRD Raman (Figure 9), XPS and other analysis showed that CaO inhibited the reducing ability of the catalyst, and significantly reduced the number of Lewis acid and Brønsted acid sites, which reduced the amount of NH_3 adsorption of the catalyst. At the same time, as shown in Figure 10, Ca and W formed CaWO_4 , which reduces the active components on the catalyst surface, thereby reducing the denitration efficiency. Wang et al. [59] found that the calcium poisoning of the $\text{CeO}_2\text{-WO}_3/\text{TiO}_2$ catalyst is due to the fact that Ca^{2+} hinder the conversion between Ce^{3+} and Ce^{4+} , reduce the Lewis acid site, inhibit the redox ability and NH_3 adsorption, and thus reduce the denitration performance.

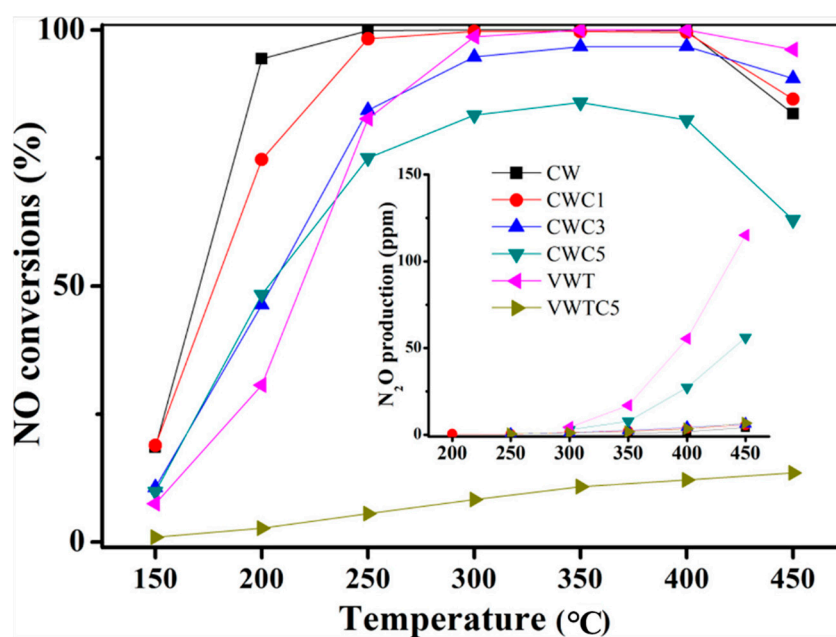


Figure 8. NO conversion and N₂O production of CW, VWT and Ca poisoned catalysts. Reaction condition: catalyst amount = 0.1 g, [NO] = [NH₃] = 500 ppm, [O₂] = 3%, N₂ balance, total flow rate = 200 mL/min, GHSV = 120,000 mL/(g·h) [58].

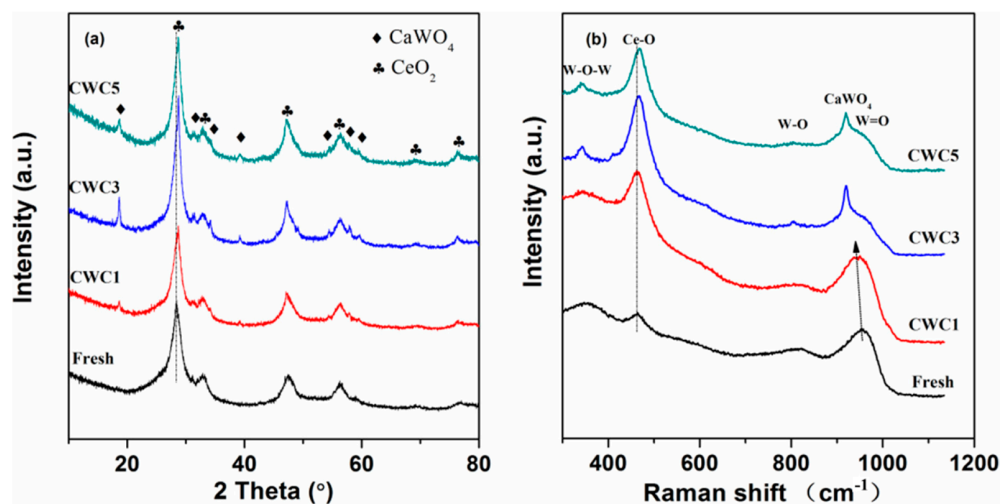


Figure 9. XRD patterns (a) and Raman spectra (b) of fresh and Ca poisoned catalysts [58].

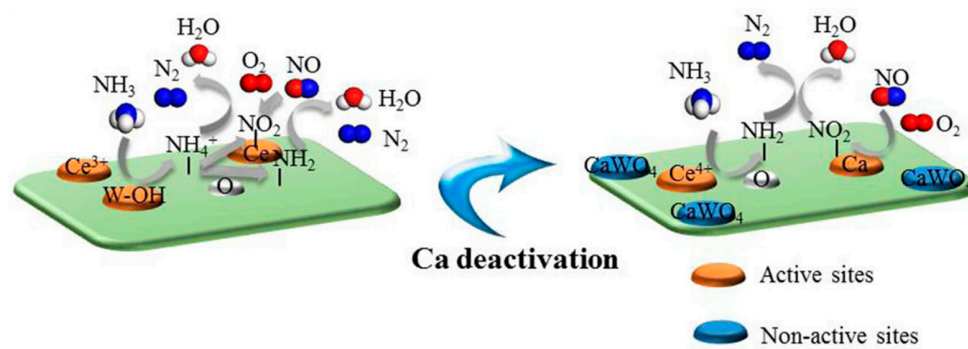


Figure 10. Schematic of calcium poisoning mechanism on CeO₂-WO₃ catalyst [58].

Alkaline earth metals in addition to calcium will affect the activity of the catalyst, and Mg will also affect it. Zhou [45] studied the effect of alkaline earth metal Mg deposition on the denitration performance of Mn-Ce/TiO₂ catalysts. The magnesium deposition of different precursors (MgCO₃, MgCl₂, Mg(NO₃)₂, MgSO₄) were studied, and it was found that the deposition of different magnesium compounds reduced the catalyst activity compared with the fresh catalyst, and with the increase of the alkaline earth metal Mg loading. The inhibitory effect on catalyst de-stocking activity increased gradually. The deposition of MgCO₃ has the strongest inhibitory effect on the catalyst activity, while Mg(NO₃)₂ has the weakest effect. It was found by XRD characterization that the deposition of alkaline earth metal Mg would generate Mn₃O₄ peaks and Mn₂O₃ peaks, which transformed amorphous Mn into crystalline Mn, which was not conducive to the catalytic reaction. It was obtained by BET and NH₃-TPD analysis that the deposition of alkaline earth metal Mg would reduce the specific surface area of the catalyst and destroy the Lewis acid sites on the surface of the catalyst. These changes in physical and chemical properties were the main reasons for the decrease of the denitration activity of the catalyst.

2.3. The Influence of Pb

Lead is one of the typical heavy metals in the flue gas of coal-fired power plants and municipal solid waste incineration power plants. Lead in fluid gases mainly exists in two forms: particles and gases. Part of the lead is adsorbed or condensed on the surface of the fine particles, and the other part of the lead is converted into lead monoxide or lead chloride in the combustion reaction and enters the atmosphere [60–62]. Studies have shown that the presence of lead has a strong toxicity to SCR catalysts. Measured by Chen et al. [63], the content of Pb in the gas is about 0.072–0.258 µg/m³; the concentration of small particles and gaseous Pb emitted into the atmosphere is relatively high, accounting for 67–81% of the total Pb, and are not captured by dust collectors, which may have a serious impact on SCR catalysts.

Jiang [64] found that when the loading of Pb on the power catalyst reaches 0.19%, the NO conversion rate is only 12%. The low-temperature SCR activity was significantly reduced after doping Pb in Mn-Ce/TiO₂ [65]. As shown in Figure 11, when the lead loading is 11%, the NO conversion at 180 °C drops from 100% of the fresh catalyst to 44%. The study of Chen et al. [51] showed that the poisoning effect of lead on SCR catalyst is between the alkali metals potassium and sodium. Guo et al. [66] studied the toxic effects of heavy metals Zn and Pb on the SCR performance of Ce/TiO₂ catalysts, and found that the toxic effects of Pb were more serious. The doping of heavy metal Pb will greatly reduce the specific surface area, pore volume, chemical adsorption oxygen content, and surface acidity of the catalyst, as well as increase the crystallinity and grain size of anatase TiO₂, resulting in deactivation of the catalyst. In addition, the researchers compared the toxicity of PbO and PbCl₂ to certain catalysts. For the V₂O₅/TiO₂ catalyst, the effect of PbCl₂ loading is greater than that of PbO [67,68], the BET specific surface area of the catalyst after PbCl₂ loading is smaller, and the acidity and reducibility are also lower. Yet for CeO₂-TiO₂ catalyst, the result is the opposite, and the effect of PbO generation is greater [69]. From this, it can be concluded that different lead compounds have different effects on different catalysts.

In order to test the influence of PbO on the performance of catalysts, Zhou et al. [70] synthesized a series of Mn-Ce/TiO₂ catalysts doped with PbO by impregnation method. At 200 °C, when the lead-manganese molar ratio reaches 0.5, the NO conversion efficiency of the Mn-Ce/TiO₂ catalyst drops from 96.75% to about 40%. The analysis shows that PbO reduces the reducibility, specific surface area, surface Mn⁴⁺, and Ce³⁺ content, as well as chemisorbed oxygen content of manganese and cerium oxides, resulting in the decrease of SCR performance. The SEM test of Figure 12 showed that the catalyst has obvious aggregation of metal oxides after PbO poisoning. The effect mechanism of PbO on CeO₂-MoO₃/TiO₂ catalyst (as shown in Figure 13) and the reduction in denitration efficiency are due to the formation of a new phase PbMoO₄ between PbO and Mo, and this formation inhibits the conversion of surface Ce⁴⁺ to Ce³⁺, thus significantly reducing the surface acidity and reduction in the catalyst [71]. At

the same time, due to the influence of Pb, the amount of chemisorbed oxygen on the surface of the catalyst is reduced, resulting in the inhibition of the $\text{NO} + \text{O}_2 \rightarrow \text{NO}_2$ reaction, thereby reducing the activity of the catalyst.

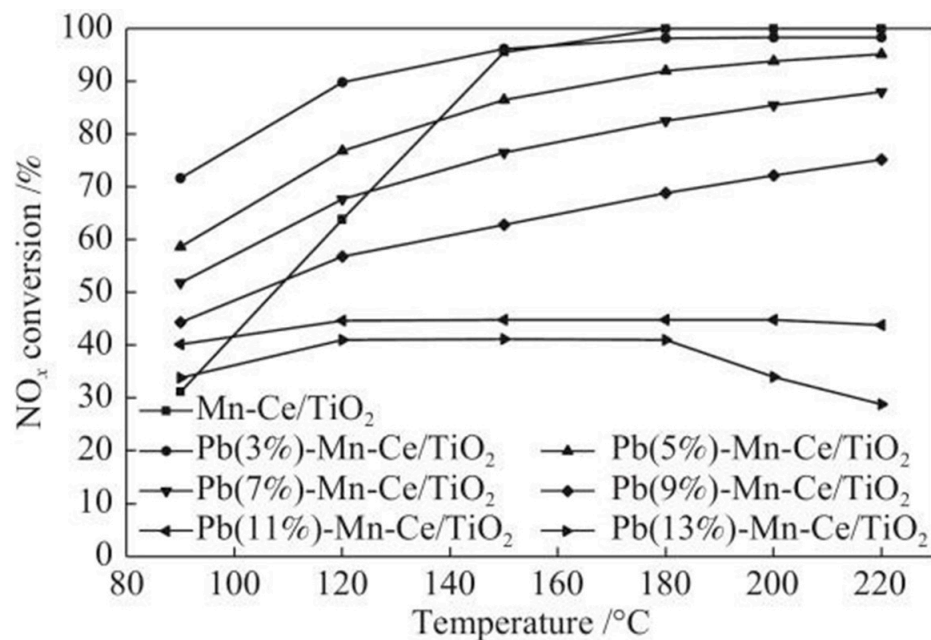


Figure 11. Activity of the Pb(x)-Mn-Ce/TiO₂ catalysts with different Pb loadings(x) in NH₃-SCR of NO reaction conditions: $\varphi\text{NO}_x = 6 \times 10^{-4}$, $\varphi\text{NH}_3 = 6.6 \times 10^{-4}$, $\varphi\text{O}_2 = 3\% \sim 5\%$, GHSV = 8000 h⁻¹ [65].

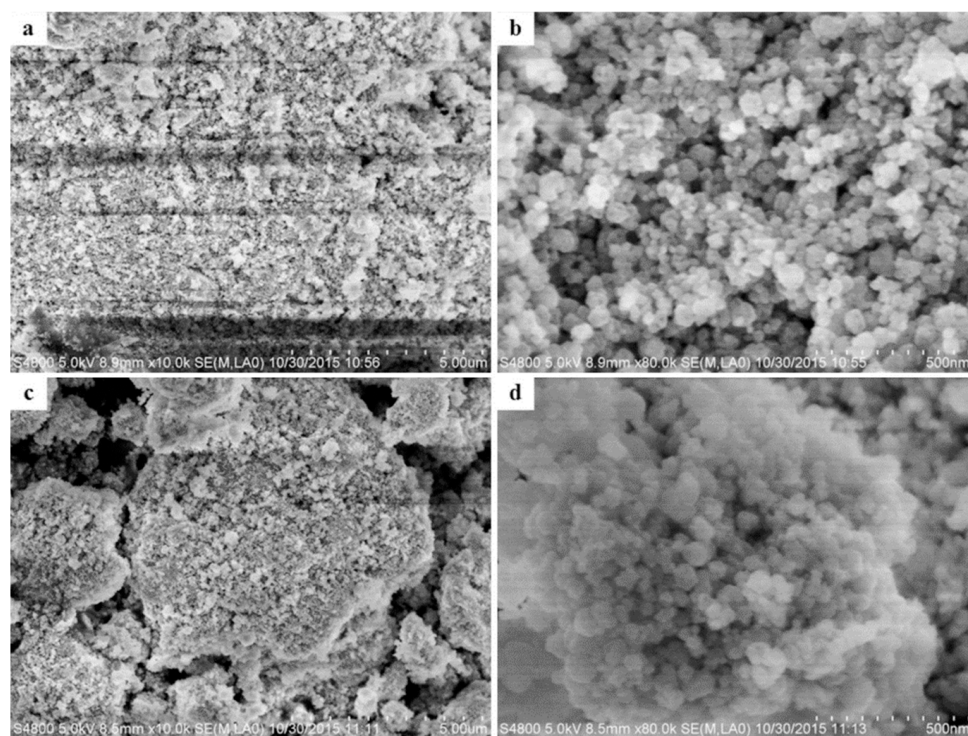


Figure 12. SEM images of the catalysts: (a) Mn-Ce/TiO₂ 10,000 multiplier; (b) Mn-Ce/TiO₂ 80,000 multiplier; (c) Pb (0.5)-Mn-Ce/TiO₂ 10,000 multiplier; (d) Pb (0.5)-Mn-Ce/TiO₂ 80,000 multiplier [70].

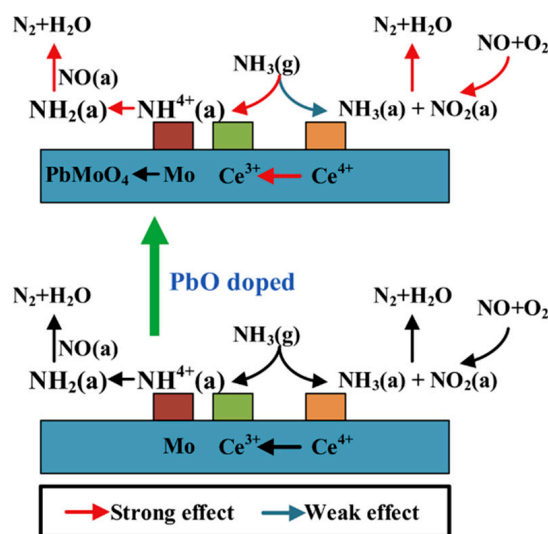


Figure 13. Diagram of PbO poisoning on CMT [71].

Studies have shown that PbCl_2 reduces the redox properties and surface acidity of the catalyst, resulting in a decrease in the denitration efficiency. Kong et al. [72] studied the poisoning mechanism of PbO and PbCl_2 on MC catalysts as shown in Figure 14. The toxicity of PbCl_2 is higher than that of PbO, the reason is that PbCl_2 is easier to form crystalline phase, resulting in smaller BET surface area of MC catalyst. At the same time, the newly formed hydrochloric acid preferentially adsorbs on cerium oxide species, forming inactive Cl^- bonds and ammonium chloride deposition, which further hinders the conversion of Ce^{4+} to Ce^{3+} , and reduces the surface acid sites, resulting in deactivation of the catalyst.

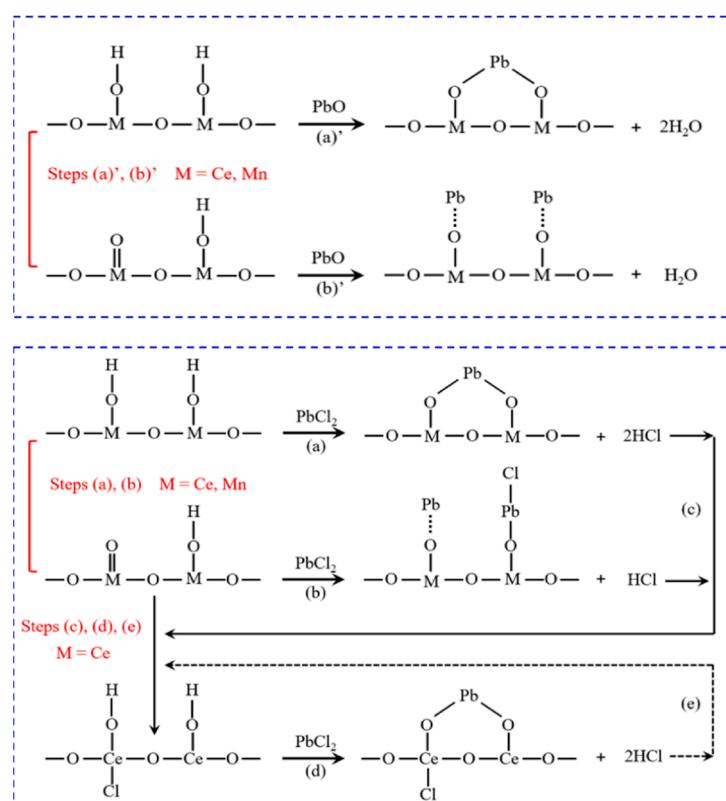


Figure 14. Schematic diagram of PbCl_2 and PbO poisoning mechanisms over MC catalysts [72].

Jiang et al. [69] studied the effects of PbO and PbCl₂ on the poisoning of the CeO₂-TiO₂ catalyst in the denitration process. It was found that the NO conversion decreased significantly with the increase of PbO doping amount. When the molar ratio of Pb to Ce exceeds 0.5, the catalyst is almost completely deactivated (Figure 15a). For PbCl₂-doped catalysts, PbCl₂ has little effect on the catalytic activity when the temperature is lower than 350 °C. In the temperature range of 350~500 °C, with the increase of PbCl₂ content, the catalyst showed obvious deactivation (Figure 15b). With the increasing loadings of Pb species, PbO or PbCl₂ would gather and form crystallized structure (Figure 16). Combined the XPS, NH₃-TPD and H₂-TPR tests shown that the PbO doping affects the denitration reaction due to the obvious reduction of the specific BET surface area of the catalyst, thereby reducing the surface Ce³⁺ and chemisorbed oxygen content. PbCl₂ reduces the redox properties and surface acidity of the catalyst, and reduces the denitration efficiency. According to DRIFT and other tests, the principle of lead poisoning on CT catalysts (as shown in Figure 17), Pb reduces the Ce³⁺ content on the catalyst surface, which leads to the reduction of Brønsted acid sites, and the reduction of surface chemisorbed oxygen inhibits the progress of NO+O₂→NO₂ reaction, which are two key factors leading to more severe inactivation of lead oxide.

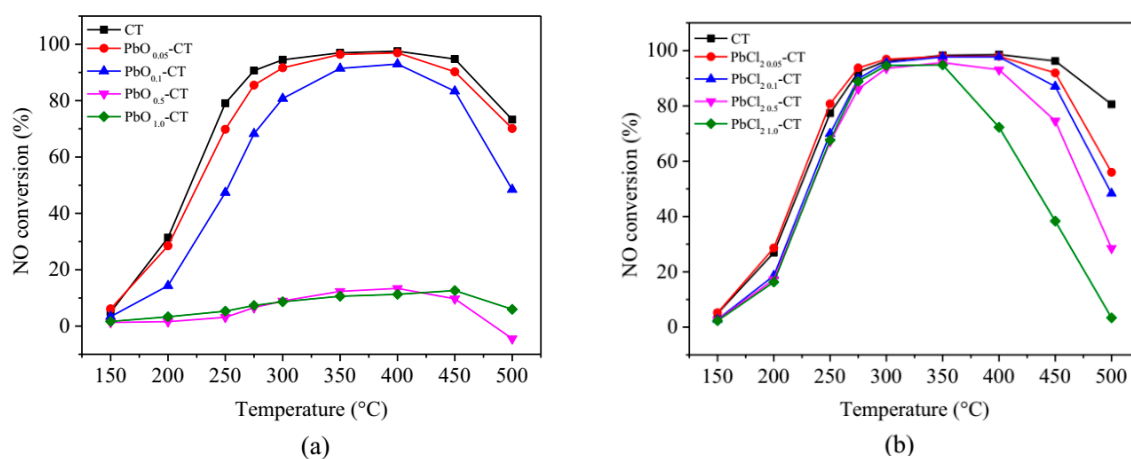


Figure 15. NO conversion of PbO_x-CT (a) and PbCl₂_x-CT (b). Reaction condition: [NO] = [NH₃] = 1000 ppm, [O₂] = 3%, N₂ balance, total flow rate = 500 mL/min, GHSV = 90,000 h⁻¹ [69].

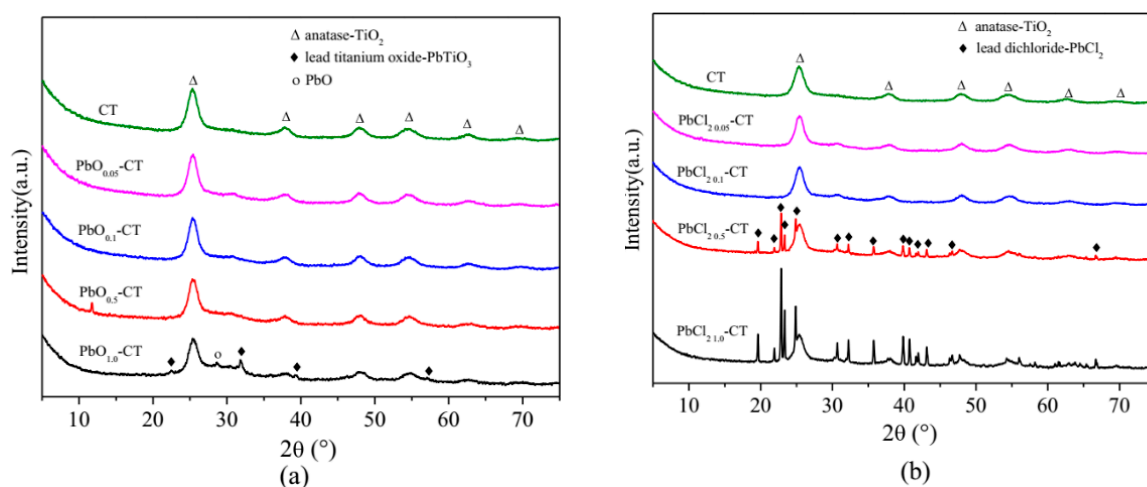


Figure 16. XRD patterns of PbO_x-CT (a) and PbCl₂_x-CT (b) [69].

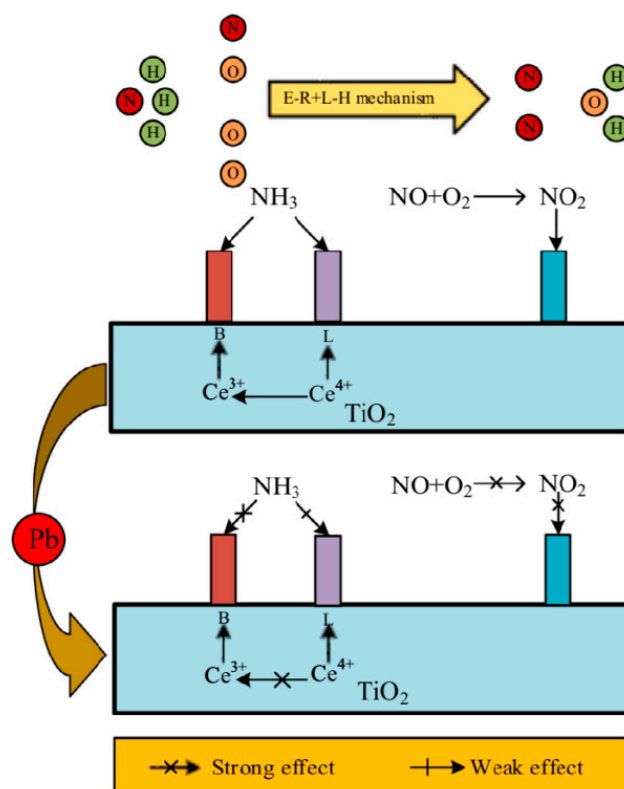


Figure 17. Schematic diagram of Pb poisoning on CT [69].

For deactivated catalysts, nitric acid can be used to restore the redox ability of the catalyst and to increase the surface area and create new acid sites. The use of nitric acid to regenerate Pb-poisoned catalysts can result in almost complete recovery of catalytic activity. Even the catalytic activity exceeds that of fresh catalyst at 80–150 °C.

In conclusion, although cerium-based catalysts have stronger resistance to metal impurities than vanadium-based catalysts, it still affects the SCR activity of catalysts. Therefore, how to improve the resistance of cerium-based catalysts to metal impurities has become the focus of future research. The catalyst can achieve better performance by adjusting the ratio of substances, different synthesis methods, or additives.

3. The Influence of Non-Metallic Impurities

In addition to the influence of metal impurities, the influence of non-metallic impurities in denitration flue gas cannot be ignored, mainly including phosphorus, fluorine, chlorine and sulfur. Their effects on rare earth catalysts are different. The following are mainly analyzed from two aspects: denitration activity and denitration mechanism.

3.1. The Effect of Phosphorus

Phosphorus compounds are constituents of dust in fuel gas, and their effect on the catalytic performance of conventional vanadium-based catalysts has been extensively studied. Some literatures point out that P doping can improve the surface acid sites and vanadium species characteristics of $\text{V}_2\text{O}_5\text{-WO}_3/\text{TiO}_2$ catalysts, thereby improving the catalytic activity of the catalysts, but the deposited phosphorus compounds may reduce its catalytic activity, due to the reduced surface active sites and redox properties of the catalyst [53,73–75]. And studies have found that some compounds of phosphorus element have a passivation effect on SCR catalysts, including H_3PO_4 , P_2O_5 and phosphate [76]. Kamata et al. [77] found that the activity of the catalyst decreased with the increase of P_2O_5 loading, and the specific surface area and specific pore volume gradually decreased with the increase of surface P_2O_5 loading. Kamata et al. also explained that P will replace V and W in V-OH and W-OH to generate P-OH groups. P-OH is not as acidic as V-OH and W-OH,

but can provide weaker Brønsted acidic site, so the phosphorus poisoning of the catalyst is not very obvious when the loading is small. In addition, P can also react with the V=O active sites on the catalyst surface to generate substances such as VOPO₄, thereby reducing the number of active sites. In light of the above studies, it can be concluded that the content, form and location of phosphorus compounds in the catalyst may have a significant impact on the performance of NH₃-SCR catalysts.

However, the effect of phosphorus on the catalytic activity of NH₃-SCR ceria-based catalysts remains controversial. To date, only a few studies have reported the effect of phosphorus compounds on the performance of CeO₂-TiO₂-based catalysts for NH₃-SCR. It has been reported that phosphorus doping can significantly improve the pore structure, thermal stability and surface acidity of TiO₂ [78,79], which in turn affects the performance of CeO₂/TiO₂ catalysts. Yi et al. [80] proposed that depositing phosphorus compounds could enhance the surface acid strength of CeO₂, thereby enhancing its catalytic activity. But a large amount of phosphorus compounds would reduce the redox properties of CeO₂, thereby reducing its catalytic activity. The deposition of phosphorus compounds on the CeO₂-TiO₂ surface could enhance the catalytic activity and resistance to K deactivation of the catalyst, which is due to the enhanced surface acidity and redox properties. The deposited phosphorus compound can deactivate CeO₂-MoO₃/TiO₂, but the formed amorphous CePO₄ species can improve the catalytic performance of CeO₂/TiO₂ catalyst due to the incorporation of phosphorus into CeO₂ [81,82].

Zeng et al. [83] studied the effect of phosphorus on the selective catalytic reduction of NO_x over CeO₂/TiO₂ catalysts. It was found that phosphorus disrupts the Ti-O-Ce structure due to phosphorus-induced migration of Ti⁴⁺ from the cerium oxide-titanium dioxide solid solution to form a separate titanium dioxide, which promotes the growth of titanium dioxide and cerium oxide grains and reduces the specific surface area of the BET, decreasing the electron transfer capacity and the ratio of Ce³⁺ to surface adsorbed oxygen, resulting in a limitation of the redox performance of the CT catalyst. DRIFT tests showed that phosphorus decreased Lewis acid sites and increased Brønsted acid sites. In addition, phosphorus reduced the adsorption capacity of NO_x species on the CeO₂/TiO₂ catalyst, changed the adsorption order of NO_x and ammonia species, and reduced the denitration efficiency.

Cao et al. [84] prepared a phosphorylated CeO₂-TiO₂ catalyst by impregnation method, denoted as xP-CT. The denitration performance test in Figure 18a showed that the catalytic activity of fresh CeO₂-TiO₂ increases rapidly with increasing temperature before 300 °C, and the NO_x conversion exceeds 85% in the range of 250~400 °C. The activity of the phosphorylation catalyst decreased with the increase of phosphorus loading in the temperature range of 50~300 °C. However, in the high temperature range (above 300 °C), the activity of phosphorus-supported catalysts is higher than that of CeO₂-TiO₂ catalysts. The NO_x conversion of CeO₂-TiO₂ catalyst at 450 °C is only 14.2%, while the activity of 2.3% P-CT catalyst is still 71.4%. As shown in Figure 19, phosphorus promotes the grain growth of titanium dioxide and ceria in the catalyst, reduces the specific surface area of the catalyst, and inhibits the electron transfer between Cerium and titanium ions, resulting in a decrease in its redox performance. However, when the temperature is above 300 °C, as shown in Figure 18b, P inhibits the NO_x and N₂O generated by the peroxidation of ammonia gas, thereby improving the activity of the catalyst at high temperature. On the 2.3% P-CT catalyst, the adsorption capacity of ammonia on the Brønsted acid site is greater than that on the Lewis acid site, which also promotes the improvement of the activity at high temperature. The effect of phosphorus on the reaction pathway for NH₃-SCR of NO over the CT catalyst can be depicted as Figure 20. In addition, P does not change the reaction mechanism of the combined action of L-H and E-R on the catalyst surface.

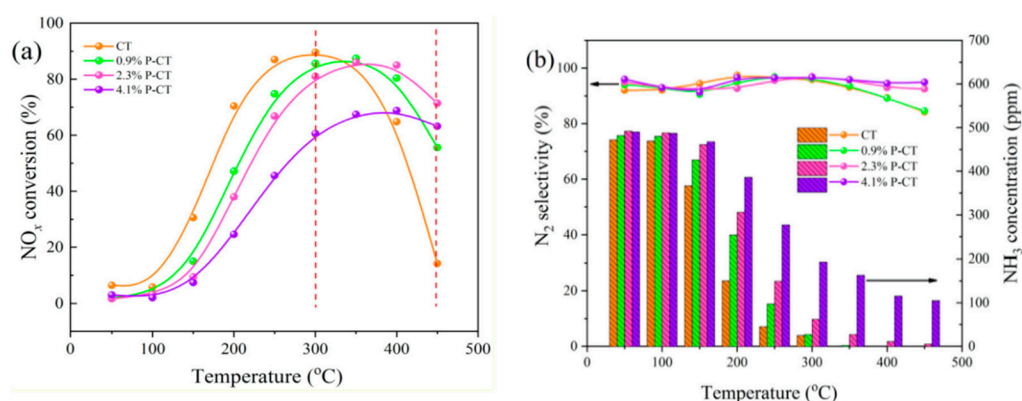


Figure 18. (a) NO_x conversion of the CT and phosphorus-loaded catalysts, (b) N_2 selectivity and NH_3 concentration during the NH_3 -SCR reaction of these catalysts. Reaction conditions: $[\text{NH}_3] = [\text{NO}] = 500 \text{ ppm}$, $[\text{O}_2] = 5 \text{ vol\%}$, N_2 as balance [84].

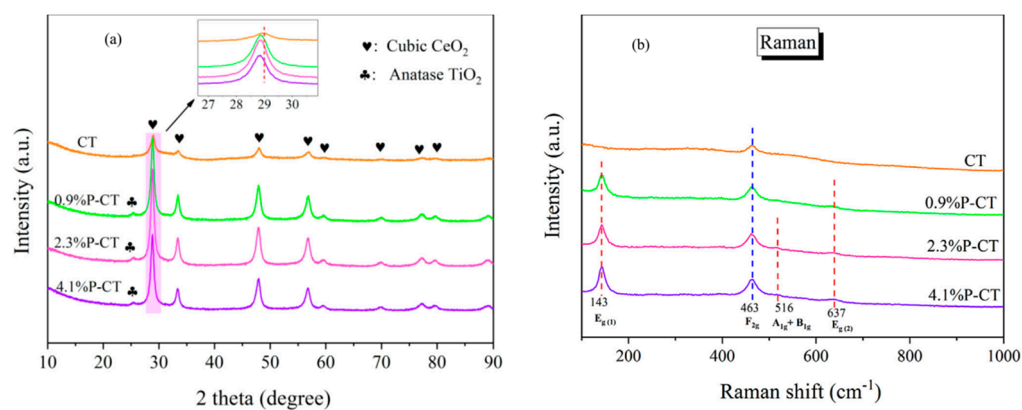


Figure 19. (a) XRD patterns of CT and phosphorus-loaded catalysts, (b) Raman spectra of CT and phosphorus-loaded catalysts [84].

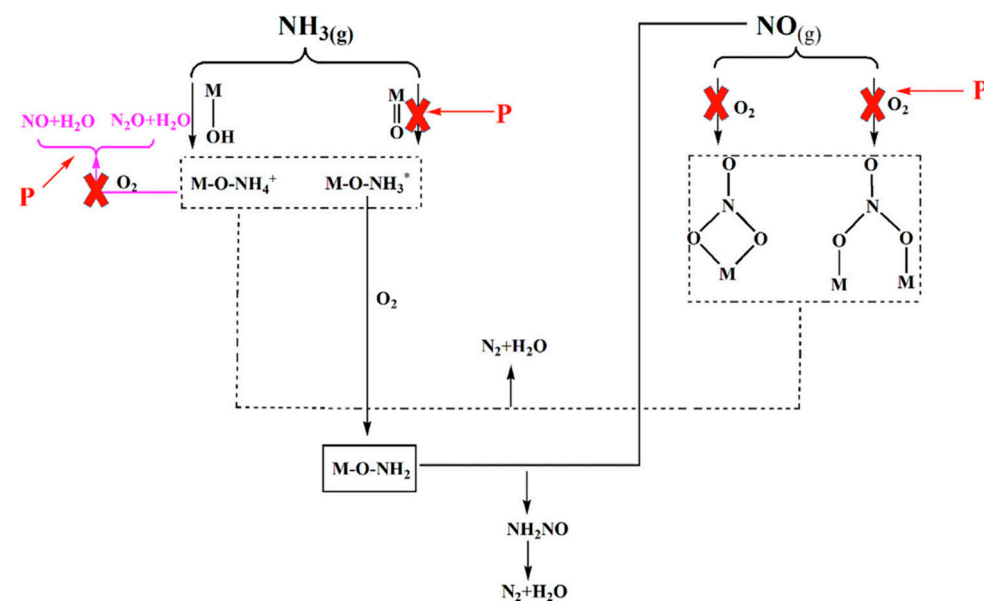


Figure 20. The effect of phosphorus on the reaction pathway for NH_3 -SCR of NO over CT catalyst [84].

3.2. The Effect of Chlorine

As the waste incineration power generation technology is becoming more and more mature, the NO_x emitted by it needs SCR denitration technology to control. However, in

addition to heavy metals and alkali metals, the waste incineration flue gas also contains a certain amount of hydrogen halide gas, and the content of Cl is similar to that of NO_x , which will have an adverse effect on the activity of the denitration catalyst. At present, the research on heavy metals and alkali metals has received extensive attention, but the research on the effect of Cl on catalyst activity is still lacking.

Over the past decade, some researchers have studied the effects of HCl on SCR catalysts. Lisi et al. [85] studied the effect of HCl on the denitration activity of vanadium-titanium catalyst. The results show that the introduction of HCl will lead to a significant decrease in the activity of the catalyst. The reason is that HCl reacts with the active component vanadium on the surface of the catalyst to generate volatile VCl_5 , which leads to the decrease of the active component on the surface of the catalyst. In addition, although HCl gas can form a new acid site on the surface of the catalyst, the performance of the new acid site is lower than that of the original acid site, which eventually leads to the decrease of the activity of the catalyst. However, Hou et al. [86] studied the effect of HCl gas on the denitration activity of $\text{V}_2\text{O}_5/\text{AC}$ catalyst. It was found that HCl gas could improve the denitration activity of $\text{V}_2\text{O}_5/\text{AC}$ catalyst when the concentration of HCl gas was less than 1200 ppm, the reaction temperature was 120–150 °C and GHSV was less than 6000 h^{-1} . This is because NH_4Cl is formed on the surface of the catalyst during the SCR reaction after adding HCl. On the one hand, NH_4Cl can increase the adsorption capacity of NH_3 on the surface of the catalyst, and on the other hand, NH_4Cl can also react with NO to avoid the continuous accumulation of NH_4Cl on the surface of the catalyst, so that the SCR reaction continues well. However, when the concentration of HCl gas was increased or the reaction temperature was changed, HCl gas resulted in a significant decrease in the denitration activity of the catalyst.

It is known that the addition of cerium in the catalyst can effectively resist the influence of Cl; the study by Jin et al. [87] had shown that HCl will react with Cu ions in the CuHM catalyst to form $\text{Cu}_2\text{Cl}(\text{OH})_3$, resulting in the change of valence state or phase of Cu ions on the catalyst, reducing the content of Cu on the surface of the catalyst, resulting in the decrease of catalyst activity. However, when Ce was added to the CuHM zeolite catalyst, the resistance of the obtained CeCuHM catalyst to HCl gas was improved, because the addition of Ce could not only reduce the loss of Cu ions on the catalyst, but also inhibit the transformation of Cu^{2+} to Cu^+ [88].

Yang et al. [89] studied the effect of Cl^- on the denitration activity of Ce/ TiO_2 catalysts in the temperature range of 75–225 °C, and the results showed that the addition of Cl^- would inhibit the adsorption of NH_3 and NO_x on the surface of the catalyst, which is not conducive to the whole SCR reaction, and ultimately led to the decrease of the denitration activity of Ce/ TiO_2 , as shown in Figures 21 and 22. Chang et al. [90] studied the effect of SO_2 and HCl gas coexistence on Rh/ Al_2O_3 catalyst and found that there is competition between SO_2 gas and HCl gas adsorption on the catalyst surface. When 500 ppm SO_2 and 500 ppm HCl gas were introduced into the SCR reaction process, the catalyst was completely deactivated.

Lu's research [91] found that HCl gas has an inhibitory effect on the SCR denitration activity of $\text{CeO}_2/\text{TiO}_2$ and $\text{CeO}_2\text{-MoO}_3/\text{TiO}_2$ catalysts. In the temperature test range of 150–500 °C, the denitration efficiency of the catalysts are all significantly decreased, and the temperature window was greatly reduced. Although HCl inhibits the catalyst obviously, the $\text{CeO}_2\text{-MoO}_3/\text{TiO}_2$ catalyst after HCl gas treatment still maintains a NO conversion rate higher than 90% in the range of 400–450 °C. HCl led to the decrease of specific surface area, the increase of crystallinity, the decrease of redox capacity and the substantial decrease of surface acid sites of the catalyst, which further affected the activity of the catalyst. In the temperature range from 150 to 300 °C, the effect of HCl on the activity of CMT is more serious than that of CT, because the reduction of acid sites corresponding to CMT is more severe.

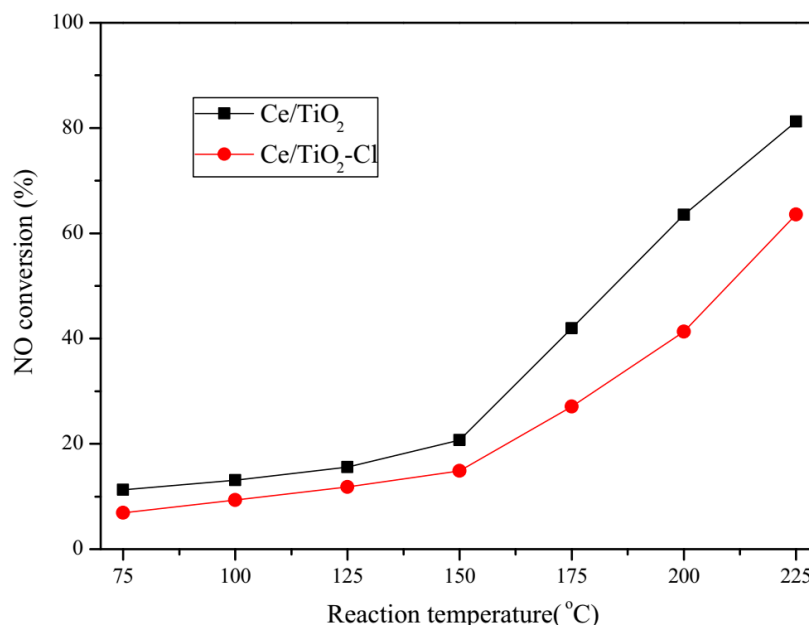


Figure 21. The SCR activities of Ce/TiO₂ and Ce/TiO₂-Cl as a function of reaction temperature. Reaction conditions: [NO] = [NH₃] = 600 ppm, [O₂] = 5%, balance Ar, GHSV = 108,000 h⁻¹ [89].

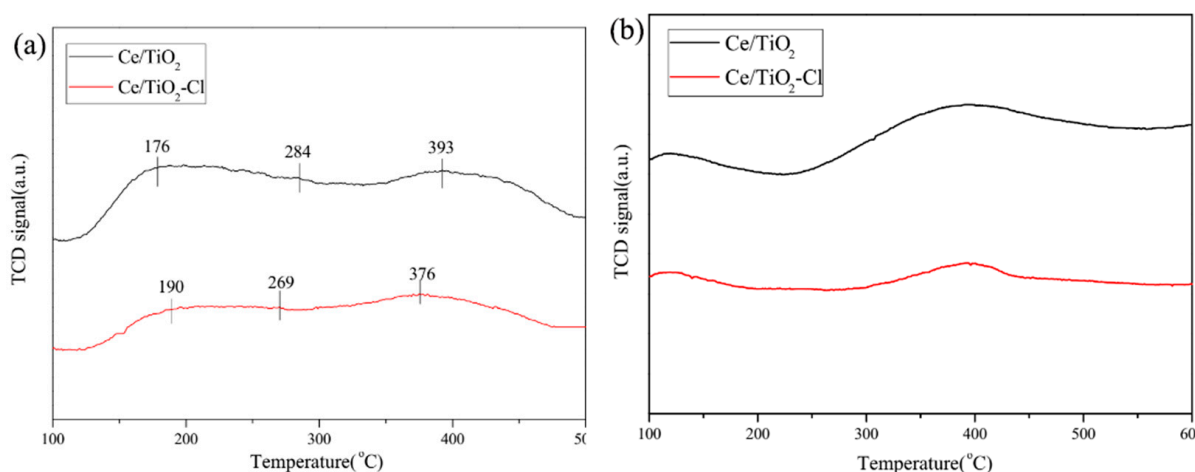


Figure 22. (a) NH₃-TPD profiles of the two catalyst samples, (b) NO-TPD profiles of the two catalyst samples [89].

In light of the above research results, it can be found that Cl has different effects on the denitration activities of different types of SCR catalysts, and there are also great differences in the activity changes of the same catalyst under different reaction temperatures and different concentrations of HCl gas.

3.3. Influence of Fluorine

In the metallurgical industry, the raw minerals and coal used for production often contain fluorine, which is emitted with the flue gas during the smelting process. The fluorine in the flue gas has great damage to the anti-corrosion layer of the flue, and many studies have proved that the fluoride additive can enhance the catalytic activity of NH₃-SCR. Studies have shown that F-doped V₂O₅-WO₃/TiO₂ catalysts exhibit high activity for NH₃ low-temperature SCR. F doping improves the oxygen vacancy interaction between WO₃ and TiO₂, resulting in the increase of superoxide ions in chemisorbed oxygen and NO oxidation, which is of great significance for low-temperature SCR reactions [92]. For V₂O₅/TiO₂ catalysts, F doping improves the interaction of V species with TiO₂ via oxygen

vacancies and electrons, which significantly promotes low-temperature SCR activity [93]. For traditional vanadium-based catalysts, there are many studies on F-doping, but the research on its effect on rare earth denitration catalysts is not yet in-depth.

Zhang et al. [94] found that F doping would promote the low-temperature SCR activity of CeO₂-TiO₂ catalysts. At 180 °C, the NO conversion rate of Ce_{0.3}TiF_{1.5} reached 92.19%, showing excellent catalytic performance. Through BET, XRD, PL spectroscopy, Raman spectroscopy and XPS analysis, it is known that F-doped CeO₂-TiO₂ catalyst can inhibit crystallization, make the catalyst have a better amorphous structure, and increase the active sites on the surface of the catalyst. A stronger interaction occurs between Ce and Ti, which is favorable for electron transfer, increases oxygen vacancies and chemisorbed oxygen, and improves the morphology of Ce³⁺, thereby promoting the catalytic performance. NH₃-TPD analysis showed that a moderate amount of F doping can significantly increase the number of acid sites on the catalyst surface, especially Lewis acid sites, which are related to the higher chemisorbed oxygen on the catalyst surface. The DRIFTS results show that the doping of F can promote the reaction of superoxide radicals (O₂⁻) on the catalyst surface with NO in the gas phase to generate nitro (NO₃⁻) and nitroso (NO₂⁻) species. These species are the intermediate products of the reaction with the reducing gas NH₃ in the reaction gas. The increase of intermediate species can speed up the SCR reaction process, thereby improving the denitration activity [11,95,96].

In order to explore the effect of the preparation method of the catalyst on the F-doped CeO₂/TiO₂ catalyst, Zhang [94,97] also tested the performance of the F-doped catalyst by the sol-gel-impregnation method and the co-precipitation method, respectively. The results show that the catalyst prepared by the sol-gel-impregnation method can improve the denitration performance after F doping, but the conversion rate of NO_x is still lower than 55% in the low temperature region below 210 °C, which has no practical significance. However, the catalyst prepared by the coprecipitation method showed excellent performance, and its sulfur resistance and water resistance were also enhanced. When the space velocity is 28,000 h⁻¹ and the reaction temperature is 210 °C, the denitration efficiency of the Ce_{0.3}TiF_{1.5} catalyst is almost 100%, and when the space velocity is 41,000 h⁻¹, the catalyst can still obtain 95% denitration at the reaction temperature of 210 °C efficiency, as shown in Figure 23. The F-doped cerium-titanium catalysts prepared by the coprecipitation method all showed an amorphous structure with high redox ability, Figure 24 indicated that F-doping resulted in more oxygen vacancies, especially the number of single-electron-trapped oxygen vacancy (F⁺ center). Oxygen vacancies could absorb O₂ to form chemisorbed oxygen. F-doping might enhance the interaction between titanium and cerium, which was in good agreement with the XRD results in Figure 25. These are all important factors for the improvement of catalyst activity.

In addition, some scholars have also studied the effect of HF on the denitration performance of SCR catalysts. For example, Yang et al. [98] studied the effect of HF treatment on the SCR performance of CeO₂ catalysts. The experimental results show that HF treatment can greatly enhance the SCR activity of CeO₂ catalysts. From the characterization results, it can be found that HF treatment of CeO₂ catalyst will lead to lower crystallinity, better reducibility, stronger NH₃ adsorption capacity, and more surface adsorption of oxygen, all of which will lead to enhanced catalyst activity. The CeO₂ was treated with HF gas, and the treated CeO₂ showed good denitration activity in the range of 100–400 °C. In addition, Jin et al. [99] obtained similar results when they studied CeO₂(ZrO₂)/TiO₂ catalysts modified by HF solution. The addition of HF improved the oxygen storage capacity of the catalysts. Figure 26 showed HR-TEM images of TiO₂-0F and TiO₂-10F. The average size of TiO₂-10F (15–20 nm) was much larger than that of TiO₂-0F (5–10 nm). In addition, the lattice fringes with an interplanar spacing of 0.35 nm and 0.235 nm were consistent with the d-spacing of (1 0 1) and (0 0 1) facets, respectively. The synergistic effect of (1 0 1) and (0 0 1) crystal planes and the increase of surface chemisorbed oxygen and Ce³⁺ concentrations are beneficial to the improvement of catalytic activity, as shown in Figure 27.

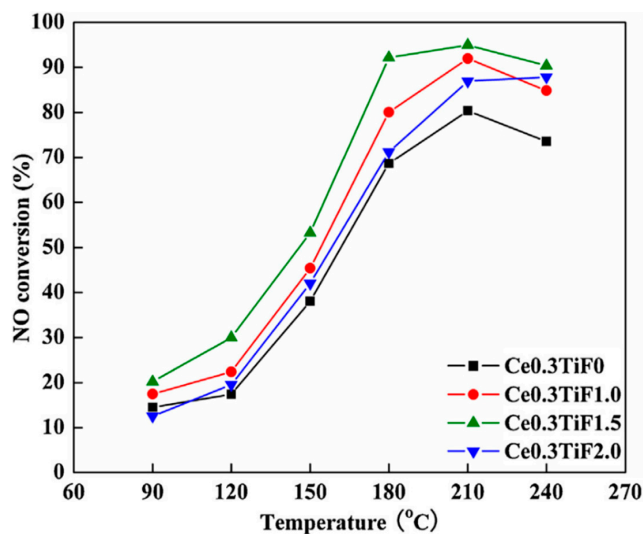


Figure 23. NO_x conversion of Ce_{0.3}TiF_y catalyst with different F doping Reaction conditions: 100 mL/min, 0.05% NO, 0.06% NH₃, 5 vol% O₂, N₂ balance, GHSV = 28,000 h⁻¹ [94].

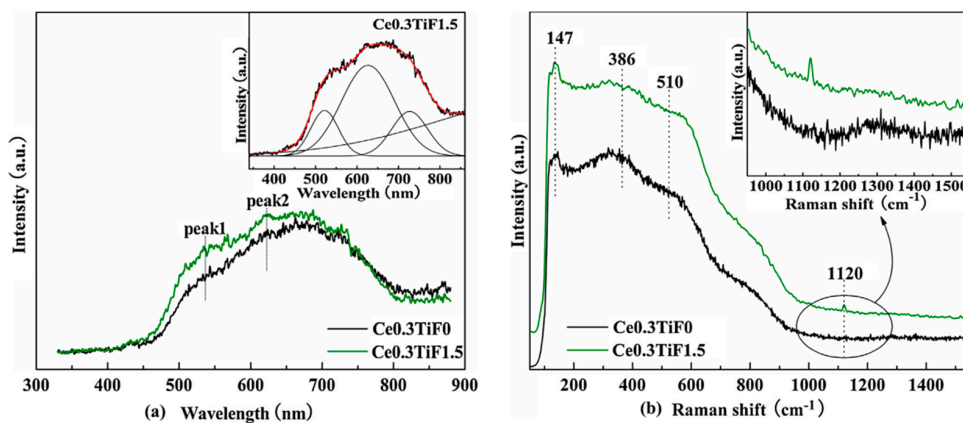


Figure 24. (a) PL spectra of Ce_{0.3}TiF₀ and Ce_{0.3}TiF_{1.5} samples, (b) Raman spectra of Ce_{0.3}TiF₀ and Ce_{0.3}TiF_{1.5} samples [94].

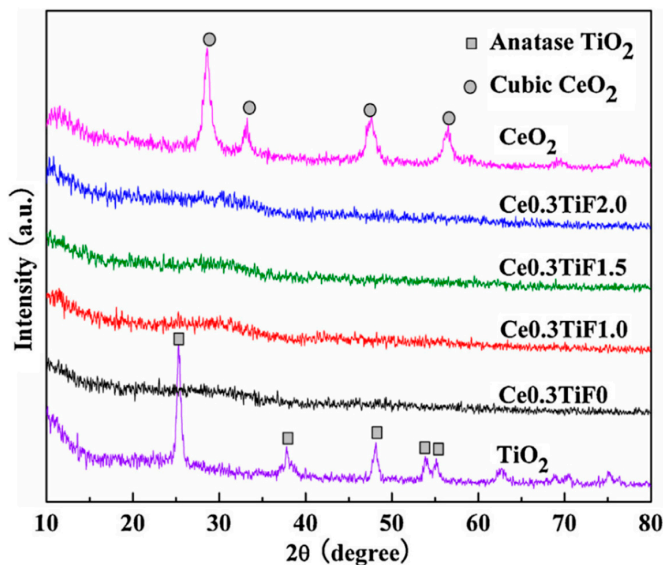


Figure 25. X-ray diffraction patterns of the Ce_{0.3}TiF_y, TiO₂ and CeO₂ [94].

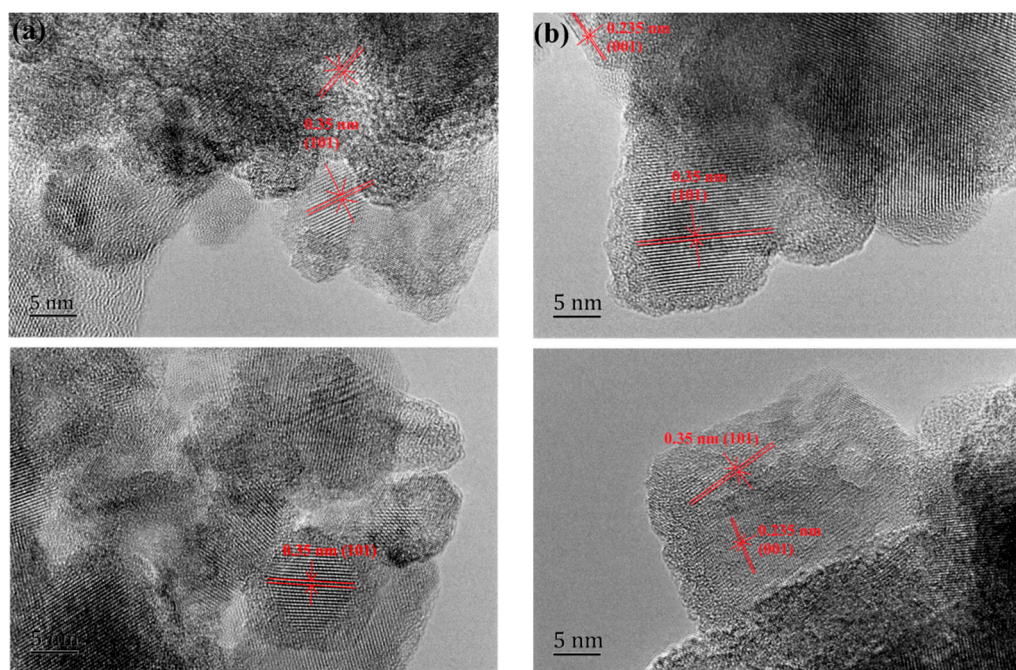


Figure 26. HR-TEM images of $\text{TiO}_2\text{-0F}$ (a), $\text{TiO}_2\text{-10F}$ (b) [99].

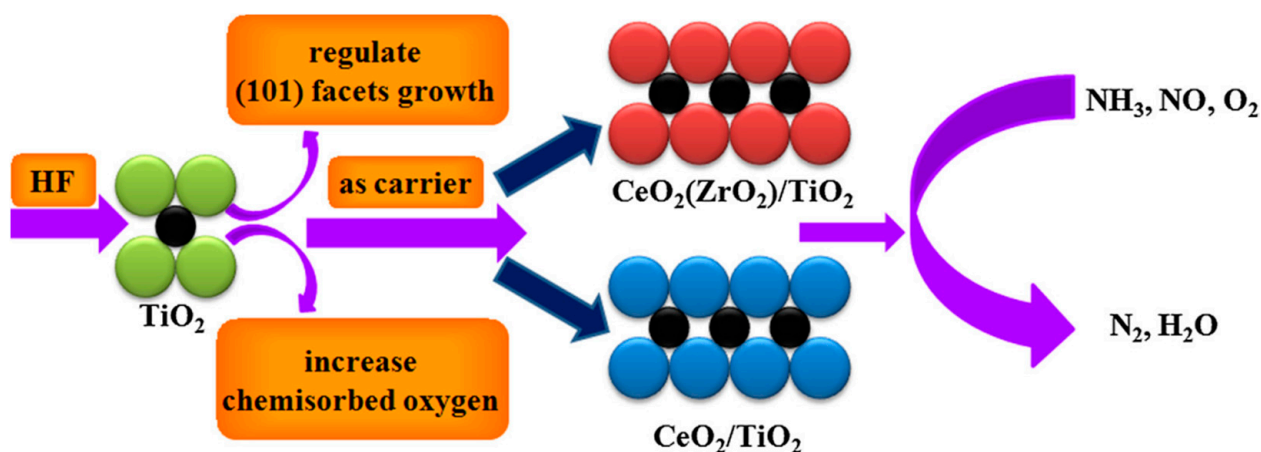


Figure 27. Influence mechanism of HF on $\text{CeO}_2(\text{ZrO}_2)/\text{TiO}_2$ catalysts [99].

In conclusion, appropriate amounts of fluorine and hydrogen fluoride can improve the denitration activity of rare earth catalysts, and can also appropriately improve sulfur resistance and water resistance, and are also closely related to the preparation method of the catalyst.

3.4. The Effect of Sulfur

It has been pointed out that transition metal oxides (eg, VO_x [100], MnO_x [101], CeO_x [102], CuO_x [103] and FeO_x [104], etc.) are the main active components of low-temperature SCR denitration catalysts, although low-temperature SCR catalysts exhibit excellent low-temperature SCR activity [105–107], most fossil fuels contain sulfur, resulting in large amounts of SO_2 in exhaust gas, these traditional catalysts have poor resistance to SO_2 , and even lead to deactivation directly. The resistance of denitration catalysts to SO_2 is an important characterization of catalyst performance. In general, the influence of SO_2 on the catalyst is mainly manifested in two aspects: first, SO_2 in the flue gas will react with ammonia to form sulfates, such as $(\text{NH}_4)_2\text{SO}_3$ and NH_4HSO_4 , which do not decompose at low temperatures and eventually deposit on the catalyst surface, the specific surface area

of the catalyst is reduced and the active site of the SCR catalyst is blocked. Second, SO_2 will compete with NH_3 for adsorption and sulfate, as well as the surface-active substances, thereby inhibiting the activity of the catalyst [108,109]. Therefore, research on improving the sulfur tolerance of low-temperature SCR catalysts has received extensive attention. Some studies have found that doping rare earth elements (Ce [110], Pr [111], Sm [112], and Eu [113], etc.) can effectively improve the resistance of catalysts to SO_2 . CeO_2 is often selected as the promoter or active component of SCR catalyst because of its excellent oxygen storage/release ability and strong redox performance. The addition of cerium has been reported to alleviate the sulfation of catalyst active sites and the formation of ammonium sulfate [108], promoting the anti-sulfur properties of SCR catalysts. However, the effect of SO_2 on the activity of cerium-based catalysts and the specific mechanism still need to be further explored.

Sheng et al. [114] showed that SO_2 can form $\text{Mn}(\text{SO}_4)_2$ and $\text{Ce}_2(\text{SO}_4)_3$ with MnO_x and CeO_2 in Mn-Ce/ TiO_2 catalysts, resulting in the decrease of catalyst activity. Jin et al. [18] also studied the effect of Mn-Ce/ TiO_2 catalyst on SO_2 tolerance, as shown in Figure 28, and found that under the same reaction conditions in SO_2 atmosphere, Mn/ TiO_2 catalyst only retained 25% of NO conversion, while the Mn-Ce/ TiO_2 catalyst retained about 60% NO conversion. In-situ DRIFT analysis (Figure 29) found that the formed sulfate species on Mn-Ce/ TiO_2 surface decomposed much more easily than those on Mn/ TiO_2 surface. The lower thermal stability of the sulfation species on Mn-Ce/ TiO_2 may lead to an increase in its sulfur tolerance. In the presence of SO_2 , sulfate species can be preferentially formed on the Ce dopant, less sulfonation of the main active phase MnO_x , and retention of some Lewis acid sites on MnO_x (mechanism Figure 30) to meet the low temperature SCR cycle. The calculation of the exchange correlation function between VASP4.6 and GGA+PW91 [115] showed that the doping of Ce reduced the binding energy of ammonium and sulfate ions, thus making ammonium sulfate easier to decompose. TG-DSC results also confirmed that the decomposition temperature of NH_4HSO_4 on Mn-Ce/ TiO_2 is about 70 °C lower than that on Mn/ TiO_2 . In addition, Gu et al. [116] also found that the surface sulfonation of CeO_2 can improve the SCR activity. Wang et al. [110] also found that the formation of MnCeO_x solid solution and the preferential sulfonation of CeO_2 make the MnCe/Ti catalyst have higher SCR activity and stronger resistance to SO_2 performance. These results indicate that Ce doping can effectively delay the formation of sulfated species on the surface, thereby improving the sulfur tolerance of Ce-modified catalysts, so rare earth catalysts have better resistance to SO_2 than traditional catalysts.

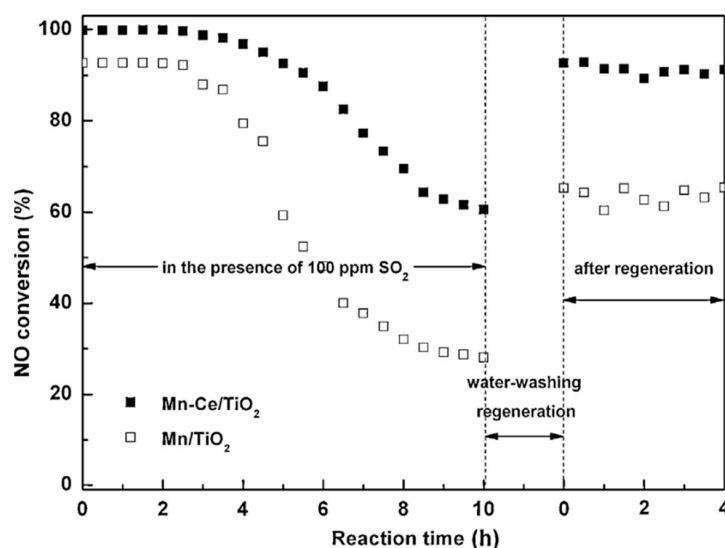


Figure 28. SCR activities of Mn/ TiO_2 and Mn-Ce/ TiO_2 in the presence of SO_2 at 150 °C. ($[\text{NH}_3] = [\text{NO}] = 800$ ppm, $[\text{O}_2] = 3\%$, $[\text{SO}_2] = 100$ ppm, $[\text{H}_2\text{O}] = 3$ vol%, N_2 balance, GHSV = 40,000 h^{-1}) [18].

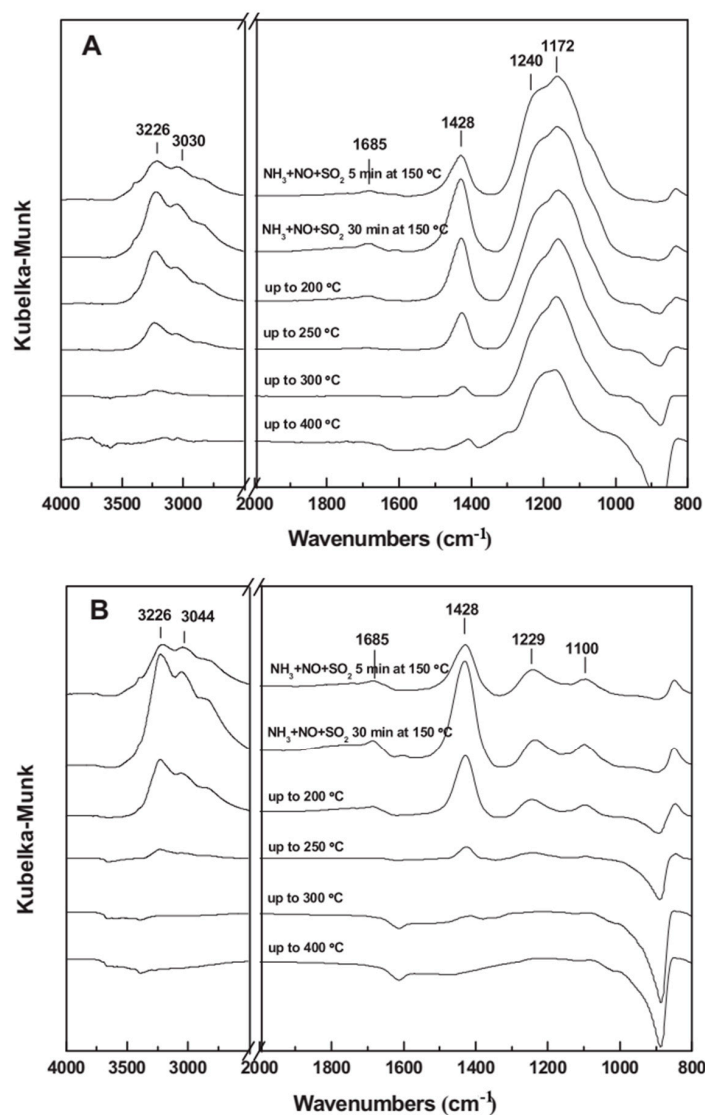


Figure 29. DRIFT spectra of Mn/TiO₂ (A) and Mn-Ce/TiO₂ (B) exposed to 800 ppm. NH₃ + 800 ppm NO + 100 ppm SO₂ in the presence of O₂ for various times at 150 °C. Subsequently, the atmosphere was switched to only He and the temperature was escalated to 400 °C [18].

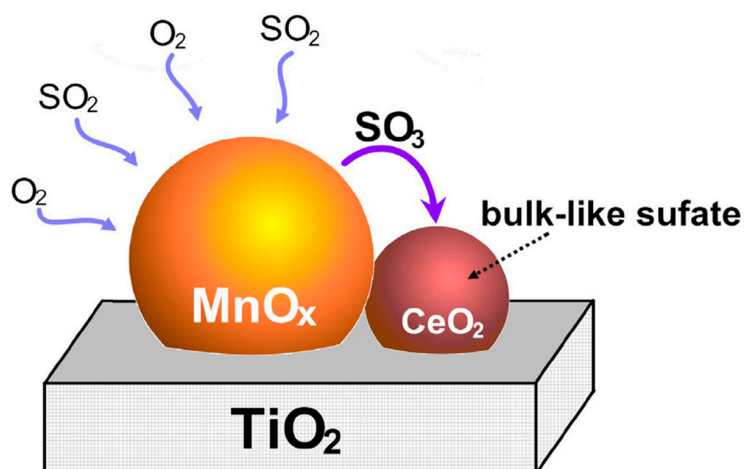


Figure 30. The formation pathway of bulk-like sulfate on Mn-Ce/TiO₂ samples [18].

It has also been suggested that the addition of modifiers to cerium-based catalysts can further improve the sulfur tolerance of the catalysts. For example, Shan et al. [23] added WO_3 to $\text{CeO}_2\text{-TiO}_2$ to form $\text{Ce}_{0.2}\text{W}_{0.2}\text{TiO}_x$. This catalyst maintained a NO_x conversion rate of nearly 100% in the presence of 100 ppm SO_2 at a temperature of 300 °C. Shen et al. [117] also found that the zirconium additive had a similar promoting effect on the catalytic performance of $\text{Ti}_{0.8}\text{Ce}_{0.2}\text{O}_2$. Iron doping also has a positive effect on the SO_2 tolerance of the Mn-Ce/ TiO_2 catalyst, as iron oxides significantly reduce the sulfate formation rate [118]. Liu et al. [119] reported that Ce/ $\text{TiO}_2\text{-SiO}_2$ had stronger SO_2 resistance than Ce/ TiO_2 , and the study showed that the introduction of SiO_2 further weakened the basicity of the Ce/ $\text{TiO}_2\text{-SiO}_2$ catalyst surface. Compared with Ce/ TiO_2 , Ce/ $\text{TiO}_2\text{-SiO}_2$ has less sulfate accumulation on the surface. However, Yu et al. [120] believed that in the SCR reaction of NO and NH_3 at low temperature, the catalyst structure rather than the catalyst composition determines the ability of the catalyst to resist SO_2 poisoning. Furthermore, the mesoporous structure promotes SO_2 resistance compared with the microporous structure. There are also studies showing that the preparation method also affects the resistance of $\text{CeO}_2\text{-TiO}_2$ catalysts to SO_2 . For example, the samples prepared by the sol-gel method by Gao et al. [20] exhibited better SO_2 resistance than the samples prepared by the impregnation method and co-precipitation method. In addition, Shan et al. [121] reported that on Ce-Ti mixed oxides prepared by uniform precipitation, the NO conversion was almost unchanged at 300 °C with the addition of 100 ppm SO_2 for 24 h. Therefore, the resistance of cerium-based catalysts to SO_2 is not only related to the composition and structure of the catalyst but also to the preparation method.

Although cerium-based catalysts have good resistance to SO_2 , the research on catalyst deactivation regeneration is still important due to the different application environments. A considerable part of the literature studies the regeneration of deactivated catalysts, and there are many methods to regenerate deactivated catalysts, such as water washing, thermal regeneration, and reductive regeneration. The study by Sheng et al. [114] found that water washing has the best regeneration performance for toxic catalysts, especially under the action of ultrasonic vibration, the catalytic activity can recover to 91.3%, as shown in Figure 31, almost reaching the level of fresh catalysts. Other studies have drawn similar conclusions: after deionized water washing and regeneration, it was found that the NO conversion rate of the Mn-Ce/ TiO_2 catalyst could be restored to more than 90%, while the NO conversion rate of the Mn/ TiO_2 catalyst was only restored to 60% [18]. This is because the SO_2 deactivation mechanism of the $\text{NH}_3\text{-SCR}$ catalyst is due to active phase sulfation and surface ammonium sulfate/bisulfate deposition, which can be easily removed by water washing. And the main washing products Nitrate NO_3^- , Sulfate SO_4^{2-} , and ammonium NH_4^+ can be recycled to improve the economic benefits of the low temperature SCR technology.

Wang et al. [122] also found that although the coexistence of H_2O and SO_2 aggravated the deactivation of the catalyst, the surface hydroxylation of the catalyst prevented the metal sulfation and significantly alleviated the irreversible poisoning. Thermal treatment with H_2O or O_2 has been proven can regenerate the SO_2 poisoned catalyst effectively, for both operations facilitate the decomposition of the deposited $(\text{NH}_4)_2\text{SO}_4$ or NH_4HSO_4 and induce the sub-bulk/bulk S atom out-migration.

In short, non-metallic impurities widely exist in denitration flue gas, and the harm to the catalyst is inevitable. Rare earth catalysts with excellent performance and good resistance to impurities are bound to become the focus of industry research in the future, some people have achieved good results in this regard. Although it has excellent performance, some aspects need to be further explored. It is urgent to explore new synthesis methods and new material ratio.

Finally, the effects of different types of impurities on rare earth catalysts are summarized in Table 1.

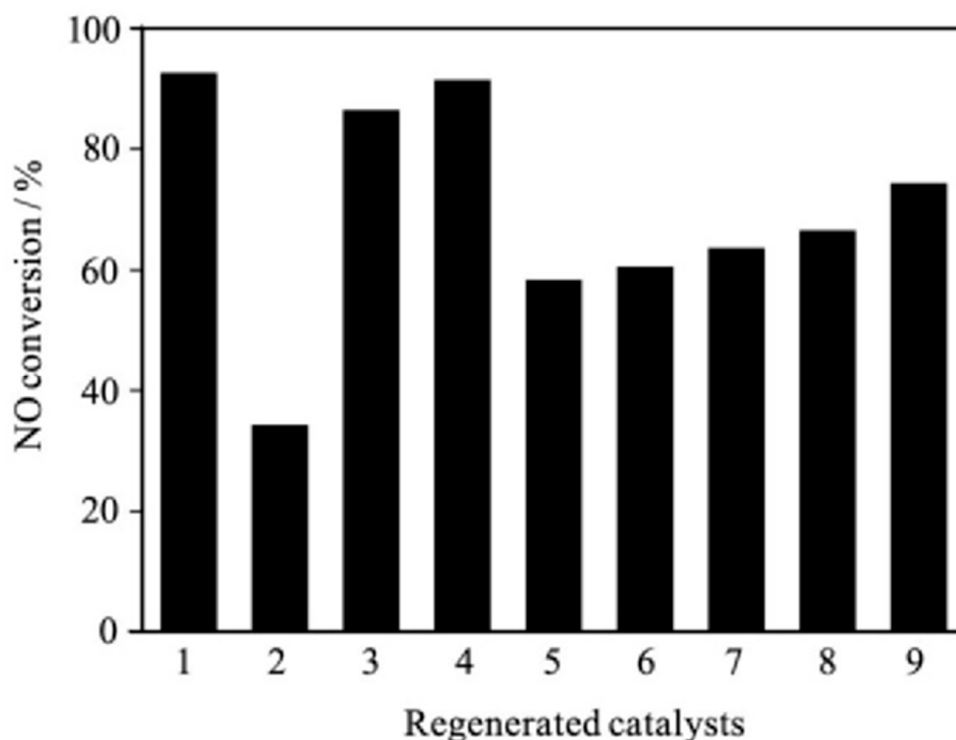


Figure 31. SCR activities of fresh Mn-Ce/TiO₂ (0.075) (1), deactivated sample (2), and regenerated catalysts treated by water washing (3), water washing with ultrasonic vibration (4), heating in air (5), heating in N₂ (6), heating in Ar (7), H₂ reduction (8), and NH₃ reduction (9) (operating conditions: 600 ppm NO, 600 ppm NH₃, 3% O₂, 3% H₂O, and balance N₂, GHSV = 40,000 h⁻¹, 120 °C reaction temperature) [114].

Table 1. Effects of Various Impurities on Rare Earth Catalysts.

Types of Impurities	Effect on Rare Earth Catalysts
Na, K	K and Na will decrease the acid sites of the catalyst, and their oxides and chlorides will weaken the reaction activity of the catalyst surface, inhibit the formation of oxygen vacancies and chemical adsorbed oxygen, thereby reducing the NH ₃ adsorption amount and weakening the denitrification performance. The influence of K is greater than that of Na, and the influence of oxides is more serious than that of chlorides.
Ca	Ca deposition can destroy the pore structure of the catalyst, reduce the surface active elements and acid sites, and Mg has a similar effect.
Pb	Lead will reduce the redox performance, chemical adsorption of oxygen and specific surface area of the catalyst. The toxicity of lead chloride is higher than lead oxide, because lead chloride is easier to form crystalline phase.
P	At low temperature, P promotes the grain growth of TiO ₂ and CeO ₂ in the catalyst, reduces the specific surface area of the catalyst, inhibits the electron transfer between Ce and Ti ions, and reduces its redox performance. At high temperature, P inhibits NO _x and N ₂ O produced by ammonia peroxidation, thereby increasing its activity.
Cl	HCl led to the decrease of specific surface area, the increase of crystallinity, the decrease of redox ability, and the significant decrease of surface acid sites, which further affected the catalyst activity.
F	F can inhibit crystallization, so that the catalyst has more surface active sites, increasing oxygen vacancies and chemisorption oxygen. In addition, the addition of F can bring more NO _x adsorption sites and the formation of intermediate species, thereby promoting the activity of the catalyst.
S	Ce in rare earth catalysts can effectively delay the formation of surface sulfating substances, reduce the binding energy of ammonium and sulfate ions, so that ammonium sulfate is easier to decompose and improve the sulfur resistance of Ce modified catalysts.

4. Conclusions and Perspectives

In conclusion, cerium-based catalysts exhibit good denitration activity and have been widely studied, but the composition of denitration flue gas is complex, and the influence on catalyst activity is unavoidable. Alkali metals will reduce the acid sites of the catalyst and reduce the amount of NH_3 gas adsorption; the deposition of alkaline earth metals will destroy the pore structure of the catalyst; lead will reduce the redox performance and specific surface area of the catalyst; P and Cl will promote grain growth and lead to increased crystallinity. However, F can inhibit crystallization, increase oxygen vacancies and chemical adsorption of oxygen, make the catalyst have more surface-active sites, and promote the formation of intermediate substances, improving the activity of the catalyst. Compared with vanadium-based catalyst, the great oxygen storage performance and excellent redox performance of CeO_2 make cerium-based catalysts more resistant to various impurities, especially to SO_2 . Some people have carried out fruitful work on the synthesis methods and modification of catalysts and the regeneration of deactivated catalysts. Nevertheless, some aspects need to be further investigated, the resistance of cerium-based catalysts to different impurities at low temperature. Second, the traditional synthesis methods of catalysts also need further research to explore and develop new synthesis methods to enhance the interaction between active components and weaken the influence of impurities on the active site. Furthermore, in order to provide more excellent performance of cerium-based catalysts, it is necessary to further study the optimal ratio of active components. In addition, considering the cost of catalysts, some metal oxides have high costs, so the regeneration of poisoned catalysts is also a key research direction in the future.

Author Contributions: X.B. and K.L.; literature search, writing-original draft preparation and editing, M.C., W.W. and P.C.; writing-review and editing, X.B. and W.W.; funding acquisition. All authors have read and agreed to the published version of the manuscript.

Funding: The work described above was supported by the Major State Basic Research Development Program of China (973 Program) [no. 2012CBA01205] and National Natural Science Foundation of China [no. 51274060].

Data Availability Statement: Not applicable.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Mousavi, S.M.; Niaei, A.; Illán Gómez, M.J.; Salari, D.; Nakhostin Panahi, P.; Abaladejo-Fuentes, V. Characterization and activity of alkaline earth metals loaded $\text{CeO}_2\text{-MO}_x$ ($M = \text{Mn, Fe}$) mixed oxides in catalytic reduction of NO. *Mater. Chem. Phys.* **2014**, *143*, 921–928. [[CrossRef](#)]
2. Wang, L.Y.; Cheng, X.X.; Wang, Z.Q.; Zhang, X.Y.; Ma, C.Y. Research progress of low temperature catalytic denitration technology. *Chem. Ind. Eng. Prog.* **2016**, *35*, 2222–2235.
3. Du, X.; Gao, X.; Qu, R.; Ji, P.; Luo, Z.; Cen, K.-F. The Influence of Alkali Metals on the Ce-Ti Mixed Oxide Catalyst for the Selective Catalytic Reduction of NO_x . *ChemCatChem* **2012**, *4*, 2075–2081. [[CrossRef](#)]
4. Li, J.; Chang, H.; Ma, L.; Hao, J.; Yang, R.T. Low-temperature selective catalytic reduction of NO_x with NH_3 over metal oxide and zeolite catalysts—A review. *Catal. Today* **2011**, *175*, 147–156. [[CrossRef](#)]
5. Long, R.Q.; Yang, R.T. Superior Fe-ZSM-5 catalyst for selective catalytic reduction of nitric oxide by ammonia. *J. Am. Chem. Soc.* **1999**, *121*, 23. [[CrossRef](#)]
6. Colombo, M.; Nova, I.; Tronconi, E. A comparative study of the NH_3 -SCR reactions over a Cu-zeolite and a Fe-zeolite catalyst. *Catal. Today* **2010**, *151*, 223–230. [[CrossRef](#)]
7. Metkar, P.S.; Harold, M.P.; Balakotaiah, V. Selective catalytic reduction of NO_x on combined Fe-and Cu-zeolite monolithic catalysts: Sequential and dual layer configurations. *Appl. Catal. B-Environ.* **2012**, *111*, 67–80. [[CrossRef](#)]
8. Xu, W.; Yu, Y.; Zhang, C.; He, H. Selective catalytic reduction of NO by NH_3 over a Ce/TiO₂ catalyst. *Catal. Commun.* **2008**, *9*, 1453–1457. [[CrossRef](#)]
9. Gao, X.; Jiang, Y.; Zhong, Y.; Luo, Z.; Cen, K. The activity and characterization of $\text{CeO}_2\text{-TiO}_2$ catalysts prepared by the sol-gel method for selective catalytic reduction of NO with NH_3 . *J. Hazard. Mater.* **2010**, *174*, 734–739. [[CrossRef](#)]
10. Liu, F.; He, H.; Zhang, C. Novel iron titanate catalyst for the selective catalytic reduction of NO with NH_3 in the medium temperature range. *Chem. Commun.* **2008**, *17*, 2043–2045. [[CrossRef](#)]

11. Liu, F.; He, H.; Ding, Y.; Zhang, C. Effect of manganese substitution on the structure and activity of iron titanate catalyst for the selective catalytic reduction of NO with NH₃. *Appl. Catal. B-Environ.* **2009**, *93*, 194–204. [[CrossRef](#)]
12. Karami, A.; Salehi, V. The influence of chromium substitution on an iron–titanium catalyst used in the selective catalytic reduction of NO. *J. Catal.* **2012**, *292*, 32–43. [[CrossRef](#)]
13. Mou, X.; Zhang, B.; Li, Y.; Yao, L.; Wei, X.; Su, D.S.; Shen, W. Rod-shaped Fe₂O₃ as an efficient catalyst for the selective reduction of nitrogen oxide by ammonia. *Angew. Chem.-Int. Edit.* **2012**, *51*, 2989–2993. [[CrossRef](#)] [[PubMed](#)]
14. Li, Y.; Cheng, H.; Li, D.; Qin, Y.; Xie, Y.; Wang, S. WO₃/CeO₂-ZrO₂, a promising catalyst for selective catalytic reduction (SCR) of NO_x with NH₃ in diesel exhaust. *Chem. Commun.* **2008**, *12*, 1470–1472. [[CrossRef](#)]
15. Chen, L.; Li, J.; Ablikim, W.; Wang, J.; Chang, H.; Ma, L.; Xu, J.; Ge, M.; Arandiyani, H. CeO₂-WO₃ mixed oxides for the selective catalytic reduction of NO_x by NH₃ over a wide temperature range. *Catal. Lett.* **2011**, *141*, 1859–1864. [[CrossRef](#)]
16. Lee, S.M.; Park, K.H.; Hong, S.C. MnO_x/CeO₂-TiO₂ mixed oxide catalysts for the selective catalytic reduction of NO with NH₃ at low temperature. *Chem. Eng. J.* **2012**, *195*, 323–331. [[CrossRef](#)]
17. Qi, G.; Yang, R.T.; Chang, R. MnO_x-CeO₂ mixed oxides prepared by co-precipitation for selective catalytic reduction of NO with NH₃ at low temperatures. *Appl. Catal. B-Environ.* **2004**, *51*, 93–106. [[CrossRef](#)]
18. Jin, R.; Liu, Y.; Wang, Y.; Cen, W.; Wu, Z.; Wang, H.; Weng, X. The role of cerium in the improved SO₂ tolerance for NO reduction with NH₃ over Mn-Ce/TiO₂ catalyst at low temperature. *Appl. Catal. B-Environ.* **2014**, *148*, 582–588. [[CrossRef](#)]
19. Guo, R.T.; Zhen, W.L.; Pan, W.G.; Zhou, Y.; Hong, J.N.; Xu, H.J.; Jin, Q.; Ding, C.G.; Guo, S.Y. Effect of Cu doping on the SCR activity of CeO₂ catalyst prepared by citric acid method. *J. Ind. Eng. Chem.* **2014**, *20*, 1577–1580. [[CrossRef](#)]
20. Gao, X.; Jiang, Y.; Fu, Y.; Zhong, Y.; Luo, Z.; Cen, K. Preparation and characterization of CeO₂/TiO₂ catalysts for selective catalytic reduction of NO with NH₃. *Catal. Commun.* **2010**, *11*, 465–469. [[CrossRef](#)]
21. Peng, Y.; Li, K.; Li, J. Identification of the active sites on CeO₂-WO₃ catalysts for SCR of NO_x with NH₃: An in situ IR and Raman spectroscopy study. *Appl. Catal. B-Environ.* **2013**, *140*, 483–492. [[CrossRef](#)]
22. Peng, Y.; Li, J.; Chen, L.; Chen, J.; Han, J.; Zhang, H.; Han, W. Alkali metal poisoning of a CeO₂-WO₃ catalyst used in the selective catalytic reduction of NO_x with NH₃: An experimental and theoretical study. *Environ. Sci. Technol.* **2012**, *46*, 2864–2869. [[CrossRef](#)] [[PubMed](#)]
23. Shan, W.; Liu, F.; He, H.; Shi, X.; Zhang, C. A superior Ce-W-Ti mixed oxide catalyst for the selective catalytic reduction of NO_x with NH₃. *Appl. Catal. B-Environ.* **2012**, *115*, 100–106. [[CrossRef](#)]
24. Jiang, Y.; Xing, Z.; Wang, X.; Huang, S.; Wang, X.; Liu, Q. Activity and characterization of a Ce-W-Ti oxide catalyst prepared by a single step sol-gel method for selective catalytic reduction of NO with NH₃. *Fuel* **2015**, *151*, 124–129. [[CrossRef](#)]
25. Liu, Z.; Zhang, S.; Li, J.; Ma, L. Promoting effect of MoO₃ on the NO_x reduction by NH₃ over CeO₂/TiO₂ catalyst studied with in situ DRIFTS. *Appl. Catal. B-Environ.* **2014**, *144*, 90–95. [[CrossRef](#)]
26. Jiang, Y.; Xing, Z.; Wang, X.; Huang, S.; Liu, Q.; Yang, J. MoO₃ modified CeO₂/TiO₂ catalyst prepared by a single step sol-gel method for selective catalytic reduction of NO with NH₃. *J. Ind. Eng. Chem.* **2015**, *29*, 43–47. [[CrossRef](#)]
27. Liu, S.W.; Guo, R.T.; Sun, X.; Liu, J.; Pan, W.G.; Shi, X.; Wang, Z.Y.; Liu, X.Y.; Qin, H. Selective catalytic reduction of NO_x over Ce/TiZrO_x catalyst: The promoted K resistance by TiZrO_x support. *Mol. Catal.* **2019**, *462*, 19–27. [[CrossRef](#)]
28. Yan, Q.; Gao, Y.; Li, Y.; Vasiliades, M.A.; Chen, S.; Zhang, C.; Gui, R.; Wang, Q.; Zhu, T.; Efstathiou, A.M. Promotional effect of Ce doping in Cu₄Al₁O_x-LDO catalyst for low-T practical NH₃-SCR: Steady-state and transient kinetics studies. *Appl. Catal. B-Environ.* **2019**, *255*, 117749. [[CrossRef](#)]
29. Liu, Z.; Yi, Y.; Li, J.; Woo, S.I.; Wang, B.; Cao, X.; Li, Z. A superior catalyst with dual redox cycles for the selective reduction of NO_x by ammonia. *Chem. Commun.* **2013**, *49*, 7726–7728. [[CrossRef](#)]
30. Zhang, Q.; Qiu, C.; Xu, H.; Lin, T.; Lin, Z.; Gong, M.; Chen, Y. Low-temperature selective catalytic reduction of NO with NH₃ over monolith catalyst of MnO_x/CeO₂-ZrO₂-Al₂O₃. *Catal. Today* **2011**, *175*, 171–176. [[CrossRef](#)]
31. Ko, J.H.; Park, S.H.; Jeon, J.-K.; Kim, S.-S.; Kim, S.C.; Kim, J.M.; Chang, D.; Park, Y.-K. Low temperature selective catalytic reduction of NO with NH₃ over Mn supported on Ce_{0.65}Zr_{0.35}O₂ prepared by supercritical method: Effect of Mn precursors on NO reduction. *Catal. Today* **2012**, *185*, 290–295. [[CrossRef](#)]
32. Andreoli, S.; Deorsola, F.; Galletti, C.; Pirone, R. Nanostructured MnO_x catalysts for low-temperature NO_x SCR. *Chem. Eng. J.* **2015**, *278*, 174–182. [[CrossRef](#)]
33. Zhang, N.; Li, L.; Guo, Y.; He, J.; Wu, R.; Song, L.; Zhang, G.; Zhao, J.; Wang, D.; He, H. A MnO₂-based catalyst with H₂O resistance for NH₃-SCR: Study of catalytic activity and reactants-H₂O competitive adsorption. *Appl. Catal. B-Environ.* **2020**, *270*, 118860. [[CrossRef](#)]
34. Yang, S.; Liao, Y.; Xiong, S.; Qi, F.; Dang, H.; Xiao, X.; Li, J. N₂ selectivity of NO reduction by NH₃ over MnO_x-CeO₂: Mechanism and key factors. *J. Phys. Chem. C* **2014**, *118*, 21500–21508. [[CrossRef](#)]
35. Xu, L.; Li, X.S.; Crocker, M.; Zhang, Z.S.; Zhu, A.M.; Shi, C. A study of the mechanism of low-temperature SCR of NO with NH₃ on MnO_x/CeO₂. *J. Mol. Catal. A Chem.* **2013**, *378*, 82–90. [[CrossRef](#)]
36. Eigenmann, F.; Maciejewski, M.; Baiker, A. Selective reduction of NO by NH₃ over manganese–cerium mixed oxides: Relation between adsorption, redox and catalytic behavior. *Appl. Catal. B-Environ.* **2006**, *62*, 311–318. [[CrossRef](#)]
37. Liu, Z.; Yi, Y.; Zhang, S.; Zhu, T.; Zhu, J.; Wang, J. Selective catalytic reduction of NO_x with NH₃ over Mn-Ce mixed oxide catalyst at low temperatures. *Catal. Today* **2013**, *216*, 76–81. [[CrossRef](#)]

38. Qi, G.; Yang, R.T. Characterization and FTIR studies of $\text{MnO}_x\text{-CeO}_2$ catalyst for low-temperature selective catalytic reduction of NO with NH_3 . *J. Phys. Chem. B* **2004**, *108*, 15738–15747. [[CrossRef](#)]
39. Jin, R.; Liu, Y.; Wu, Z.; Wang, H.; Gu, T. Relationship between SO_2 poisoning effects and reaction temperature for selective catalytic reduction of NO over Mn–Ce/TiO₂ catalyst. *Catal. Today* **2010**, *153*, 84–89. [[CrossRef](#)]
40. Wu, Z.; Jin, R.; Liu, Y.; Wang, H. Ceria modified $\text{MnO}_x/\text{TiO}_2$ as a superior catalyst for NO reduction with NH_3 at low-temperature. *Catal. Commun.* **2008**, *9*, 2217–2220. [[CrossRef](#)]
41. Du, K.M.; Qin, G.H.; Qi, Z.F.; Liu, C.H.; Jiang, N.; Hu, D.Q. Poisoning of NH_3 -SCR denitration catalyst and its anti-poisoning strategy. *Modern Chem. Ind.* **2021**, *41*, 58–62.
42. Gao, F.; Tang, X.; Yi, H.; Zhao, S.; Zhang, T.; Li, D.; Ma, D. The poisoning and regeneration effect of alkali metals deposited over commercial $\text{V}_2\text{O}_5\text{-WO}_3/\text{TiO}_2$ catalysts on SCR of NO by NH_3 . *Chin. Sci. Bull.* **2014**, *59*, 3966–3972. [[CrossRef](#)]
43. Guo, L.X.; Lu, Y.H.; Han, Z.G. Discussion on deactivation mechanism and regeneration technology of SCR denitration catalyst in thermal power plant. *Resour. Econ. Environ. Prot.* **2016**, 19–20. [[CrossRef](#)]
44. Wang, S.X.; Guo, R.T.; Pan, W.G.; Chen, Q.L.; Sun, P.; Li, M.Y.; Liu, S.M. The deactivation of Ce/TiO₂ catalyst for NH_3 -SCR reaction by alkali metals: TPD and DRIFT studies. *Catal. Commun.* **2017**, *89*, 143–147. [[CrossRef](#)]
45. Zhou, A.Y. Mechanism Study on the Effect of Alkali/Alkaline Earth Metal and Halogen Deposition on the Performance of Mn-Ce/TiO₂ Catalyst for Low Temperature SCR Denitration. Master's Thesis, Nanjing Normal University, Nanjing, China, 2016.
46. Jiang, Y.; Shi, W.; Lai, C.; Gao, W.; Yang, L.; Yu, X.; Yang, Z.; Lin, R. The deactivation effect of Na_2O and NaCl on $\text{CeO}_2\text{-TiO}_2$ catalysts for selective catalytic reduction of NO with NH_3 . *J. Energy Inst.* **2020**, *93*, 1332–1340. [[CrossRef](#)]
47. Reyna-Alvarado, J.; López-Galán, O.A.; Ramos, M.; Rodríguez, J.; Pérez-Hernández, R. A theoretical catalytic mechanism for methanol reforming in CeO_2 vs Ni/CeO_2 by energy transition states profiles. *Catal. Today* **2022**, 392–393, 146–153. [[CrossRef](#)]
48. Jiang, Y.; Lai, C.; Li, Q.; Gao, W.; Yang, L.; Yang, Z.; Lin, R.; Wang, X.; Zhu, X. The poisoning effect of KCl and K_2O on $\text{CeO}_2\text{-TiO}_2$ catalyst for selective catalytic reduction of NO with NH_3 . *Fuel* **2020**, *280*, 118638. [[CrossRef](#)]
49. Strege, J.R.; Zygarlicke, C.J.; Folkedahl, B.C.; McCollor, D.P. SCR deactivation in a full-scale cofired utility boiler. *Fuel* **2008**, *87*, 1341–1347. [[CrossRef](#)]
50. Kim, S.S.; Kang, Y.S.; Lee, H.D.; Kim, J.K.; Hong, S.C. Release of potassium and sodium species during combustion of various rank coals, biomass, sludge and peats. *J. Ind. Eng. Chem.* **2012**, *18*, 2199–2203. [[CrossRef](#)]
51. Chen, J.; Buzanowski, M.; Yang, R.; Cichanowicz, J. Deactivation of the vanadia catalyst in the selective catalytic reduction process. *J. Air Waste Manage. Assoc.* **1990**, *40*, 1403–1409. [[CrossRef](#)]
52. Benson, S.A.; Laumb, J.D.; Crocker, C.R.; Pavlish, J.H. SCR catalyst performance in flue gases derived from subbituminous and lignite coals. *Fuel Process. Technol.* **2005**, *86*, 577–613. [[CrossRef](#)]
53. Nicosia, D.; Czekaj, I.; Kröcher, O. Chemical deactivation of $\text{V}_2\text{O}_5/\text{WO}_3\text{-TiO}_2$ SCR catalysts by additives and impurities from fuels, lubrication oils and urea solution: Part II. Characterization study of the effect of alkali and alkaline earth metals. *Appl. Catal. B-Environ.* **2008**, *77*, 228–236. [[CrossRef](#)]
54. Liu, Y.; Gu, T.; Wang, Y.; Weng, X.; Wu, Z. Influence of Ca doping on $\text{MnO}_x/\text{TiO}_2$ catalysts for low-temperature selective catalytic reduction of NO_x by NH_3 . *Catal. Commun.* **2012**, *18*, 106–109. [[CrossRef](#)]
55. Shen, B.; Deng, L.; Chen, J. Effect of K and Ca on catalytic activity of Mn-CeO_x/Ti-PILC. *Front. Environ. Sci. Eng.* **2013**, *7*, 512–517. [[CrossRef](#)]
56. Zhou, A.Y.; Mao, H.F.; Sheng, Z.Y.; Tan, Y.; Yang, L. Poisoning effect of Ca depositing over Mn-Ce/TiO₂ catalyst for low-temperature selective catalytic reduction of NO by NH_3 . *Environ. Sci.* **2014**, *35*, 4745–4751.
57. Wang, X.B.; Zhou, J.; Wang, J.; Ding, A.F.; Gui, K.T.; Thomas, H.R. The effect of different Ca precursors on the activity of manganese and cerium oxides supported on TiO₂ for NO abatement. *React. Kinet. Mech. Catal.* **2020**, *129*, 153–164. [[CrossRef](#)]
58. Li, X.; Li, X.; Li, J.; Hao, J. High calcium resistance of $\text{CeO}_2\text{-WO}_3$ SCR catalysts: Structure investigation and deactivation analysis. *Chem. Eng. J.* **2017**, *317*, 70–79. [[CrossRef](#)]
59. Wang, D.; Luo, J.; Yang, Q.; Yan, J.; Zhang, K.; Zhang, W.; Peng, Y.; Li, J.; Crittenden, J. Deactivation mechanism of multipoisons in cement furnace flue gas on selective catalytic reduction catalysts. *Environ. Sci. Technol.* **2019**, *53*, 6937–6944. [[CrossRef](#)]
60. Deng, S.; Zhang, F.; Liu, Y.; Shi, Y.J.; Wang, H.M.; Zhang, C.; Wang, X.F.; Cao, Q. Lead emission and speciation of coal-fired power plants in China. *China Environ. Sci.* **2013**, *33*, 1199–1206.
61. Khodayari, R.; Odenbrand, C.I. Deactivating effects of lead on the selective catalytic reduction of nitric oxide with ammonia over a $\text{V}_2\text{O}_5/\text{WO}_3/\text{TiO}_2$ catalyst for waste incineration applications. *Ind. Eng. Chem. Res.* **1998**, *37*, 1196–1202. [[CrossRef](#)]
62. Linak, W.P.; Wendt, J.O. Trace metal transformation mechanisms during coal combustion. *Fuel Process. Technol.* **1994**, *39*, 173–198. [[CrossRef](#)]
63. Chen, G.; Ke, Z.Y.; Tang, N.; Zhang, K.; Liu, J. Preliminary study on the determination method of lead in flue gas of coal-fired power plant. *Adm. Tech. Environ. Monit.* **2020**, *32*, 52–54.
64. Jiang, Y. Study on Titanium-Based SCR Catalyst and Its Potassium and Lead Poisoning Mechanism. Ph.D. Thesis, Zhejiang University, Zhejiang, China, 2010.
65. Yan, D.J.; Tong, G.; Ya, Y.; Chen, Z.H. Lead poisoning and regeneration of Mn-Ce/TiO₂ catalysts for NH_3 -SCR of NO_x at low temperature. *J. Fuel Chem. Technol.* **2021**, *49*, 113–120. [[CrossRef](#)]

66. Guo, R.T.; Lu, C.Z.; Pan, W.G.; Zhen, W.L.; Wang, Q.S.; Chen, Q.L.; Ding, H.L.; Yang, N.Z. A comparative study of the poisoning effect of Zn and Pb on Ce/TiO₂ catalyst for low temperature selective catalytic reduction of NO with NH₃. *Catal. Commun.* **2015**, *59*, 136–139. [CrossRef]
67. Jiang, Y.; Gao, X.; Zhang, Y.; Wu, W.; Song, H.; Luo, Z.; Cen, K. Effects of PbCl₂ on selective catalytic reduction of NO with NH₃ over vanadia-based catalysts. *J. Hazard. Mater.* **2014**, *274*, 270–278. [CrossRef]
68. Jiang, Y.; Gao, X.; Du, X.S.; Mao, J.H.; Luo, Z.Y.; Cen, K.F. Effect of PbO on Selective Catalytic Reduction of NO by NH₃ over V₂O₅/TiO₂ Catalyst. *J. Eng. Thermophys.* **2009**, *30*, 1973–1976.
69. Jiang, Y.; Liang, G.; Bao, C.; Lu, M.; Lai, C.; Shi, W. The poisoning effect of PbO and PbCl₂ on CeO₂-TiO₂ catalyst for selective catalytic reduction of NO with NH₃. *J. Colloid Interface Sci.* **2018**, *528*, 82–91. [CrossRef]
70. Zhou, L.; Li, C.; Zhao, L.; Zeng, G.; Gao, L.; Wang, Y. The poisoning effect of PbO on Mn-Ce/TiO₂ catalyst for selective catalytic reduction of NO with NH₃ at low temperature. *Appl. Surf. Sci.* **2016**, *389*, 532–539. [CrossRef]
71. Jiang, Y.; Yang, L.; Liang, G.; Liu, S.; Gao, W.; Yang, Z.; Wang, X.; Lin, R.; Zhu, X. The poisoning effect of PbO on CeO₂-MoO₃/TiO₂ catalyst for selective catalytic reduction of NO with NH₃. *Mol. Catal.* **2020**, *486*, 110877. [CrossRef]
72. Kong, M.; Zhang, H.; Wang, Y.; Liu, Q.; Liu, W.; Wu, H. Deactivation mechanisms of MnO_x-CeO₂/Ti-bearing blast furnace slag low-temperature SCR catalyst by PbO and PbCl₂. *Mol. Catal.* **2022**, *521*, 112209. [CrossRef]
73. Castellino, F.; Rasmussen, S.B.; Jensen, A.D.; Johnsson, J.E.; Fehrmann, R. Deactivation of vanadia-based commercial SCR catalysts by polyphosphoric acids. *Appl. Catal. B-Environ.* **2008**, *83*, 110–122. [CrossRef]
74. Kröcher, O.; Elsener, M. Chemical deactivation of V₂O₅/WO₃-TiO₂ SCR catalysts by additives and impurities from fuels, lubrication oils, and urea solution: I. Catalytic studies. *Appl. Catal. B-Environ.* **2008**, *77*, 215–227. [CrossRef]
75. Yan, T.; Liu, Q.; Wang, S.; Xu, G.; Wu, M.; Chen, J.; Li, J. Promoter rather than Inhibitor: Phosphorus Incorporation Accelerates the Activity of V₂O₅-WO₃/TiO₂ Catalyst for Selective Catalytic Reduction of NO_x by NH₃. *ACS Catal.* **2020**, *10*, 2747–2753. [CrossRef]
76. Trabelsi, F.; Ait-Lyazidi, H.; Ratsimba, B.; Wilhelm, A.; Delmas, H.; Fabre, P.; Berlan, J. Oxidation of phenol in wastewater by sonoelectrochemistry. *Chem. Eng. Sci.* **1996**, *51*, 1857–1865. [CrossRef]
77. Kamata, H.; Takahashi, K.; Odenbrand, C. Surface acid property and its relation to SCR activity of phosphorus added to commercial V₂O₅ (WO₃)/TiO₂ catalyst. *Catal. Lett.* **1998**, *53*, 65–71. [CrossRef]
78. Gopal, N.O.; Lo, H.H.; Ke, T.F.; Lee, C.H.; Chou, C.C.; Wu, J.D.; Sheu, S.C.; Ke, S.C. Visible light active phosphorus-doped TiO₂ nanoparticles: An EPR evidence for the enhanced charge separation. *J. Phys. Chem. C* **2012**, *116*, 16191–16197. [CrossRef]
79. Miao, Z.; Li, Z.; Liang, M.; Meng, J.; Zhao, Y.; Xu, L.; Mu, J.; Zhou, J.; Zhuo, S.; Si, W. Ordered mesoporous titanium phosphate material: A highly efficient, robust and reusable solid acid catalyst for acetalization of glycerol. *Chem. Eng. J.* **2020**, *381*, 122594. [CrossRef]
80. Yao, X.; Wang, Z.; Yu, S.; Yang, F.; Dong, L. Acid pretreatment effect on the physicochemical property and catalytic performance of CeO₂ for NH₃-SCR. *Appl. Catal. A-Gen.* **2017**, *542*, 282–288. [CrossRef]
81. You, Y.; Chang, H.; Zhu, T.; Zhang, T.; Li, X.; Li, J. The poisoning effects of phosphorus on CeO₂-MoO₃/TiO₂ DeNO_x catalysts: NH₃-SCR activity and the formation of N₂O. *Mol. Catal.* **2017**, *439*, 15–24. [CrossRef]
82. You, Y.; Shi, C.; Chang, H.; Guo, L.; Xu, L.; Li, J. The promoting effects of amorphous CePO₄ species on phosphorus-doped CeO₂/TiO₂ catalysts for selective catalytic reduction of NO_x by NH₃. *Mol. Catal.* **2018**, *453*, 47–54. [CrossRef]
83. Zeng, Y.; Wang, Y.; Hongmanorom, P.; Wang, Z.; Zhang, S.; Chen, J.; Zhong, Q.; Kawi, S. Active sites adjustable phosphorus promoted CeO₂/TiO₂ catalysts for selective catalytic reduction of NO_x by NH₃. *Chem. Eng. J.* **2021**, *409*, 128242. [CrossRef]
84. Cao, J.; Rohani, S.; Liu, W.; Liu, H.; Lu, Z.; Wu, H.; Jiang, L.; Kong, M.; Liu, Q.; Yao, X. Influence of phosphorus on the NH₃-SCR performance of CeO₂-TiO₂ catalyst for NO_x removal from co-incineration flue gas of domestic waste and municipal sludge. *J. Colloid Interface Sci.* **2022**, *610*, 463–473. [CrossRef] [PubMed]
85. Lisi, L.; Lasorella, G.; Malloggi, S.; Russo, G. Single and combined deactivating effect of alkali metals and HCl on commercial SCR catalysts. *Appl. Catal. B-Environ.* **2004**, *50*, 251–258. [CrossRef]
86. Hou, Y.; Cai, G.; Huang, Z.; Han, X.; Guo, S. Effect of HCl on V₂O₅/AC catalyst for NO reduction by NH₃ at low temperatures. *Chem. Eng. J.* **2014**, *247*, 59–65. [CrossRef]
87. Choung, J.W.; Nam, I.-S. Characteristics of copper ion exchanged mordenite catalyst deactivated by HCl for the reduction of NO_x with NH₃. *Appl. Catal. B-Environ.* **2006**, *64*, 42–50. [CrossRef]
88. Choung, J.W.; Nam, I.-S. Role of cerium in promoting the stability of CuHM catalyst against HCl to reduce NO with NH₃. *Appl. Catal. A-Gen.* **2006**, *312*, 165–174. [CrossRef]
89. Yang, N.Z.; Guo, R.T.; Pan, W.G.; Chen, Q.L.; Wang, Q.S.; Lu, C.Z.; Wang, S.X. The deactivation mechanism of Cl on Ce/TiO₂ catalyst for selective catalytic reduction of NO with NH₃. *Appl. Surf. Sci.* **2016**, *378*, 513–518. [CrossRef]
90. Chang, F.Y.; Chen, J.C.; Wey, M.Y. Activity and characterization of Rh/Al₂O₃ and Rh-Na/Al₂O₃ catalysts for the SCR of NO with CO in the presence of SO₂ and HCl. *Fuel* **2010**, *89*, 1919–1927. [CrossRef]
91. Lu, M.Y. Influence of Cl on the Flue Gas Denitration Performance of Ce-Ti series Metal Oxide Catalysts. Master's Thesis, China University of Petro-leum (East China), Shandong, China, 2018.
92. Zhang, S.; Li, H.; Zhong, Q. Promotional effect of F-doped V₂O₅-WO₃/TiO₂ catalyst for NH₃-SCR of NO at low-temperature. *Appl. Catal. A-Gen.* **2012**, *435*, 156–162. [CrossRef]

93. Zhang, S.; Zhong, Q.; Zhao, W.; Li, Y. Surface characterization studies on F-doped V_2O_5/TiO_2 catalyst for NO reduction with NH_3 at low-temperature. *Chem. Eng. J.* **2014**, *253*, 207–216. [[CrossRef](#)]
94. Zhang, R.; Zhong, Q.; Zhao, W.; Yu, L.; Qu, H. Promotional effect of fluorine on the selective catalytic reduction of NO with NH_3 over CeO_2-TiO_2 catalyst at low temperature. *Appl. Surf. Sci.* **2014**, *289*, 237–244. [[CrossRef](#)]
95. Ciardelli, C.; Nova, I.; Tronconi, E.; Chatterjee, D.; Bandl-Konrad, B. A “Nitrate Route” for the low temperature “Fast SCR” reaction over a $V_2O_5-WO_3/TiO_2$ commercial catalyst. *Catal. Commun.* **2004**, *23*, 2718–2719.
96. Koebel, M.; Elsener, M.; Madia, G. Reaction pathways in the selective catalytic reduction process with NO and NO_2 at low temperatures. *Ind. Eng. Chem. Res.* **2001**, *40*, 52–59. [[CrossRef](#)]
97. Zhang, R. Preparation and Denitration Performance of F-Doped Cerium-Titanium Catalysts for low-Temperature SCR. Ph.D. Thesis, Nanjing University of Science and Technology, Nanjing, China, 2014.
98. Yang, N.Z.; Guo, R.T.; Tian, Y.; Pan, W.G.; Chen, Q.L.; Wang, Q.S.; Lu, C.Z.; Wang, S.X. The enhanced performance of ceria by HF treatment for selective catalytic reduction of NO with NH_3 . *Fuel* **2016**, *179*, 305–311. [[CrossRef](#)]
99. Jin, Q.; Shen, Y.; Zhu, S. Effect of fluorine additive on $CeO_2(ZrO_2)/TiO_2$ for selective catalytic reduction of NO by NH_3 . *J. Colloid Interface Sci.* **2017**, *487*, 401–409. [[CrossRef](#)] [[PubMed](#)]
100. Won, J.M.; Kim, J.T.; Jeong, S.K.; Hwang, S.M. Primary factors affecting denitrification efficiency of V-based catalysts in low-temperature selective catalytic reduction using NH_3 . *Appl. Surf. Sci.* **2021**, *566*, 150632. [[CrossRef](#)]
101. Lin, F.; Wang, Q.; Zhang, J.; Jin, J.; Lu, S.; Yan, J. Mechanism and kinetics study on low-temperature NH_3 -SCR over manganese-cerium composite oxide catalysts. *Ind. Eng. Chem. Res.* **2019**, *58*, 22763–22770. [[CrossRef](#)]
102. Liu, K.; He, H.; Chu, B. Microkinetic study of NO oxidation, standard and fast NH_3 -SCR on $CeWO_x$ at low temperatures. *Chem. Eng. J.* **2021**, *423*, 130128. [[CrossRef](#)]
103. Woo, J.; Wang, A.; Bernin, D.; Ahari, H.; Shost, M.; Zammit, M.; Olsson, L. Impact of Different Synthesis Methods on the Low-Temperature Deactivation of Cu/SAPO-34 for NH_3 -SCR Reaction. *Emiss. Control. Sci. Technol.* **2021**, *7*, 198–209. [[CrossRef](#)]
104. Yang, W.; Ren, J.; Zhang, H.; Li, J.; Wu, C.; Gates, I.D.; Gao, Z. Single-atom iron as a promising low-temperature catalyst for selective catalytic reduction of NO_x with NH_3 : A theoretical prediction. *Fuel* **2021**, *302*, 121041. [[CrossRef](#)]
105. Wang, H.; Huang, B.; Yu, C.; Lu, M.; Huang, H.; Zhou, Y. Research progress, challenges and perspectives on the sulfur and water resistance of catalysts for low temperature selective catalytic reduction of NO_x by NH_3 . *Appl. Catal. A-Gen.* **2019**, *588*, 117207. [[CrossRef](#)]
106. Xiao, X.; Xiong, S.; Shi, Y.; Shan, W.; Yang, S. Effect of H_2O and SO_2 on the selective catalytic reduction of NO with NH_3 over Ce/TiO_2 catalyst: Mechanism and kinetic study. *J. Phys. Chem. C* **2016**, *120*, 1066–1076. [[CrossRef](#)]
107. Wang, Y.; Ge, D.; Chen, M.; Gao, S.; Wu, Z. A dual-functional way for regenerating NH_3 -SCR catalysts while enhancing their poisoning resistance. *Catal. Commun.* **2018**, *117*, 69–73. [[CrossRef](#)]
108. Wu, Z.; Jin, R.; Wang, H.; Liu, Y. Effect of ceria doping on SO_2 resistance of Mn/TiO_2 for selective catalytic reduction of NO with NH_3 at low temperature. *Catal. Commun.* **2009**, *10*, 935–939. [[CrossRef](#)]
109. Xu, W.; He, H.; Yu, Y. Deactivation of a Ce/TiO_2 catalyst by SO_2 in the selective catalytic reduction of NO by NH_3 . *J. Phys. Chem. C* **2009**, *113*, 4426–4432. [[CrossRef](#)]
110. Wang, Q.; Zhou, J.; Zhang, J.; Zhu, H.; Feng, Y.; Jin, J. Effect of ceria doping on the catalytic activity and SO_2 resistance of MnO_x/TiO_2 catalysts for the selective catalytic reduction of NO with NH_3 at low temperatures. *Aerosol Air Qual. Res.* **2020**, *20*, 477–488. [[CrossRef](#)]
111. Zhai, G.; Han, Z.; Wu, X.; Du, H.; Gao, Y.; Yang, S.; Song, L.; Dong, J.; Pan, X. Pr-modified MnO_x catalysts for selective reduction of NO with NH_3 at low temperature. *J. Taiwan Inst. Chem. Eng.* **2021**, *125*, 132–140. [[CrossRef](#)]
112. Gao, C.; Shi, J.W.; Fan, Z.; Wang, B.; Wang, Y.; He, C.; Wang, X.; Li, J.; Niu, C. “Fast SCR” reaction over Sm-modified MnO_x-TiO_2 for promoting reduction of NO_x with NH_3 . *Appl. Catal. A-Gen.* **2018**, *564*, 102–112. [[CrossRef](#)]
113. Sun, P.; Guo, R.T.; Liu, S.M.; Wang, S.X.; Pan, W.G.; Li, M.Y. The enhanced performance of MnO_x catalyst for NH_3 -SCR reaction by the modification with Eu. *Appl. Catal. A-Gen.* **2017**, *531*, 129–138. [[CrossRef](#)]
114. Sheng, Z.; Hu, Y.; Xue, J.; Wang, X.; Liao, W. SO_2 poisoning and regeneration of $Mn-Ce/TiO_2$ catalyst for low temperature NO_x reduction with NH_3 . *J. Rare Earths* **2012**, *30*, 676–682. [[CrossRef](#)]
115. Kresse, G.; Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **1996**, *6*, 15–50.
116. Gu, T.; Liu, Y.; Weng, X.; Wang, H.; Wu, Z. The enhanced performance of ceria with surface sulfation for selective catalytic reduction of NO by NH_3 . *Catal. Commun.* **2010**, *12*, 310–313. [[CrossRef](#)]
117. Shen, Y.; Ma, Y.; Zhu, S. Promotional effect of zirconium additives on $Ti_{0.8}Ce_{0.2}O_2$ for selective catalytic reduction of NO. *Catal. Sci. Technol.* **2012**, *2*, 589–599. [[CrossRef](#)]
118. Shen, B.; Liu, T.; Zhao, N.; Yang, X.; Deng, L. Iron-doped $Mn-Ce/TiO_2$ catalyst for low temperature selective catalytic reduction of NO with NH_3 . *J. Environ. Sci.* **2010**, *22*, 1447–1454. [[CrossRef](#)]
119. Liu, C.; Chen, L.; Li, J.; Ma, L.; Arandiyana, H.; Du, Y.; Xu, J.; Hao, J. Enhancement of activity and sulfur resistance of CeO_2 supported on TiO_2-SiO_2 for the selective catalytic reduction of NO by NH_3 . *Environ. Sci. Technol.* **2012**, *46*, 6182–6189. [[CrossRef](#)]
120. Yu, J.; Guo, F.; Wang, Y.; Zhu, J.; Liu, Y.; Su, F.; Gao, S.; Xu, G. Sulfur poisoning resistant mesoporous Mn-base catalyst for low-temperature SCR of NO with NH_3 . *Appl. Catal. B-Environ.* **2010**, *95*, 160–168. [[CrossRef](#)]

121. Shan, W.; Liu, F.; He, H.; Shi, X.; Zhang, C. The Remarkable Improvement of a CeTi based Catalyst for NO_x Abatement, Prepared by a Homogeneous Precipitation Method. *ChemCatChem* **2011**, *3*, 1286–1289. [[CrossRef](#)]
122. Wang, Q.; Wang, R.; Huang, X.; Shi, H. Sulfur/water resistance and regeneration of MnO_x-CeO₂/TiO₂ catalyst for low-temperature selective catalytic reduction of NO_x. *J. Environ. Chem. Eng.* **2022**, *10*, 107345.