

Article

Defect-Engineering of 2D Dichalcogenide VSe₂ to Enhance Ammonia Sensing: Acumens from DFT Calculations

Gopal Sanyal ¹, Surinder Pal Kaur ², Chandra Sekhar Rout ³ and Brahmananda Chakraborty ^{4,5,*}¹ Mechanical Metallurgy Division, Bhabha Atomic Research Centre, Trombay, Mumbai 400085, India² Department of Chemistry, Indian Institute of Technology Ropar, Rupnagar 140001, India³ Centre for Nano and Material Sciences, Jain Global Campus, Jakkasandra, Ramangaram, Bangalore 562112, India⁴ High Pressure and Synchrotron Radiation Physics Division, Bhabha Atomic Research Centre, Trombay, Mumbai 400085, India⁵ Homi Bhabha National Institute, Mumbai 400094, India

* Correspondence: brahma@barc.gov.in

Abstract: Opportune sensing of ammonia (NH₃) gas is industrially important for avoiding hazards. With the advent of nanostructured 2D materials, it is felt vital to miniaturize the detector architecture so as to attain more and more efficacy with simultaneous cost reduction. Adaptation of layered transition metal dichalcogenide as the host may be a potential answer to such challenges. The current study presents a theoretical in-depth analysis regarding improvement in efficient detection of NH₃ using layered vanadium di-selenide (VSe₂) with the introduction of point defects. The poor affinity between VSe₂ and NH₃ forbids the use of the former in the nano-sensing device's fabrications. The adsorption and electronic properties of VSe₂ nanomaterials can be tuned with defect induction, which would modulate the sensing properties. The introduction of Se vacancy to pristine VSe₂ was found to cause about an eight-fold increase (from −0.12 eV to −0.97 eV) in adsorption energy. A charge transfer from the N 2p orbital of NH₃ to the V 3d orbital of VSe₂ has been observed to cause appreciable NH₃ detection by VSe₂. In addition to that, the stability of the best-defected system has been confirmed through molecular dynamics simulation, and the possibility of repeated usability has been analyzed for calculating recovery time. Our theoretical results clearly indicate that Se-vacant layered VSe₂ can be an efficient NH₃ sensor if practically produced in the future. The presented results will thus potentially be useful for experimentalists in designing and developing VSe₂-based NH₃ sensors.

Keywords: 2D materials; VSe₂ monolayer; ammonia sensing; electronic properties; reversible sensors; density functional theory



Citation: Sanyal, G.; Kaur, S.P.; Rout, C.S.; Chakraborty, B.

Defect-Engineering of 2D Dichalcogenide VSe₂ to Enhance Ammonia Sensing: Acumens from DFT Calculations. *Biosensors* **2023**, *13*, 257. <https://doi.org/10.3390/bios13020257>

Received: 4 December 2022

Revised: 7 February 2023

Accepted: 10 February 2023

Published: 11 February 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

With the development of technology, the requirement for gas sensors in the fields of industry, agriculture, medicine, air-quality monitoring, etc., has been amplified [1,2]. For instance, gases such as carbon monoxide, nitrogen oxide, nitrogen dioxide, ammonia, etc. are harmful to living beings and can trigger serious health issues [3,4]. To eliminate such hazardous gases from the environment, lucrative sensors with good stability, sensitivity, and selectivity are desirable. In the past, metal oxides such as ZnO, SnO₂, and so on were explored as efficient sensors having good sensitivity and selectivity towards the sensing of harmful gases [5]. Although metal oxides are cheaper and need low fabrication costs, their elevated operating temperature restricts their use in sensing devices [6]. Following this, various types of sensing materials have been reported in the past. Among all the reported sensing materials, chemi-resistors are recommended as promising sensitive and selective sensors [7,8]. For instance, Oudenhoven et al. reported a thin layer of ionic liquid [BMIM][NTf₂] as the electrolyte, capable of sensing NH₃ even at a level of 1 ppm [9]. On the other hand, Amirjani et al. reported a calorimetric sensor for detecting NH₃ by

utilizing localized surface plasmon resonance of Ag nanoparticles for detection in the range of 10–1000 mg L⁻¹ [10]. The electrochemical sensor developed by Arya et al. uses SnO₂ nanoparticles synthesized with the sol–gel route to sense NH₃ in aqueous solution [11].

Graphene is a two-dimensional carbon allotrope with a zero band gap and possesses a high surface-to-volume ratio [12,13]. The discovery of graphene brought a breakthrough in the exploration of two-dimensional nanomaterials [14–18]. Due to the presence of novel physical and chemical properties, two-dimensional nanomaterials can be used in a wide range of applications such as energy storage devices, catalysis, sensing devices, etc. [19–21]. The application of two-dimensional materials, namely borophene, phosphorene, transition metal dichalcogenides (TMDs), etc., in gas sensing has been studied by different research groups [19–26]. For instance, honeycomb germanium is reported to act as an efficient sensor as compared to graphene-based sensors [27,28]. Sosa and his coworkers investigated the application of alkali, alkaline earth metals, and transition metal-doped germanene in ammonia (NH₃) sensing by computing adsorption energies, charge transfer analysis, work function, and desorption time [29]. Several other studies have also been reported in the past to investigate the adsorption properties of NH₃ on different two-dimensional materials [30]. For instance, adsorption energies and diffusion energy barriers were computed for NH₃ adsorption on MoO₃ nanomaterial by Xu and coworkers [31]. The authors reported the low sensing of NH₃ on the studied two-dimensional material. Lv and his coworkers studied the sensing properties of NH₃ on a two-dimensional C₃N monolayer by performing density functional theory [32].

Transition metal dichalcogenide nanosheet; MoSe₂ is reported to act as an efficient sensor in the sensing of CO, NO, NO, and NO₂ gases [33,34]. It is also possible to tune the physical and chemical properties of such two-dimensional nanomaterials by tuning their structures [35–43]. The Janus TMDs are two-dimensional nanomaterials in which a metal layer is sandwiched between two different non-metal atom layers. The difference in the non-metal atom layers introduces asymmetry, which is responsible for enhancing the physicochemical properties of such materials. The Janus TMDs have been explored for their use in hydrogen storage, catalysis, water splitting, etc. [44–47]. Along with these properties, the application of Janus TMDs in gas sensing has also been studied by researchers in the past [48–50]. For instance, the role of MoSSe nanomaterial in the sensing of CO, CO₂, NO, and NO₂ was studied using DFT methods [46]. The authors reported that the selectivity of sensing can be improved with the help of external strain. Following this, the sensing properties of the defected Janus TMDs have also been studied in the past [51]. The studies showed that the defected Janus TMDs showed higher sensitivity towards the gas molecules as compared to pristine monolayers.

The charge transfer between adsorbate and adsorbent partakes in the gas sensing mechanism (Figure 1). Previous studies showed that the gas-sensing behavior of two-dimensional can be improved by introducing p-type or n-type doping [52–55]. The doping can be introduced by incorporating impurities in the two-dimensional nanomaterial lattice [56,57]. Suh and his group reported the hole generation in the MoSe₂ monolayer with the doping of Nb in the lattice structure [58]. The gas-sensing behavior of Nb-doped MoS₂ nanosheets has been investigated by Choi and his coworkers [59]. Their report stated that optimum NO₂ sensing of MoS₂ can be enhanced up to 8% with Nb doping and hence, can be considered an effective way to achieve high-performance gas sensing devices. The improvement of the gas-sensing behavior of MoSe₂ and MoTe₂ nanomaterials with the elemental substitution is also reported in the past [60]. The role of V, Nb, and Ta-doped MoS₂ in NH₃, H₂O, and NO₂ sensing has been studied by Zhu and his group [61]. Authors suggested that doping of transition metal atoms enriches the sensing properties of MoS₂. The effect of Al, Si, and P-doped MoS₂ on the adsorption as well as sensing of NH₃ has been studied by Luo and his group [62]. The effect of nitrogen, phosphorus, and arsenic doping on the CO, NO, and HF sensing of Janus WSSe nanosheets has been studied in the past using DFT methods [63]. The studies showed that ~3.12% doping of nitrogen, phosphorus, and arsenic makes Janus WSSe nanosheets efficient sensing materials even

without imposing external strain. The utilization of VSe₂ nanomaterial for the sensing of nitrobenzene and catechol has been reported in past studies [64,65]. Vacancy engineering has been reviewed as a critical strategy for tuning electron and phonon structures of two-dimensional materials in general and for gas-sensing applications in particular [66–68]. For instance, in the case of TMDs, the introduction of vacancy has been reported to be beneficial for the sensing of SO₂, NH₃, NO₂, 'NO, O₂, and CO, and decomposed SF₆ gases in SnSe₂, SnS₂, MoS₂, PtSe₂, and WS₂ layered systems, respectively [69–73]. Keeping the above in mind, the potential of vacancy-engineered VSe₂ for the detection of NH₃ appears to be a still unaddressed topic, to the best knowledge of the authors.

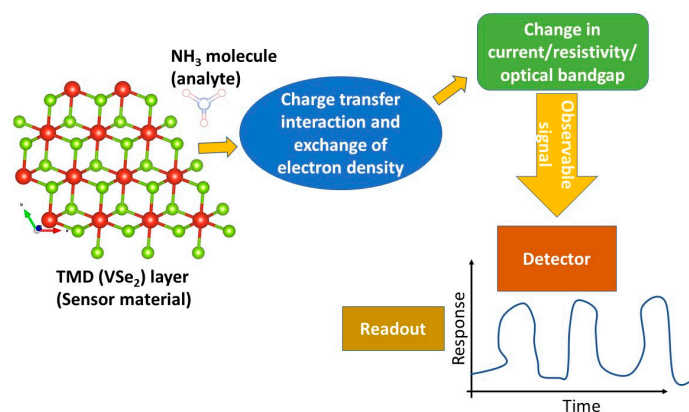


Figure 1. Schematic flow diagram of gas sensing mechanism involving charge transfer interactions.

The modality of detection of NH₃ with VSe₂ nanosheets has thus been theoretically studied in the present work. The effect of defect-engineered nanosheets has also been considered in this work by introducing V-defected as well as Se-defected layered VSe₂ nanomaterials. Using first-principles calculations, the change in the electronic and magnetic properties of defected VSe₂ monolayers has been compared with the pristine material. The sensing capabilities of pristine and defected VSe₂ monolayers have also been assessed in terms of adsorption energy values, electronic, magnetic, and charge transfer properties with the NH₃ molecule.

2. Computational Methods

The density functional theory (DFT) computations were accomplished by means of the Projector Augmented Wave (PAW) principles as implemented in the Vienna ab initio Simulation Package (VASP) [74–77]. In the simulations, generalized gradient approximation (GGA) was used for exchange–correlation functions [78]. During the computations, the convergence criteria for Hellman–Feynman forces were kept at 0.01 eV/Å alongside the plane wave cut-off energy of 600 eV. The long-range interactions may impact the sensing properties of the material. Hence, long-range interactions were taken care of with Grimme’s DFT-D3 functional [79,80]. The Γ -centered K-points grid of $6 \times 6 \times 1$ was used for the integration of the first Brillouin zone [81]. A vacuum of 20 Å was introduced in the z-direction to avoid the interactions between the layers in the Z direction. The thermal stability of the VSe₂ monolayer adsorbed with NH₃ was computed with the help of ab-initio molecular dynamics simulations (AIMD). The AIMD simulations were carried out in the NVT ensemble using the Nosé–Hoover thermostat to determine the thermal stability of VSe₂ + NH₃ and VSe₂(Se_v) + NH₃ systems at 400 K. The simulations were carried out for a total time of 5 ps with a time step of 1 fs.

3. Results and Discussion

3.1. Structural Analysis of Pristine and Defected VSe₂

The $4 \times 4 \times 1$ supercell of VSe₂ was used to mimic the two-dimensional monolayer in this work. The geometry-relaxed structure of pristine VSe₂ is shown in Figure 2a. In

this structure, the metal atom layer is embedded between the selenium atom layers. Using the optimized structure of pristine VSe_2 , V-defected VSe_2 was constructed by removing a single V-metal atom from the monolayer [Figure 2b]. Similarly, the Se-defected layer was modeled by eliminating a Se-atom from the monolayer [Figure 2c]. The V and Se-defected monolayers are described as $VSe_2(V_v)$ and $VSe_2(Se_v)$, distinctly. The optimized structures of VSe_2 , $VSe_2(V_v)$, and $VSe_2(Se_v)$ are used for the further adsorption of the NH_3 molecule at various possible positions, as mentioned below.

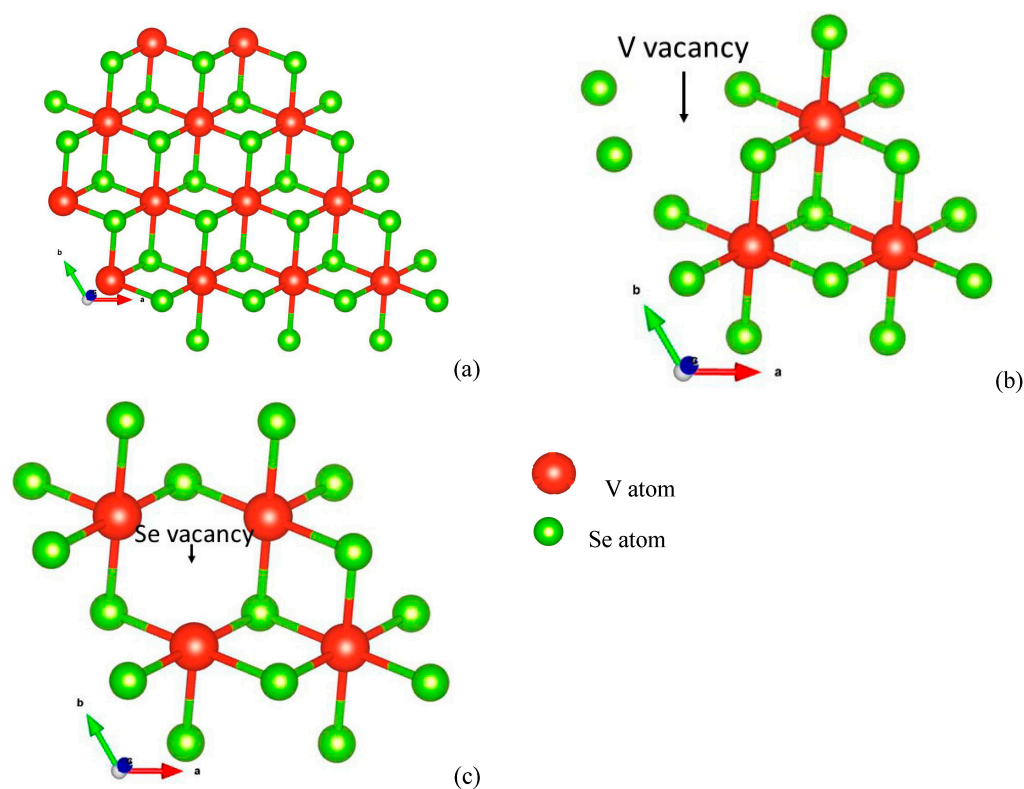


Figure 2. Relaxed structure of (a) pristine VSe_2 , (b) VSe_2 deficient with V atom, and (c) VSe_2 deficient with Se atom.

3.2. Adsorption of NH_3 on VSe_2 , $VSe_2(V_v)$, and $VSe_2(Se_v)$

To understand the NH_3 sensing of pure and defected VSe_2 , the NH_3 molecule was placed at various possible sites, 2 Å above the VSe_2 , $VSe_2(V_v)$, and $VSe_2(Se_v)$ monolayers. The structurally relaxed geometries upon NH_3 introduction on VSe_2 , $VSe_2(V_v)$, and $VSe_2(Se_v)$ monolayers are depicted in Figure 3. The stability of the NH_3 adsorbed complexes is assessed in terms of adsorption energy values both with and without van der Waals (VdW) interactions.

The adsorption energy is computed using the following equation:

$$BE = E_{(\text{complex})} - E_{(\text{monolayer})} - E_{(NH_3)} \quad (1)$$

In this equation, $E_{(\text{complex})}$ is the energy of the NH_3 adsorbed $VSe_2/VSe_2(V_v)/VSe_2(Se_v)$ systems. The $E_{(\text{monolayer})}$ represents the energy of the VSe_2 or $VSe_2(V_v)$ or $VSe_2(Se_v)$ systems. The last term $E_{(NH_3)}$ represents the energy of the isolated ammonia gas molecule.

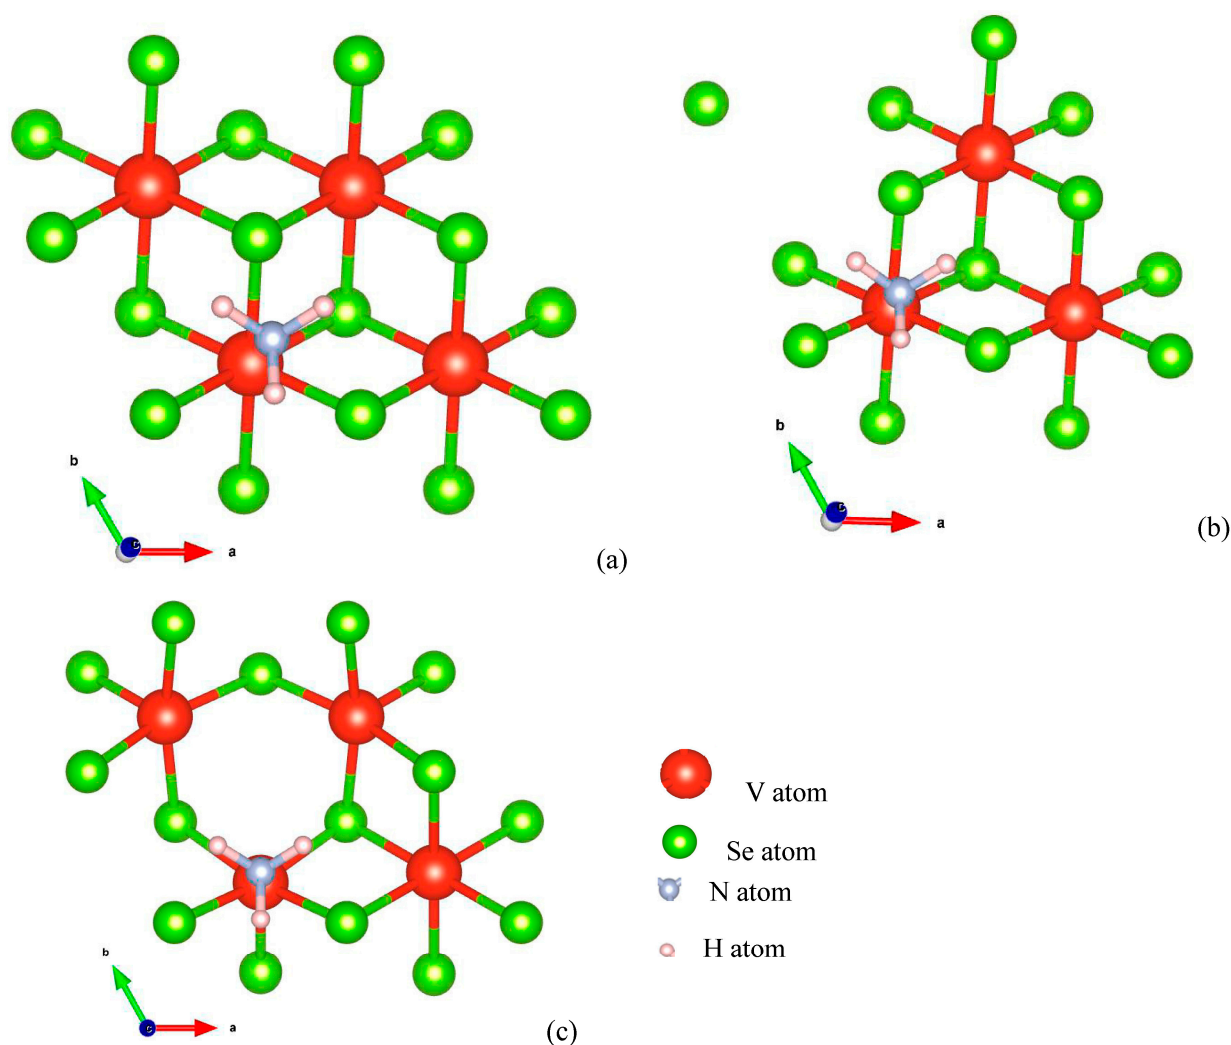


Figure 3. Relaxed structures of (a) NH_3 (N atom directly placed above V atom) on pristine VSe_2 , (b) NH_3 (N atom directly placed above V atom) on VSe_2 deficient with V atom, and (c) NH_3 (N atom directly placed above V atom) on VSe_2 deficient with Se atom.

The adsorption energy values are shown in Table 1. It can be observed from Table 1 that the NH_3 molecule is weakly bound to the pure VSe_2 . Or, in other words, the NH_3 shows weak affinity towards the VSe_2 monolayer, specifying that pure material is not much suitable for sensing purposes. The result shown in Table 1 for the $\text{VSe}_2 + \text{NH}_3$ system corresponds to the adsorption energy of 0.124 eV for the case when the N atom of NH_3 has been placed upright the V atom of VSe_2 . The same practice has been repeated for the other three possible sites, i.e., Se atom, V-Se bond, and center of a hexagonal ring consisting of V and Se atoms, and all four obtained adsorption energy values are shown in Table S1. As can be seen, the adsorption energy for the arrangement corresponding to the “above V” case is the least (though positive without VdW incorporation); further, all calculations are based on that arrangement. However, $\text{VSe}_2(\text{V}_v)$ and $\text{VSe}_2(\text{Se}_v)$ monolayers show stronger affinity towards NH_3 with adsorption energy values of -0.22 and -0.66 eV, respectively. The present studies also determined the influence of long-range interactions by computing the adsorption energy values with DFT-D3 functional to consider van der Waal interaction. It can be observed from Table 1 that the adsorption energy values improve with the inclusion of VdW interactions. The values reported in Table 1 suggest that the $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ forms the most stable complex due to higher adsorption energy values. The bond lengths between NH_3 and the adsorbent are also measured and are given in Table 1. In the case of $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$, the distance between the vanadium atom of the monolayer and the N

atom of NH_3 is reduced as compared to the $\text{VSe}_2 + \text{NH}_3$ complex. This supports stronger adsorption interactions between $\text{VSe}_2(\text{Se}_v)$ and the NH_3 molecule. As the $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ forms the most stable complex, the change in the electronic properties of pure and Se-defected monolayers with the adsorption of NH_3 molecule is studied in this work and has been comparatively discussed further.

Table 1. Adsorption energies for the adsorption of NH_3 on VSe_2 , $\text{VSe}_2(\text{V}_v)$, and $\text{VSe}_2(\text{Se}_v)$ systems with and without VdW functional. The bond lengths between the atoms of adsorbate and adsorbent are given in Å units.

System	Adsorption Energy (eV)	Bond Length (Å)
$\text{VSe}_2 + \text{NH}_3$	0.124	V-N: 4.786 S-N: 3.94
$\text{VSe}_2 + \text{NH}_3$ (with VdW)	−0.12	V-N: 4.709 S-N: 3.93
VSe_2 (V vacancy) + NH_3	−0.219	V-N: 4.756 S-N: 3.92
VSe_2 (V vacancy) + NH_3 (with VdW)	−0.342	V-N: 4.479 S-N: 3.732
VSe_2 (Se vacancy) + NH_3	−0.664	V-N: 2.26 S-N: 3.697
VSe_2 (Se vacancy) + NH_3 (with VdW)	−0.97	V-N: 2.253 S-N: 3.681
VSe_2 (2Se vacancy) + NH_3	−1.33	V-N: 2.242 S-N: 3.514
VSe_2 (2Se vacancy) + NH_3 (with VdW)	−1.58	V-N: 2.241 S-N: 3.501

To study the effect of a further increase in defect density, a VSe_2 structure deficient with two Se atoms has been relaxed and again optimized with the insertion of an NH_3 molecule. (Figure 4). The resultant adsorption energy values (−1.33 and −1.58 eV with VdW), as shown in Table 1, indicate stronger adsorption. Such observation is promising to conclude that doubling the Se vacancy population is beneficial for better NH_3 detection.

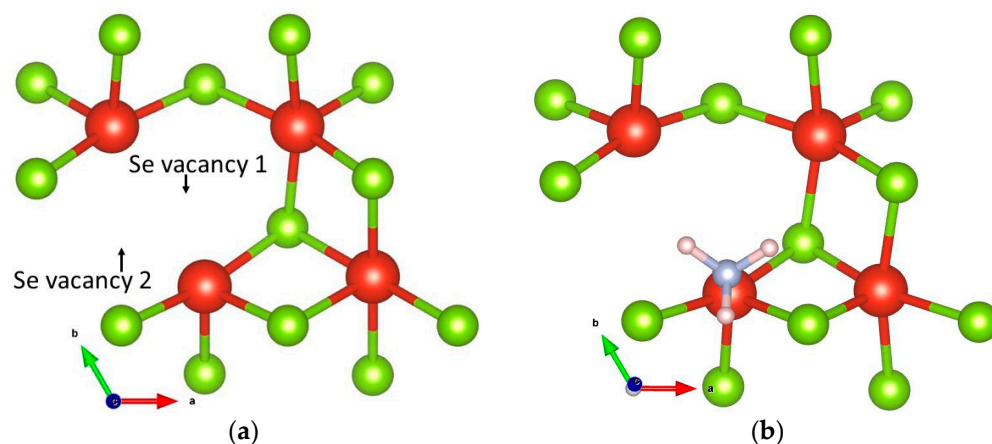


Figure 4. Relaxed structures of (a) VSe_2 deficient with 2 Se atoms and (b) NH_3 (N atom directly placed above V atom) on VSe_2 deficient with 2 Se atoms.

3.3. Total Density of States (TDOS) Plots

In order to get insights regarding charge transfer and the interaction mechanism of NH_3 with pristine and defected VSe_2 , we have presented total and partial density of states analyses. The TDOS plot of a pure VSe_2 monolayer is specified in Figure 3a. To determine the magnetic behavior, spin-up and spin-down states are plotted. It is observed from the figure that the pure material is magnetic due to the asymmetry in spin states. The existence of the density of states at the Fermi level implies the metallic behavior of the materials, consistent with earlier findings [64,65]. The total density of states enhanced by the adsorption of the NH_3 molecule on VSe_2 is shown in Figure 5a. In the case of the $\text{VSe}_2(\text{Se}_v)$ system, an enhancement in TDOS is observed below the Fermi level, as depicted in Figure 5b. The enhancement in the density of states occurs due to the unbound V-atom bonds after the removal of the Se atom from the monolayer. The change in the density of

states with the adsorption of NH_3 supports the orbital interactions. The density of states is also enhanced at the Fermi level with the adsorption of NH_3 on the $\text{VSe}_2(\text{Se}_v)$ system.

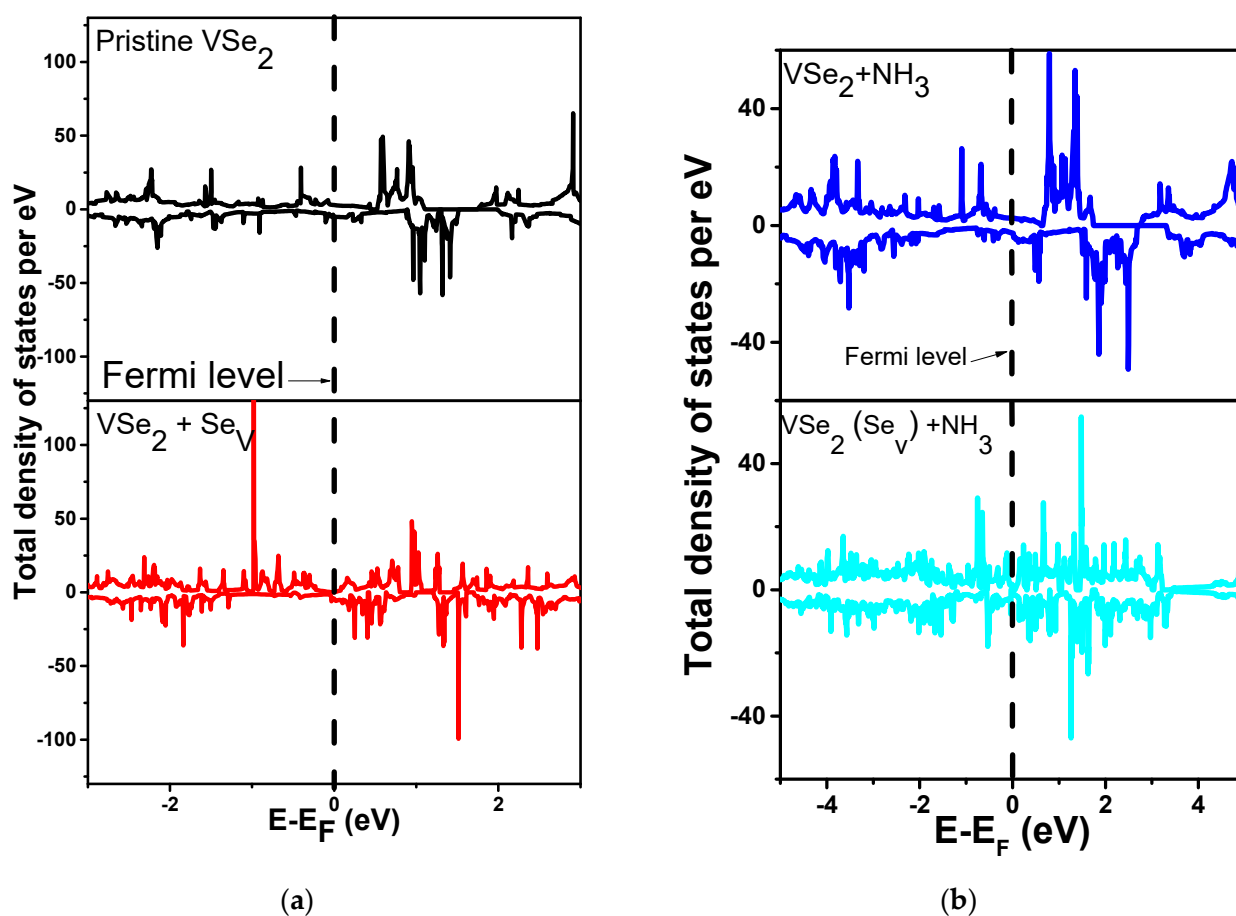


Figure 5. Comparison of TDOS plots between (a) Pristine VSe_2 and VSe_2 with Se Vacancy, and (b) NH_3 adsorbed on pristine VSe_2 on V atom, and NH_3 adsorbed on VSe_2 with Se vacancy on V atom.

3.4. Partial Density of States (PDOS) Plots

To investigate the orbital interactions, the spin-polarized partial density of states (PDOS) is analyzed. The spin-polarized partial density of states (PDOS) for N-2p and H-1s orbitals in NH_3 and $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ were computed and are shown in Figure 6a. In the case of the NH_3 molecule, the partial density of states for N-2p and H-1s orbitals is spotted in the valence band. These partial densities of states disappeared (or were reduced) with the adsorption of NH_3 on the $\text{VSe}_2(\text{Se}_v)$ monolayer. Further, the spin-polarized partial density of states (PDOS) of V-3d orbitals for $\text{VSe}_2 + \text{Se}_v$ and $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ were computed and are shown in Figure 6b. On comparing the PDOS of V-3d orbitals of $\text{VSe}_2(\text{Se}_v)$ and $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ systems, it can be observed that the densities of states are enhanced in the latter with the adsorption of the NH_3 molecule. This suggests that the monolayer is acting as an electron acceptor, whereas NH_3 is acting as an electron donor. So, we can say that there is a charge transfer from NH_3 to $\text{VSe}_2(\text{Se}_v)$ due to the adsorption of NH_3 .

The total density of states and partial density of states plots have shown that the electronic properties of the VSe_2 monolayer can be tuned with the defect induction, which impacts the adsorption properties.

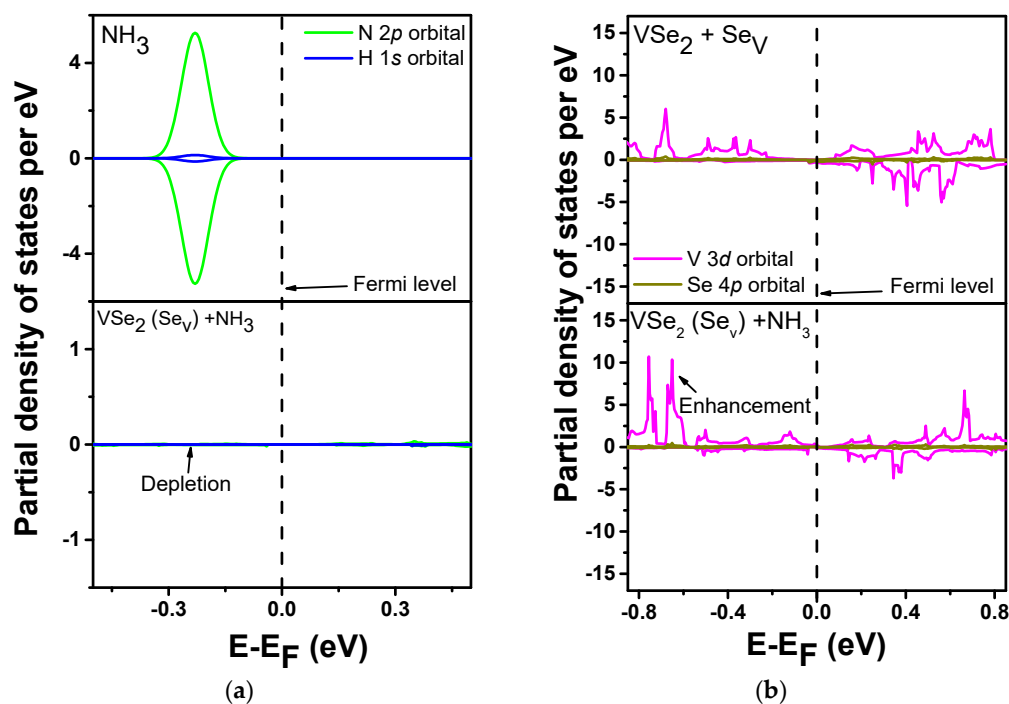


Figure 6. PDOS plots for (a) N 2p and H 1s orbital in NH₃ and NH₃ + VSe₂ with Se vacancy and (b) V 3d and Se 4p orbital in VSe₂ with Se vacancy and NH₃ + VSe₂ with Se vacancy.

3.5. Charge Transfer Analysis

The interactions between the analyte and host were determined in terms of Bader charge analysis [82]. The VSe₂(Se_v) monolayer shows a net gain of 0.009e of charge due to adsorption of the NH₃ molecule whereas, the NH₃ molecule shows a net loss of 0.009e of charge, suggesting that the monolayer acts as an electron acceptor. The Bader charge analysis is in accordance with the partial density of states (PDOS) plots (Figure 6). The above observation is consistent with the opinion of earlier researchers regarding ammonia sensing in terms of charge transfer course. (Table 2) [37,83–86]. Additionally, a charge density difference plot has been shown in Figure 7. It is performed with the relation:

$$\rho_{Difference} = \rho_{VSe_2(Se_v)+NH_3} - \rho_{VSe_2(Se_v)} - \rho_{NH_3}$$

Table 2. Comparison with earlier reported charge transfer data for NH₃ sensing.

2D Material	Charge Lost by NH ₃	Reference
MoS ₂ / WS ₂	0.09e/0.03e	[37]
Ag ₃ -WSe ₂ monolayer	0.202e	[83]
MoS ₂	Pictorial illustration	[84]
Ti ₃ C ₂ T _x MXene @ TiO ₂ /MoS ₂ heterostructure	~0.03e	[85]
WOS nanosheet	Pictorial illustration	[86]
VSe ₂ (Se _v)	0.009e	This work

For all three systems, the ISO values are around 0.04e, wherein red regions denote regions of charge loss and green or blue regions denote charge gain. In all three systems, a charge loss region is noted around the N atom of the NH₃ molecule, while a charge gain region is noted over the VSe₂ surface with a Se vacancy.

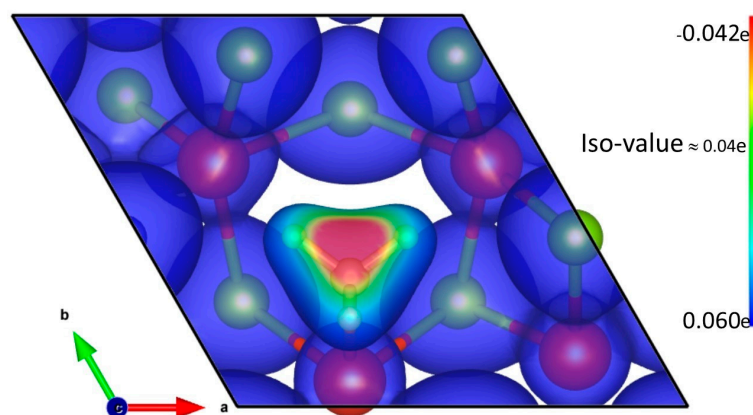


Figure 7. The charge density difference plot of NH_3 -attached Se-deficient VSe_2 . Red regions indicate charge loss, whereas blue and green regions indicate charge gain.

3.6. Thermal Stability from Molecular Dynamics Simulations

A nanosensor should be stable at higher temperatures for its efficient performance. Moreover, the gas molecules adsorbed on it should remain intact in the system until the sensing procedure is completed. As pristine VSe_2 is a synthesized material, it is thermally stable at room temperature. So, we have investigated the thermal stability of $\text{VSe}_2 + \text{NH}_3$ and $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ systems. The ab initio molecular dynamics simulations were carried out to investigate the thermal stability of the considered material at higher temperatures. The snapshots of equilibrated $\text{VSe}_2 + \text{NH}_3$ and $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ systems after 5 ps at 400 K are shown in Figure 8.

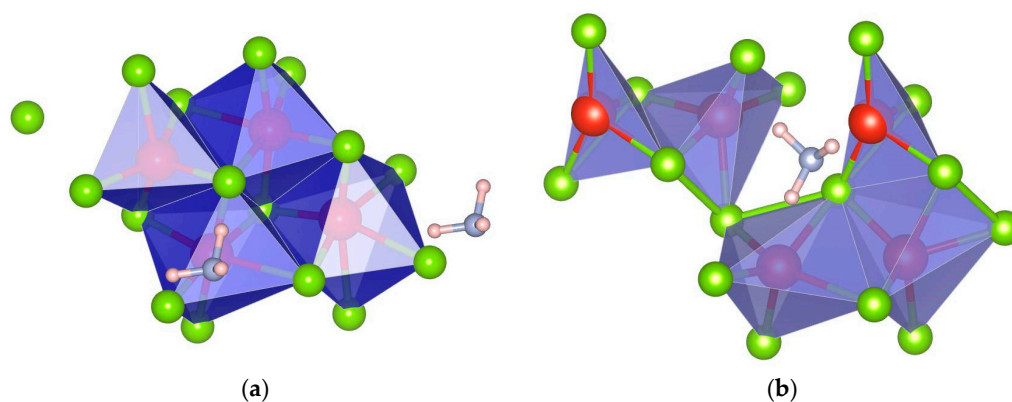


Figure 8. MD snapshots (a) $\text{VSe}_2 + \text{NH}_3$ (b) $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ at 400 K after 5 ps; for the pristine VSe_2 : as adsorption energy is less, NH_3 is desorbed while for $\text{VSe}_2(\text{Se}_v)$ it remains intact.

The bond length fluctuations (between N of NH_3 and V of VSe_2) with the temperature are plotted in Figure 9. We can notice that for pristine VSe_2 , the NH_3 molecule goes away from the system starting with a temperature of 108 K. It seems that the NH_3 molecule desorbs from the system once the temperature is increased, with desorption starting around 108 K. This is because NH_3 is bonded very weakly on pristine VSe_2 and goes out of the system at higher temperatures. So NH_3 desorbs from the system below room temperature for pristine VSe_2 . So, pristine VSe_2 is not suitable for NH_3 sensing due to weaker interactions and low adsorption energy. But for $\text{VSe}_2(\text{Se}_v) + \text{NH}_3$ system, the bond length fluctuations are not much. It is around 10% of the mean value, suggesting that adsorbed NH_3 remains intact at 300 K and even up to 400 K on the sensing material. This is due to the fact that the adsorption energy of NH_3 on defected VSe_2 has increased from -0.12 eV for the pristine system to -0.97 eV for the $\text{VSe}_2(\text{Se}_v)$ system. Strong adsorption energy is due to charge transfer from NH_3 to defected VSe_2 . So, the defected VSe_2 is promising for NH_3 sensing.

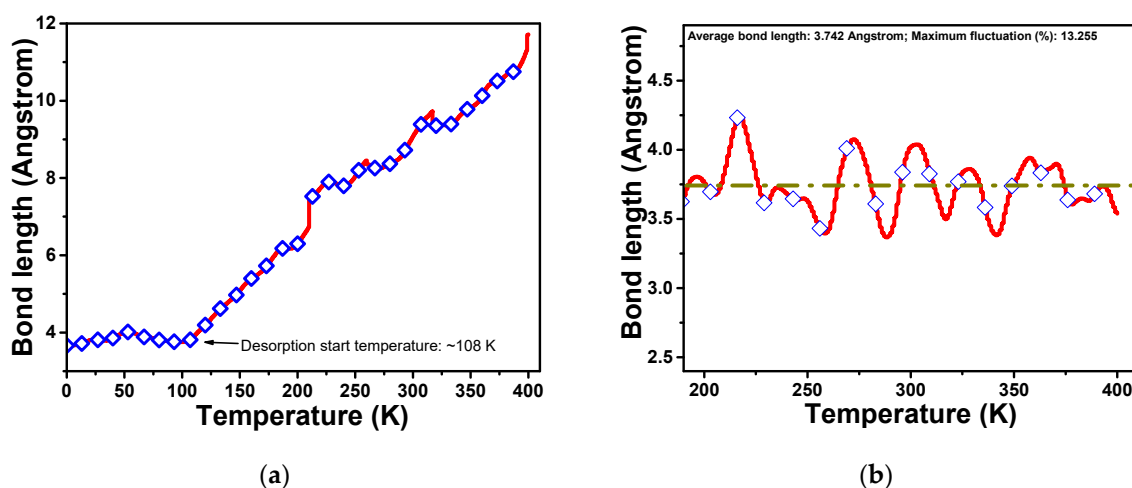


Figure 9. Variation of bond length N-V with the temperature during AIMD simulations for (a) $VSe_2 + NH_3$ (b) $VSe_2(Se_v) + NH_3$; for pristine VSe_2 , NH_3 is desorbed while for $VSe_2(Se_v)$ it remains intact.

3.7. Recovery time (τ)

The reversible sensors could be used repeatedly and hence, are economically convenient for utilization in industrial sectors [65]. The recovery time analysis helps to determine the extent to which a sensor can be used reversibly. The recovery time determines the time required for an analyte to desorb from the host surface. It can be computed using the following equation [65]:

$$\tau = \nu^{-1} \exp(-E_{ads}/kT) \quad (2)$$

In the equation, the ν denotes the frequency factor or the reciprocal of the pre-exponential factor of the Arrhenius equation [87]. The terms E_{ads} , k , and T denote the adsorption energy, Boltzmann constant, and temperature, respectively.

Using this equation, the recovery time for $VSe_2 + NH_3$ and $VSe_2(Se_v) + NH_3$ systems were computed at 300 K and 500 K for visible yellow light and UV light. The τ values are shown in Table 3. The tabulated values show that at 300 K under UV radiation, $VSe_2(Se_v) + NH_3$ system promises a convenient recovery time (~ 2 s). This suggests that $VSe_2(Se_v) + NH_3$ system can act as a reusable sensor.

Table 3. Recovery time for $VSe_2 + NH_3$ and $VSe_2(Se_v) + NH_3$ systems at 300 K and 500 K for yellow light and UV light.

System	Recovery Time (s)			
	Yellow Light ($\nu = \sim 5.2 \times 10^{14}$ Hz)		UV Radiation ($\nu = 1 \times 10^{14}$ Hz)	
	300 K	500 K	300 K	500 K
$VSe_2 + NH_3$ (with VdW)	1.97×10^{-13}	3.09×10^{-14}	1.02×10^{-14}	1.61×10^{-15}
$VSe_2(Se_v) + NH_3$ (with VdW)	1.92×10^{-15}	1.16×10^{-05}	<u>1.99</u>	6.01×10^{-07}

Apart from the above, response time is also considered a very important parameter for determining the sensitivity of any gas detector. When the gas is initially applied, it takes a few seconds for the sensor output current to attain steady-state conditions [88]. The response time of the sensor is commonly specified by the T_{90} or T_{50} time. T_{90} is the time for the sensor's response current to reach 90% of its steady-state value. Similarly, the T_{50} metric is the time required for the sensor to reach 50% of its steady-state value [88]. Future progress in this work can consist of determining the response time for VSe_2 to detect NH_3 .

In spite of promising results, improvements in 2D VSe_2 are needed to attain better sensitivity, selectivity, and stability. Specifically, there is scope for improvement in recovery time owing to the slow gas desorption process to enable it suitable for usage at

room temperature. Currently, this kind of resource seems to be substandard in terms of sensing presentations when contrasted with metal oxide nanostructures; however, their performance is on par with that of pristine graphene. The technology available as of now to physically fabricate planer structures is still not industrially budget-friendly, so more technological advancement is necessary.

4. Conclusions

The structural, electronic, and sensing properties of pure and defected VSe₂ monolayers have been investigated with density functional theory calculations. The energetic stability of VSe₂(Se_v) + NH₃ and VSe₂(V_v) + NH₃ monolayers is studied as adsorption energy values. The VSe₂(Se_v) binds strongly with the adsorbed NH₃ molecule compared to the pure nanomaterial. With the introduction of Se vacancy, the adsorption energy increases from −0.12 eV in the pristine case to −0.97 eV for VSe₂(Se_v). Charge transfer from NH₃ to defected VSe₂ is responsible for stronger adsorption. It has been observed that NH₃ acts as a charge donor and the host, i.e., VSe₂, as a charge acceptor to cause the adsorption to be effective. The thermal stability of the VSe₂(Se_v) + NH₃ system was investigated by performing ab initio molecular dynamics simulations at 300 K and 400 K and the system was found to be structurally stable even at higher temperatures. The recovery time analysis suggests that the VSe₂(Se_v) monolayer can act as a reusable nanosensor. The present studies show that the sensing properties of the VSe₂ monolayer can be significantly improved with the introduction of Se-defects in the lattice structure. Or, in other words, tuning structural and electronic properties through the introduction of Se vacancy aids in enhancing the sensing properties of the VSe₂ monolayer for NH₃ adsorption. The obtained results will be potentially helpful for experimentalists to design defect-engineered TMD-based novel gas sensors.

Supplementary Materials: The following supporting information can be downloaded at: <https://www.mdpi.com/article/10.3390/bios13020257/s1>, Table S1: Adsorption energies for the adsorption of NH₃ on VSe₂ at different sites.

Author Contributions: G.S. software, writing and editing draft, making illustrations; S.P.K. writing original draft; C.S.R. support and supervision; B.C. conceptualization, software, editing draft, and overall supervision. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: The data presented in this study are available on reasonable request to the corresponding author.

Acknowledgments: B.C. would like to thank Nandini Garg, T. Sakuntala, S. M. Yusuf, and A. K. Mohanty for their encouragement and support and the staff of the computer division of BARC for availing facility for supercomputing.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Kong, J.; Franklin, N.R.; Zhou, C.; Chapline, M.G.; Peng, S.; Cho, K.; Dai, H. Nanotube molecular wires as chemical sensors. *Science* **2000**, *287*, 622–625. [[CrossRef](#)]
2. Mirzaei, A.; Lee, J.-H.; Majhi, S.M.; Weber, M.; Bechelany, M.; Kim, H.W.; Kim, S.S. Resistive gas sensors based on metal-oxide nanowires. *J. Appl. Phys.* **2019**, *126*, 241102. [[CrossRef](#)]
3. Chen, X.; Wong, C.K.Y.; Yuan, C.A.; Zhang, G. Nanowire-based gas sensors. *Sens. Actuators B Chem.* **2013**, *177*, 178–195. [[CrossRef](#)]
4. Sun, Y.; Chen, L.; Zhang, F.; Li, D.; Pan, H.; Ye, J. First-principles studies of HF molecule adsorption on intrinsic graphene and Al-doped graphene. *Solid State Commun.* **2010**, *150*, 1906–1910. [[CrossRef](#)]
5. Zhang, J.; Qin, Z.; Zeng, D.; Xie, C. Metal-oxide-semiconductor based gas sensors: Screening, preparation, and integration. *Phys. Chem. Chem. Phys.* **2017**, *19*, 6313–6329. [[CrossRef](#)]

6. Wang, C.; Yin, L.; Zhang, L.; Xiang, D.; Gao, R. Metal oxide gas sensors: Sensitivity and influencing factors. *Sensors* **2010**, *10*, 2088–2106. [[CrossRef](#)]
7. Cai, Z.; Liu, B.; Zou, X.; Cheng, H.-M. Chemical vapor deposition growth and applications of two-dimensional materials and their heterostructures. *Chem. Rev.* **2018**, *118*, 6091–6133. [[CrossRef](#)]
8. Hussain, T.; Hankel, M.; Searles, D.J. Improving sensing of sulfur-containing gas molecules with ZnO monolayers by implanting dopants and defects. *J. Phys. Chem. C* **2017**, *121*, 24365–24375. [[CrossRef](#)]
9. Oudenhoven, J.F.M.; Knoblen, W.; Van Schaijk, R. Electrochemical detection of ammonia using a thin ionic liquid film as the electrolyte. *Procedia Eng.* **2015**, *120*, 983–986. [[CrossRef](#)]
10. Amirjani, A.; Fatmehsari, D.H. Colorimetric detection of ammonia using smartphones based on localized surface plasmon resonance of silver nanoparticles. *Talanta* **2018**, *176*, 242–246. [[CrossRef](#)]
11. Arya, S.; Riyas, M.; Sharma, A.; Singh, B.; Prerna; Bandhoria, P.; Khan, S.; Bharti, V. Electrochemical detection of ammonia solution using tin oxide nanoparticles synthesized via sol–gel route. *Appl. Phys. A* **2018**, *124*, 538. [[CrossRef](#)]
12. Ben Aziza, Z.; Zhang, Q.; Baillargeat, D. Graphene/mica based ammonia gas sensors. *Appl. Phys. Lett.* **2014**, *105*, 254102. [[CrossRef](#)]
13. Geim, A.K.; Novoselov, K.S. The rise of graphene. In *Nanoscience and Technology: A Collection of Reviews from Nature Journals*; World Scientific: Singapore, 2010; pp. 11–19.
14. Radisavljevic, B.; Radenovic, A.; Brivio, J.; Giacometti, V.; Kis, A. Single-layer MoS₂ transistors. *Nat. Nanotechnol.* **2011**, *6*, 147–150. [[CrossRef](#)] [[PubMed](#)]
15. Hussain, T.; De Sarkar, A.; Ahuja, R. Functionalization of hydrogenated graphene by polyolithiated species for efficient hydrogen storage. *Int. J. Hydrog. Energy* **2014**, *39*, 2560–2566. [[CrossRef](#)]
16. Yagmurcukardes, M.; Peeters, F.M. Stable single layer of Janus MoSO: Strong out-of-plane piezoelectricity. *Phys. Rev. B* **2020**, *101*, 155205. [[CrossRef](#)]
17. Yagmurcukardes, M.; Qin, Y.; Ozen, S.; Sayyad, M.; Peeters, F.M.; Tongay, S.; Sahin, H. Quantum properties and applications of 2D Janus crystals and their superlattices. *Appl. Phys. Rev.* **2020**, *7*, 011311. [[CrossRef](#)]
18. Li, L.L.; Bacaksiz, C.; Nakhaee, M.; Pentcheva, R.; Peeters, F.M.; Yagmurcukardes, M. Single-layer Janus black arsenic-phosphorus (b-AsP): Optical dichroism, anisotropic vibrational, thermal, and elastic properties. *Phys. Rev. B* **2020**, *101*, 134102. [[CrossRef](#)]
19. Wang, T.; Huang, D.; Yang, Z.; Xu, S.; He, G.; Li, X.; Hu, N.; Yin, G.; He, D.; Zhang, L. A review on graphene-based gas/vapor sensors with unique properties and potential applications. *Nano-Micro Lett.* **2016**, *8*, 95–119. [[CrossRef](#)] [[PubMed](#)]
20. Nag, A.; Mitra, A.; Mukhopadhyay, S.C. Graphene and its sensor-based applications: A review. *Sens. Actuators A Phys.* **2018**, *270*, 177–194. [[CrossRef](#)]
21. Yang, S.; Jiang, C.; Wei, S.-H. Gas sensing in 2D materials. *Appl. Phys. Rev.* **2017**, *4*, 021304. [[CrossRef](#)]
22. Pospischil, A.; Furchi, M.M.; Mueller, T. Solar-energy conversion and light emission in an atomic monolayer p–n diode. *Nat. Nanotechnol.* **2014**, *9*, 257–261. [[CrossRef](#)] [[PubMed](#)]
23. Shukla, V.; Wärnå, J.; Jena, N.K.; Grigoriev, A.; Ahuja, R. Toward the realization of 2D borophene based gas sensor. *J. Phys. Chem. C* **2017**, *121*, 26869–26876. [[CrossRef](#)]
24. Huang, C.-S.; Murat, A.; Babar, V.; Montes, E.; Schwingschloögl, U. Adsorption of the Gas Molecules NH₃, NO, NO₂, and CO on Borophene. *J. Phys. Chem. C* **2018**, *122*, 14665–14670. [[CrossRef](#)]
25. Shen, J.; Yang, Z.; Wang, Y.; Xu, L.-C.; Liu, R.; Liu, X. Organic gas sensing performance of the borophene van der Waals heterostructure. *J. Phys. Chem. C* **2020**, *125*, 427–435. [[CrossRef](#)]
26. Babar, V.; Sharma, S.; Schwingschloögl, U. Gas sensing performance of pristine and monovacant C₆BN monolayers evaluated by density functional theory and the nonequilibrium green’s function formalism. *J. Phys. Chem. C* **2020**, *124*, 5853–5860. [[CrossRef](#)]
27. Gupta, S.K.; Singh, D.; Rajput, K.; Sonvane, Y. Germanene: A new electronic gas sensing material. *RSC Adv.* **2016**, *6*, 102264–102271. [[CrossRef](#)]
28. Song, Z.; Ang, W.L.; Sturala, J.; Mazanek, V.; Marvan, P.; Sofer, Z.; Ambrosi, A.; Ding, C.; Luo, X.; Bonanni, A. Functionalized germanene-based nanomaterials for the detection of single nucleotide polymorphism. *ACS Appl. Nano Mater.* **2021**, *4*, 5164–5175. [[CrossRef](#)]
29. Sosa, A.N.; Santana, J.E.; Miranda, Á.; Pérez, L.A.; Trejo, A.; Salazar, F.; Cruz-Irisson, M. NH₃ capture and detection by metal-decorated germanene: A DFT study. *J. Mater. Sci.* **2022**, *57*, 8516–8529. [[CrossRef](#)]
30. Xu, K.; Liao, N.; Zheng, B.; Zhou, H. Adsorption and diffusion behaviors of H₂, H₂S, NH₃, CO and H₂O gases molecules on MoO₃ monolayer: A DFT study. *Phys. Lett. A* **2020**, *384*, 126533. [[CrossRef](#)]
31. Qu, Y.; Ding, J.; Fu, H.; Peng, J.; Chen, H. Adsorption of CO, NO, and NH₃ on ZnO monolayer decorated with noble metal (Ag, Au). *Appl. Surf. Sci.* **2020**, *508*, 145202. [[CrossRef](#)]
32. Lv, Y.; Wang, Y.; Zhang, H.; Dai, C. Adsorption of NH₃ and NO₂ molecules on the carbon doped C₃N monolayer: A first principles study. *Comput. Theor. Chem.* **2021**, *1195*, 113075. [[CrossRef](#)]
33. Kou, L.; Du, A.; Chen, C.; Frauenheim, T. Strain engineering of selective chemical adsorption on monolayer MoS₂. *Nanoscale* **2014**, *6*, 5156–5161. [[CrossRef](#)]
34. He, Q.; Zeng, Z.; Yin, Z.; Li, H.; Wu, S.; Huang, X.; Zhang, H. Fabrication of flexible MoS₂ thin-film transistor arrays for practical gas-sensing applications. *Small* **2012**, *8*, 2994–2999. [[CrossRef](#)] [[PubMed](#)]

35. Kim, S.; Konar, A.; Hwang, W.-S.; Lee, J.H.; Lee, J.; Yang, J.; Jung, C.; Kim, H.; Yoo, J.-B.; Choi, J.-Y.; et al. High-mobility and low-power thin-film transistors based on multilayer MoS₂ crystals. *Nat. Commun.* **2012**, *3*, 1011. [[CrossRef](#)] [[PubMed](#)]
36. Radisavljevic, B.; Whitwick, M.B.; Kis, A. Integrated circuits and logic operations based on single-layer MoS₂. *ACS Nano* **2011**, *5*, 9934–9938. [[CrossRef](#)]
37. Babar, V.; Vovusha, H.; Schwingenschloögl, U. Density functional theory analysis of gas adsorption on monolayer and few layer transition metal dichalcogenides: Implications for sensing. *ACS Appl. Nano Mater.* **2019**, *2*, 6076–6080. [[CrossRef](#)]
38. Abbasi, A.; Sardroodi, J.J. Adsorption of O₃, SO₂ and SO₃ gas molecules on MoS₂ monolayers: A computational investigation. *Appl. Surf. Sci.* **2019**, *469*, 781–791. [[CrossRef](#)]
39. Deng, X.; Liang, X.; Ng, S.-P.; Wu, C.-M.L. Adsorption of formaldehyde on transition metal doped monolayer MoS₂: A DFT study. *Appl. Surf. Sci.* **2019**, *484*, 1244–1252. [[CrossRef](#)]
40. Nayeri, M.; Moradinasab, M.; Fathipour, M. The transport and optical sensing properties of MoS₂, MoSe₂, WS₂ and WSe₂ semiconducting transition metal dichalcogenides. *Semicond. Sci. Technol.* **2018**, *33*, 025002. [[CrossRef](#)]
41. Abbas, H.G.; Debela, T.T.; Hussain, S.; Hussain, I. Inorganic molecule (O₂, NO) adsorption on nitrogen-and phosphorus-doped MoS₂ monolayer using first principle calculations. *RSC Adv.* **2018**, *8*, 38656–38666. [[CrossRef](#)]
42. Cabral, L.; Sabino, F.P.; Lima, M.P.; Marques, G.E.; Lopez-Richard, V.; Da Silva, J.L.F. Azobenzene Adsorption on the MoS₂(0001) Surface: A Density Functional Investigation within van der Waals Corrections. *J. Phys. Chem. C* **2018**, *122*, 18895–18901. [[CrossRef](#)]
43. Ma, D.; Ma, B.; Lu, Z.; He, C.; Tang, Y.; Lu, Z.; Yang, Z. Interaction between H₂O, N₂, CO, NO, NO₂ and N₂O molecules and a defective WSe₂ monolayer. *Phys. Chem. Chem. Phys.* **2017**, *19*, 26022–26033. [[CrossRef](#)] [[PubMed](#)]
44. Idrees, M.; Din, H.U.; Ali, R.; Rehman, G.; Hussain, T.; Nguyen, C.V.; Ahmad, I.; Amin, B. Optoelectronic and solar cell applications of Janus monolayers and their van der Waals heterostructures. *Phys. Chem. Chem. Phys.* **2019**, *21*, 18612–18621. [[CrossRef](#)]
45. Ma, X.; Wu, X.; Wang, H.; Wang, Y. A Janus MoSSe monolayer: A potential wide solar-spectrum water-splitting photocatalyst with a low carrier recombination rate. *J. Mater. Chem. A* **2018**, *6*, 2295–2301. [[CrossRef](#)]
46. Jin, C.; Tang, X.; Tan, X.; Smith, S.C.; Dai, Y.; Kou, L. A Janus MoSSe monolayer: A superior and strain-sensitive gas sensing material. *J. Mater. Chem. A* **2019**, *7*, 1099–1106. [[CrossRef](#)]
47. Shang, C.; Lei, X.; Hou, B.; Wu, M.; Xu, B.; Liu, G.; Ouyang, C. Theoretical prediction of Janus MoSSe as a potential anode material for lithium-ion batteries. *J. Phys. Chem. C* **2018**, *122*, 23899–23909. [[CrossRef](#)]
48. Dong, L.; Lou, J.; Shenoy, V.B. Large in-plane and vertical piezoelectricity in Janus transition metal dichalcogenides. *ACS Nano* **2017**, *11*, 8242–8248. [[CrossRef](#)]
49. Li, Y.; Wang, J.; Zhou, B.; Wang, F.; Miao, Y.; Wei, J.; Zhang, B.; Zhang, K. Tunable interlayer coupling and Schottky barrier in graphene and Janus MoSSe heterostructures by applying an external field. *Phys. Chem. Chem. Phys.* **2018**, *20*, 24109–24116. [[CrossRef](#)]
50. Kaur, S.P.; Kumar, T.J.D. Tuning structure, electronic, and catalytic properties of non-metal atom doped Janus transition metal dichalcogenides for hydrogen evolution. *Appl. Surf. Sci.* **2021**, *552*, 149146. [[CrossRef](#)]
51. Chaurasiya, R.; Dixit, A. Defect engineered MoSSe Janus monolayer as a promising two dimensional material for NO₂ and NO gas sensing. *Appl. Surf. Sci.* **2019**, *490*, 204–219. [[CrossRef](#)]
52. Sanyal, G.; Vaidyanathan, A.; Rout, C.S.; Chakraborty, B. Recent developments in two-dimensional layered tungsten dichalcogenides based materials for gas sensing applications. *Mater. Today Commun.* **2021**, *28*, 102717. [[CrossRef](#)]
53. Shankar, P.; Rayappan, J.B.B. Gas sensing mechanism of metal oxides: The role of ambient atmosphere, type of semiconductor and gases-A review. *Sci. Lett. J.* **2015**, *4*, 126.
54. Yuan, H.T.; Toh, M.; Morimoto, K.; Tan, W.; Wei, F.; Shimotani, H.; Kloc, C.; Iwasa, Y. Liquid-gated electric-double-layer transistor on layered metal dichalcogenide, SnS₂. *Appl. Phys. Lett.* **2011**, *98*, 012102. [[CrossRef](#)]
55. Pu, J.; Yomogida, Y.; Liu, K.-K.; Li, L.-J.; Iwasa, Y.; Takenobu, T. Highly flexible MoS₂ thin-film transistors with ion gel dielectrics. *Nano Lett.* **2012**, *12*, 4013–4017. [[CrossRef](#)]
56. Xie, J.; Zhang, J.; Li, S.; Grote, F.; Zhang, X.; Zhang, H.; Wang, R.; Lei, Y.; Pan, B.; Xie, Y. Controllable disorder engineering in oxygen-incorporated MoS₂ ultrathin nanosheets for efficient hydrogen evolution. *J. Am. Chem. Soc.* **2013**, *135*, 17881–17888. [[CrossRef](#)]
57. Liu, P.; Zhu, J.; Zhang, J.; Xi, P.; Tao, K.; Gao, D.; Xue, D. P dopants triggered new basal plane active sites and enlarged interlayer spacing in MoS₂ nanosheets toward electrocatalytic hydrogen evolution. *ACS Energy Lett.* **2017**, *2*, 745–752. [[CrossRef](#)]
58. Suh, J.; Park, T.-E.; Lin, D.-Y.; Fu, D.; Park, J.; Jung, H.J.; Chen, Y.; Ko, C.; Jang, C.; Sun, Y.; et al. Doping against the native propensity of MoS₂: Degenerate hole doping by cation substitution. *Nano Lett.* **2014**, *14*, 6976–6982. [[CrossRef](#)]
59. Choi, S.Y.; Kim, Y.; Chung, H.-S.; Kim, A.R.; Kwon, J.-D.; Park, J.; Kim, Y.L.; Kwon, S.-H.; Hahm, M.G.; Cho, B. Effect of Nb doping on chemical sensing performance of two-dimensional layered MoSe₂. *ACS Appl. Mater. Interfaces* **2017**, *9*, 3817–3823. [[CrossRef](#)]
60. Panigrahi, P.; Hussain, T.; Karton, A.; Ahuja, R. Elemental substitution of two-dimensional transition metal dichalcogenides (MoSe₂ and MoTe₂): Implications for enhanced gas sensing. *ACS Sens.* **2019**, *4*, 2646–2653. [[CrossRef](#)]
61. Zhu, J.; Zhang, H.; Tong, Y.; Zhao, L.; Zhang, Y.; Qiu, Y.; Lin, X. First-principles investigations of metal (V, Nb, Ta)-doped monolayer MoS₂: Structural stability, electronic properties and adsorption of gas molecules. *Appl. Surf. Sci.* **2017**, *419*, 522–530. [[CrossRef](#)]

62. Luo, H.; Cao, Y.; Zhou, J.; Feng, J.; Cao, J.; Guo, H. Adsorption of NO₂, NH₃ on monolayer MoS₂ doped with Al, Si, and P: A first-principles study. *Chem. Phys. Lett.* **2016**, *643*, 27–33. [[CrossRef](#)]
63. Kaur, S.P.; Hussain, T.; Kumar, T.J.D. Substituted 2D Janus WSe monolayers as efficient nanosensor toward toxic gases. *J. Appl. Phys.* **2021**, *130*, 014501. [[CrossRef](#)]
64. Sanyal, G.; Lakshmy, S.; Vaidyanathan, A.; Kalarikkal, N.; Chakraborty, B. Detection of nitrobenzene in pristine and metal decorated 2D dichalcogenide VSe₂: Perspectives from density functional theory. *Surf. Interfaces* **2022**, *29*, 101816. [[CrossRef](#)]
65. Chakraborty, B.; Vaidyanathan, A.; Sanyal, G.; Lakshmy, S.; Kalarikkal, N. Transition metal decorated VSe₂ as promising catechol sensor: Insights from DFT simulations. *J. Appl. Phys.* **2022**, *132*, 084502. [[CrossRef](#)]
66. Liu, Y.; Xiao, C.; Li, Z.; Xie, Y. Vacancy engineering for tuning electron and phonon structures of two-dimensional materials. *Adv. Energy Mater.* **2016**, *6*, 1600436. [[CrossRef](#)]
67. Zhang, C.; Liu, G.; Geng, X.; Wu, K.; Debliquy, M. Metal oxide semiconductors with highly concentrated oxygen vacancies for gas sensing materials: A review. *Sens. Actuators A Phys.* **2020**, *309*, 112026. [[CrossRef](#)]
68. Al-Hashem, M.; Akbar, S.; Morris, P. Role of oxygen vacancies in nanostructured metal-oxide gas sensors: A review. *Sens. Actuators B Chem.* **2019**, *301*, 126845. [[CrossRef](#)]
69. Guo, X.; Shi, Y.; Ding, Y.; He, Y.; Du, B.; Liang, C.; Tan, Y.; Liu, P.; Miao, X.; He, Y.; et al. Indium-doping-induced selenium vacancy engineering of layered tin diselenide for improving room-temperature sulfur dioxide gas sensing. *J. Mater. Chem. A* **2022**, *10*, 22629–22637. [[CrossRef](#)]
70. Qin, Z.; Xu, K.; Yue, H.; Wang, H.; Zhang, J.; Ouyang, C.; Xie, C.; Zeng, D. Enhanced room-temperature NH₃ gas sensing by 2D SnS₂ with sulfur vacancies synthesized by chemical exfoliation. *Sens. Actuators B Chem.* **2018**, *262*, 771–779. [[CrossRef](#)]
71. Xia, Y.; Hu, C.; Guo, S.; Zhang, L.; Wang, M.; Peng, J.; Xu, L.; Wang, J. Sulfur-vacancy-enriched MoS₂ nanosheets based heterostructures for near-infrared optoelectronic NO₂ sensing. *ACS Appl. Nano Mater.* **2019**, *3*, 665–673. [[CrossRef](#)]
72. Norouzzadeh, E.; Mohammadi, S.; Moradinasab, M. First principles characterization of defect-free and vacancy-defected monolayer PtSe₂ gas sensors. *Sens. Actuators A Phys.* **2020**, *313*, 112209. [[CrossRef](#)]
73. Chen, D.; Zhang, X.; Xiong, H.; Li, Y.; Tang, J.; Xiao, S.; Zhang, D. A first-principles study of the SF₆ decomposed products adsorbed over defective WS₂ monolayer as promising gas sensing device. *IEEE Trans. Device Mater. Reliab.* **2019**, *19*, 473–483. [[CrossRef](#)]
74. Kresse, G.; Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **1996**, *6*, 15–50. [[CrossRef](#)]
75. Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54*, 11169. [[CrossRef](#)]
76. Kresse, G.; Hafner, J. Ab initio molecular-dynamics simulation of the liquid-metal–amorphous-semiconductor transition in germanium. *Phys. Rev. B* **1994**, *49*, 14251. [[CrossRef](#)]
77. Kresse, G.; Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **1993**, *47*, 558. [[CrossRef](#)]
78. Perdew, J.P.; Burke, K.; Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **1996**, *77*, 3865. [[CrossRef](#)]
79. Grimme, S.; Antony, J.; Ehrlich, S.; Krieg, H. A consistent and accurate ab initio parametrization of density functional dispersion correction (DFT-D) for the 94 elements H–Pu. *J. Chem. Phys.* **2010**, *132*, 154104. [[CrossRef](#)]
80. Grimme, S. Density functional theory with London dispersion corrections. *WIREs Comput. Mol. Sci.* **2011**, *1*, 211–228. [[CrossRef](#)]
81. Monkhorst, H.J.; Pack, J.D. Special points for Brillouin-zone integrations. *Phys. Rev. B* **1976**, *13*, 5188. [[CrossRef](#)]
82. Tang, W.; Sanville, E.; Henkelman, G. A grid-based Bader analysis algorithm without lattice bias. *J. Phys. Condens. Matter* **2009**, *21*, 084204. [[CrossRef](#)] [[PubMed](#)]
83. Mi, H.; Zhou, Q.; Zeng, W. A density functional theory study of the adsorption of Cl₂, NH₃, and NO₂ on Ag₃-doped WSe₂ monolayers. *Appl. Surf. Sci.* **2021**, *563*, 150329. [[CrossRef](#)]
84. Cho, B.; Hahm, M.G.; Choi, M.; Yoon, J.; Kim, A.R.; Lee, Y.-J.; Park, S.-G.; Kwon, J.-D.; Kim, C.S.; Song, M.; et al. Charge-transfer-based gas sensing using atomic-layer MoS₂. *Sci. Rep.* **2015**, *5*, 8052. [[CrossRef](#)] [[PubMed](#)]
85. Tian, X.; Yao, L.; Cui, X.; Zhao, R.; Chen, T.; Xiao, X.; Wang, Y. A two-dimensional Ti₃C₂T_X MXene@TiO₂/MoS₂ heterostructure with excellent selectivity for the room temperature detection of ammonia. *J. Mater. Chem. A* **2022**, *10*, 5505–5519. [[CrossRef](#)]
86. Zheng, Y.; Sun, L.; Liu, W.; Wang, C.; Dai, Z.; Ma, F. Tungsten oxysulfide nanosheets for highly sensitive and selective NH₃ sensing. *J. Mater. Chem. C* **2020**, *8*, 4206–4214. [[CrossRef](#)]
87. Arrhenius, S. Über die Dissociationswärme und den Einfluss der Temperatur auf den Dissociationsgrad der Elektrolyte. *Zeitschrift für physikalische Chemie* **1889**, *4*, 96–116. [[CrossRef](#)]
88. Warburton, P.R.; Pagano, M.P.; Hoover, R.; Logman, M.; Crytzer, K.; Warburton, Y.J. Amperometric gas sensor response times. *Anal. Chem.* **1998**, *70*, 998–1006. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.